

Catalysis Science & Technology

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: N. Martin, P. Velin, M. Skoglundh, M. Bauer and P. Carlsson, *Catal. Sci. Technol.*, 2017, DOI: 10.1039/C6CY02536F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/xxxxxxxxxx

Catalytic hydrogenation of CO₂ to methane over supported Pd, Rh and Ni catalysts[†]

Natalia M. Martin,^{*a} Peter Velin,^a Magnus Skoglundh,^a Matthias Bauer,^b and Per-Anders Carlsson^a

Received Date

Accepted Date

DOI: 10.1039/xxxxxxxxxx

www.rsc.org/journalname



As a step in production of so-called electrofuels, ambient pressure CO₂ hydrogenation has been investigated over different catalytic model systems based on metal particles (Pd, Rh and Ni) supported on various metal oxides (SiO₂, Al₂O₃ and CeO₂) and aluminosilicates (ZSM-5 and MCM-41) at different specific reactant ratios and temperatures between 150 and 450 °C. Catalytic activity and selectivity measurements in a flow reactor show that the highest CO₂ conversion towards methane is obtained for the Rh/Al₂O₃ and Rh/CeO₂ catalysts, followed by Ni/CeO₂. Generally, the results suggest that both the support material and reaction conditions play an important role in the hydrogenation process. Further, *in situ* diffusive reflectance infrared Fourier transform spectroscopy revealed the intermediate species during transient CO₂ hydrogenation over the Rh and Ni containing catalysts. Adsorption and dissociation of CO₂ occurs over the Rh/Al₂O₃ catalyst in the presence of H₂, resulting in the formation of linear Rh-CO species, while formates and carbonates are formed over the Rh/CeO₂ and Ni/CeO₂ catalysts, likely at the metal-support interface.

1 Introduction

Because of the high demand on the limited fossil fuel resources and the environmental problems associated with the increased anthropogenic CO₂ emissions, significant attention is paid to exploring means to utilise CO₂ as a renewable source of energy. A possible viable route for recycling of CO₂ is through catalytic hydrogenation preferably directly to a usable hydrocarbon-based fuel, e.g., methane, methanol or dimethyl ether¹. Although some progress has been made in this direction^{2,3}, development of efficient routes for CO₂ hydrogenation to produce such green fuels remains an important topic in catalysis. In particular, the promising progress in sustainable production of H₂ by wind and/or solar powered electrolysis of water or by photocatalytic water splitting⁴ stimulates studies on catalytic CO₂ hydrogenation at ambient pressures as a realistic technology for producing so-called electrofuels or sunfuels through CO₂ recycling not only at large scale biorefineries but also at smaller scale remote plants⁵.

To catalyse the reaction between CO₂ and H₂, surface sites that bind and activate CO₂ need to co-exist and cooperate with sites

for dissociation of H₂. Activation of CO₂ by heterogeneous catalysis is often carried out using basic or amphoteric reducible oxides as for example ceria, zirconia or titania, while metals are most frequently used to dissociate H₂. The transformation of CO₂, however, is still an issue due to the difficulties in activating the thermodynamically stable CO₂ molecule, a process that is highly energy-intensive⁶. In the present study, the conversion of CO₂ into methane and/or methanol is the prime target. There are different competing reactions during CO₂ hydrogenation, the ones relevant for this study being enumerated in equations (1)-(3) below.



The formation of by-products and particularly the formation of carbon monoxide and water through the strongly competing reverse water-gas shift reaction (rWGS, eq. (1)), consumes CO₂ and H₂ such that the desired product formation and thereby the selectivity become low. Therefore, the sole formation of the desired product is not an easy task. For several decades, methanol has been produced industrially over Cu-ZnO/Al₂O₃ catalysts at 200-300 °C and 50-100 bar using syngas (CO/H₂/CO₂)^{7,8}. Using the industrial Cu-ZnO/Al₂O₃ catalyst at low pressures methanol synthesis leads to significant CO production, lowering the desired product formation, suggesting that a low-pressure CO₂ reduction

^a Competence Centre for Catalysis, Chalmers University of Technology, Gothenburgh, 412 96, Sweden Fax: +46 31 160062; Tel: +46 31 772 29 04; E-mail: Natalia.Martin@chalmers.se

^b Department of Chemistry, Paderborn University, 33098 Paderborn, Germany.

[†] Electronic Supplementary Information (ESI) available: [Figures S1-S2]. See DOI: 10.1039/b000000x/

process may require a different catalyst⁹. An important challenge for atmospheric pressure CO₂ hydrogenation is to design catalysts that efficiently can suppress the rWGS reaction as well as formation of other by-products in favour of methanol and/or methane formation.

Hydrogenation of CO₂ to methane (eq. (2)) is the most advantageous reaction with respect to thermodynamics ($\Delta G_{298} = -130.8 \text{ kJmol}^{-1}$) among the CO₂ conversion reactions. Previous work has reported different transition metals such as Ru, Rh, Ni and Pd to be highly active and selective for the methane formation by CO₂ hydrogenation, especially at low temperatures^{10–12}. Among these, the supported Ni catalysts were reported to have the highest selectivity to form methane¹³.

In the present work we have synthesised and studied industrially relevant polycrystalline catalysts that can bind CO₂ and facilitate H₂ dissociation and further reaction with activated CO₂ to form methane at atmospheric pressure conditions. We also consider possible methanol formation, even though no methanol has been observed to form in the present study, under the investigated conditions. A series of metal oxide supported catalysts containing Pd, Ni and Rh have been prepared with impregnation and ion-exchange methods, characterised and evaluated in terms of activity and selectivity for CO₂ hydrogenation. The kinetic study showed an increased conversion of CO₂ to methane and CO at elevated temperature, with varying selectivity depending on the active phase. The Rh/Al₂O₃ and Rh/CeO₂ catalysts were singled out as the ones giving the highest CO₂ conversion and lowest selectivity for the rWGS reaction in the methanation reaction, followed by the Ni/CeO₂ catalyst. Furthermore, ceria is concluded to be the most active support for hydrogenation of CO₂, probably due to a participating role in CO₂ adsorption and a highly dispersed active phase. In addition, the CO₂ methanation reaction mechanism was investigated by *in situ* diffusive reflectance Fourier transform infrared spectroscopy and the results reveal clear differences between Rh/Al₂O₃ and Rh/CeO₂ catalysts.

2 Experimental section

2.1 Catalyst preparation and *ex situ* characterization

In this study, 13 different catalysts were prepared with Pd, Ni and Rh supported on silica, alumina, ceria, MCM-41 and ZSM-5. The samples with silica, alumina, ceria and MCM-41 were prepared by incipient wetness impregnation, while the Ni/ZSM-5 sample was prepared by ion-exchange as described below. Powders of silica (Kromasil Silica KR-300-10, Akzo Nobel Eka Chemicals), alumina (Puralox SBa200, Sasol) and ceria (99.5 H.S.A. 514, Rhône-Poulenc) were calcined in air at 600 °C for 2 h starting from room temperature with a heating rate of 5 °C/min to remove carbonaceous impurities and stabilise the structure of the support materials. Since MCM-41 (Sigma-Aldrich) is more fragile, a lower calcination temperature (450 °C) was used for this material. Precursor solutions of nickel and rhodium were prepared by dissolving Ni(NO₃)₂ × 6H₂O (Alfa Aesar) and Rh(NO₃)₃ × 2H₂O (Alfa Aesar) salts in Milli-Q water (18 MΩ/cm). To increase the solubility of the rhodium salt, 25 droplets of 70% HNO₃ were added. The precursor for palladium was an aqueous solution of the complex

(NH₃)₄Pd(NO₃)₂ (Alfa Aesar). The specific amount of precursor solution to obtain 3 wt.% of the metal was added to 3 g of each support. The impregnated silica, alumina and ceria samples were instantly frozen with liquid nitrogen for 24 h and finally calcined in air at 550 °C for 1 h. After freeze-drying, the impregnated MCM-41 sample was calcined in air at 450 °C for 1 h.

For the Ni/ZSM-5 catalyst, 3 g ZSM-5 (SAR 27, Akzo Nobel) was added to a beaker together with 1.5 liter 0.025 molar nickel nitrate solution. After 24 h of stirring at room temperature the solution was filtered and washed with Milli-Q water. The aqueous ion-exchanged zeolite was then dried at 110 °C for 24 h before calcination in air at 450 °C for 1 h starting from room temperature with a heating rate of 5 °C/min. Table 1 gives an overview of the prepared catalysts.

Monolith samples were prepared by coating corderite monoliths with approximately 200 mg of the powder samples through dip coating. Colloidal alumina sol (Disperal, Sasol) was used as binder for all samples. The monolith samples were thereafter dried at 90 °C in air until all water evaporated and finally calcined at 600 °C for 5 min.

The crystal structure of the as-prepared samples was studied by X-ray diffraction (XRD) under ambient atmosphere using a Bruker AXS D8 ADVANCE diffractometer with Cu-Kα radiation equivalent to 0.15418 nm. The diffraction data was recorded in the 2θ range of 20–66° with incremental steps of 0.03° for 28 minutes.

The specific surface area of the catalysts was determined by nitrogen sorption at 77 K (Micrometrics Tristar 3000) using the Brunauer Emmet and Teller (BET) method¹⁴. The samples were dried in vacuum at 230 °C for 3 h before the measurement.

2.2 Flow-reactor experiments

The catalytic performance of the catalysts was analysed in a flow reactor. An FTIR instrument (MultiGas 2030, MKS Instruments) was used to measure the composition of the effluent gas. The flow reactor, described elsewhere¹⁵, consists of a quartz tube wherein the sample was positioned. Heating of the inlet gas and the sample occurred via resistive heating of a metal coil surrounding the reactor tube. Both the inlet gas and the catalyst temperature were measured by separate thermocouples. Feed gases were mixed from H₂, CO₂ and Ar and introduced into the reactor via individual mass flow controllers, providing a total flow of 2000 ml/min, corresponding to a gas hourly space velocity (GHSV) of about 60000 h⁻¹. Prior to each experiment the samples were pre-treated at 450 °C under a flow of 5% oxygen followed by a flow of 5% hydrogen, each for 10 minutes. The catalytic performance of the catalysts was measured under a flow of 1% CO₂ and 5% H₂, corresponding to a molar ratio of 1:5, for 10 minutes at four different temperatures (450, 350, 250, and 150 °C).

2.3 *In situ* FTIR spectroscopy measurements

The *in situ* FTIR spectroscopy experiments were performed in diffusive reflectance (DRIFT) mode with a BRUKER Vertex 70 spectrometer equipped with a nitrogen cooled MCT detector and a high-temperature stainless steel reaction cell (Harrick Praying Mantis™ High Temperature Reaction Chamber) with KBr win-

Table 1 Metal loading, calcination temperature and specific surface area for the Pd-, Ni-, and Rh-based catalyst samples used in this study.

Sample	Metal loading (wt.%)			Calcination temperature (°C)	Specific surface area (m ² /g)
	Pd	Ni	Rh		
Pd/SiO ₂	3.0	-	-	550	315
Pd/Al ₂ O ₃	3.0	-	-	550	187
Pd/CeO ₂	3.0	-	-	550	131
Pd/MCM-41	3.0	-	-	450	-
Ni/SiO ₂	-	3.0	-	550	311
Ni/Al ₂ O ₃	-	3.0	-	550	182
Ni/CeO ₂	-	3.0	-	550	128
Ni/MCM-41	-	3.0	-	450	-
Ni/ZSM-5	-	1.5	-	450	-
Rh/SiO ₂	-	-	3.0	550	310
Rh/Al ₂ O ₃	-	-	3.0	550	180
Rh/CeO ₂	-	-	3.0	550	125
Rh/MCM-41	-	-	3.0	450	-

dows. The temperature of the sample holder was measured by a thermocouple (type K) and controlled by a PID regulator (Eurotherm). Feed gases were introduced into the reaction cell via individual mass flow controllers, providing a total flow of 100 ml/min in all experiments. Moreover, the H₂ feed was introduced via a high-speed gas valve (Valco, VICI) in order to provide precise transients. Prior to each experiment the samples were pre-treated at 350 °C with 5% O₂ in Ar for 10 min and 0.8% H₂ in Ar for 10 min and then cooled in Ar to the desired temperature where a background spectrum was collected. The experiment started by introducing a flow of 0.2% CO₂ and 0.8% H₂ to the reaction cell. After 10 min the H₂ flow was turned off for 10 min and reintroduced again for 10 minutes. The measurements were repeated five times giving a total length of the experiments of 100 minutes. The hydrogen pulse-response measurements were performed at different temperatures (400, 350, 300, and 250 °C). The region between 790-3800 cm⁻¹ was investigated with a spectral resolution of 8 cm⁻¹. The product stream was continuously analysed with mass spectrometry (Hiden Analytical, HPR-20 QIC) following the m/e ratios 2 (H₂), 15 and 16 (CH₄), 18 (H₂O), 28 (CO), 40 (Ar), and 44 (CO₂).

3 Results and discussion

3.1 *Ex situ* characterization of as-prepared samples

The specific surface areas and the X-ray diffraction patterns of the as-prepared powder catalyst samples are presented in Table 1 and Figure 1, respectively. The surface area measurements reveal that all samples initially have high specific surface areas. The silica supported catalysts had the highest surface area (310-315 m²/g), followed by the alumina (180-187 m²/g) and the ceria (125-131 m²/g) supported catalysts. The surface area measurements of MCM-41 and ZSM-5 were cancelled due to the long measurement times, which indicates that the high surface areas are preserved after metal impregnation and calcination. Figure 1 shows the XRD patterns for the as-prepared Pd-, Ni- and Rh-based catalysts. It can be observed that the pure metal oxide patterns are unaffected by calcination at 600 °C and impregnation with Pd, Ni and Rh, suggesting that the metals are well dispersed over the oxide supports. Additional peaks are observed for some of

the samples, which were found to correspond to the diffraction patterns of PdO, NiO and Rh₂O₃, seen as coloured marks above the diffraction patterns (Figure 1 a), c) and d)). The XRD results indicate that the metal particle sizes are different for the metals supported on each oxide. The metals supported by cerium oxide nearly have diffraction peaks, which might indicate that Pd, Ni, and Rh are in amorphous phase or in extreme small crystalline size (below 3 nm), while the metals supported on silica show diffraction peaks for PdO, NiO and Rh₂O₃. In addition, the broadening of the diffraction peak gives insight into the size of the crystallites: sharp peaks indicate larger crystallites, while broader peaks indicate smaller crystallites. The Ni-silica sample has a very sharp XRD peak for NiO, suggesting a much larger particle size of Ni, compared to the Pd-silica or Rh-silica samples which show broader diffraction peaks. For the alumina supported samples, only Pd-alumina has some reflections originating from PdO, suggesting that this sample has larger particles compared to the other alumina supported samples investigated. For the ion-exchanged sample Ni/ZSM-5, no new reflections are observed compared to the pattern for ZSM-5 suggesting that Ni is highly dispersed in this sample.

3.2 Methanation reaction over Pd-, Ni-, and Rh-based catalysts

Figure 2 shows the catalytic performance of the metal-promoted silica, alumina and ceria samples for CO₂ hydrogenation. The inlet gas concentrations to the flow reactor are 1% CO₂ and 5% H₂ in Ar and each marker in the figure represents the measured average outlet concentration over a 10 min period. The main reaction products formed during CO₂ hydrogenation are CH₄, CO and H₂O. No hydrocarbon compounds except methane are observed. Due to high background, the water signal is not included in Figure 2.

The temperature dependence of CO₂ hydrogenation can clearly be seen for all samples. A clear trend is the increased formation of CO at high temperature, due to the reverse water gas shift reaction¹⁶. The ceria supported catalysts show the highest CO₂ conversion and CH₄ production over the temperature range in-

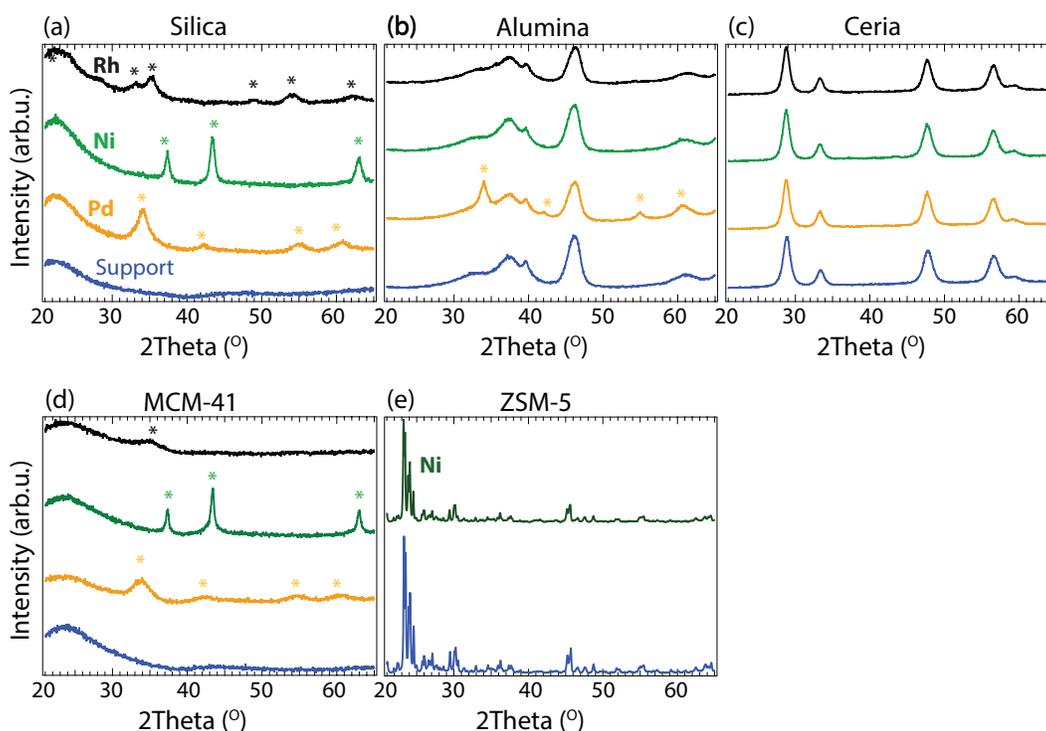


Fig. 1 X-ray diffraction patterns of the support materials (blue) and as-prepared Pd (orange), Ni (green) and Rh (black) catalysts (3 wt.%) supported on a) silica b) alumina c) ceria and d) MCM-41. e) shows the XRD pattern for 1.5 wt.% Ni (dark green) ion-exchanged into ZSM-5.

investigated, followed by the alumina supported catalysts. This can be attributed to metal particle size effects. As discussed above, the catalysts supported on ceria have no metal XRD peaks suggesting amorphous or very small metal particles, followed by the alumina supported catalysts. Among the studied catalysts, the Rh/Al₂O₃ catalyst shows the lowest CO production and highest methane selectivity, up to 350 °C. Over this temperature the CH₄ production declines and the selectivity towards CO increases. The Ni/CeO₂ sample shows the highest CO₂ conversion compared to the other Ni catalysts investigated, in agreement with previous studies¹³. The silica supported catalysts show the overall lowest methane formation also suggested by the larger metal particle sizes as obtained from the XRD measurements. Further, a significant difference in product selectivity between the active metals is observed.

Using MCM-41 as a support gives similar results as the silica supported catalysts described above, with a slightly higher selectivity towards CH₄. However, for Ni/ZSM-5, almost no conversion of CO₂ is observed. The results over the metal-promoted MCM-41 and ZSM-5 samples are shown in Figure S1 (see Electronic Supplementary Information (ESI)[†]). Due to the low catalytic activity for CO₂ hydrogenation (at least below 400 °C), the results of silica, MCM-41 and ZSM-5 catalysts will not be further reported in this study.

The results of a more extended investigation of CO₂ hydrogenation over the Rh/CeO₂ catalyst are shown in Figure 3. The experiment is carried out by measuring the steady-state outlet gas concentrations for inlet concentrations between 0.3 and 1.5% of CO₂ (left panel), and between 1 and 5% H₂ (right panel). Since

no reaction was observed at 150 °C during the previous test, the investigation focused on measuring the activity at 250 (blue), 350 (orange) and 450 °C (grey). At 250 °C, the outlet concentration of CO₂ is the same as the inlet concentration for both experiments, which means that no reaction occurs. At 350 and 450 °C the outlet concentrations of CO₂ and the formation of methane are similar, whereas the formation of CO is considerably higher at the highest temperature. Above an inlet CO₂ concentration of 1%, the increased CO formation gives rise to a slightly higher CO₂ conversion. Initially, for low inlet concentrations of CO₂, the left column shows a higher CH₄ formation at 350 compared to 450 °C. The formation of CH₄ then decreases slightly with increased inlet concentration of CO₂ and becomes lower than at 450 °C for an inlet CO₂ concentration of 1.5%. In the right column one can see a linear increase in CH₄ formation with the same gradient at both 350 and 450 °C when the inlet H₂ concentration is increased. At the same time, the formation of CO decreases linearly with a less steep slope. To obtain higher CO₂ conversion and CH₄ formation it is necessary to increase the H₂:CO₂ ratio.

From all studied catalysts in this work, the ones supported on ceria are found to have the highest activity for CO₂ hydrogenation, followed by the alumina supported catalysts. No considerable methanol production was observed over the studied catalysts under ambient pressure conditions and temperatures up to 450 °C. In addition, the results reveal that the catalysts preparation method and structure play an important role on the catalytic activity and/or selectivity. The catalysts prepared by impregnation show the highest CO₂ conversion activity and the comparison between the different catalysts prepared by impregnation reveals

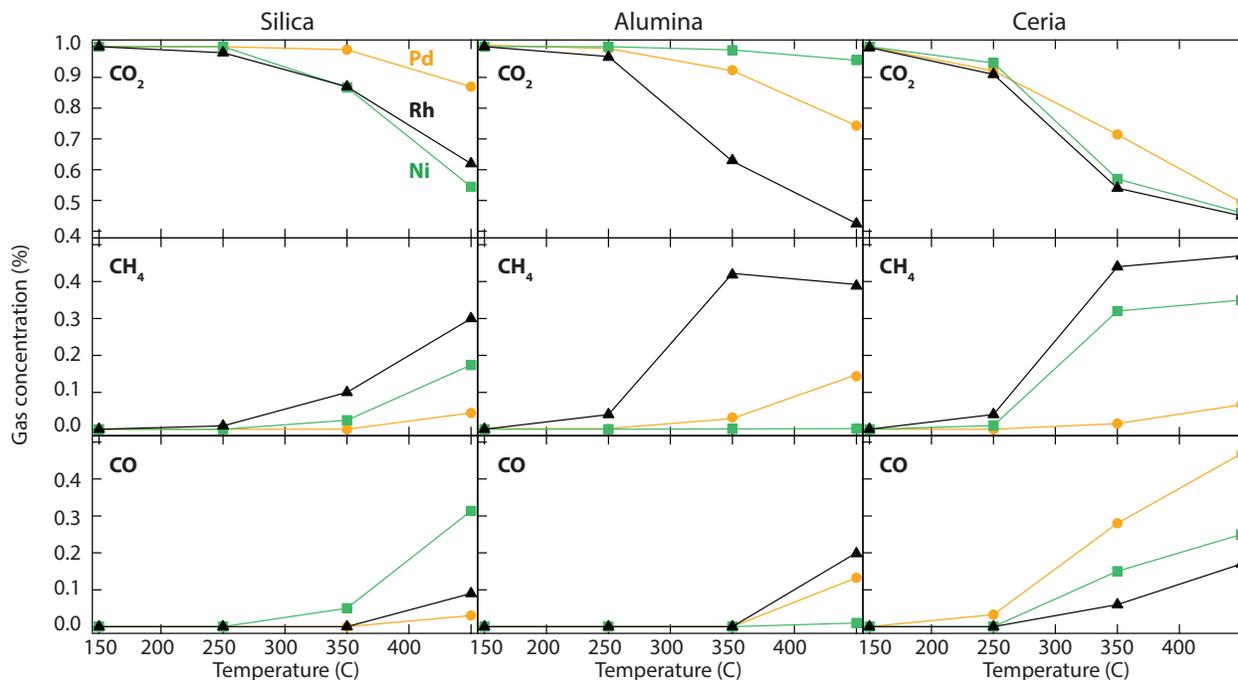


Fig. 2 Steady-state outlet concentration of CO₂ (top), CH₄ (middle) and CO (bottom) as a function of temperature during the reaction between 1% CO₂ and 5% H₂ in Ar between 150 and 450 °C at a total flow rate of 2000 ml/min at atmospheric pressure over the silica, alumina and ceria supported Pd (orange), Ni (green) and Rh (black) catalysts.

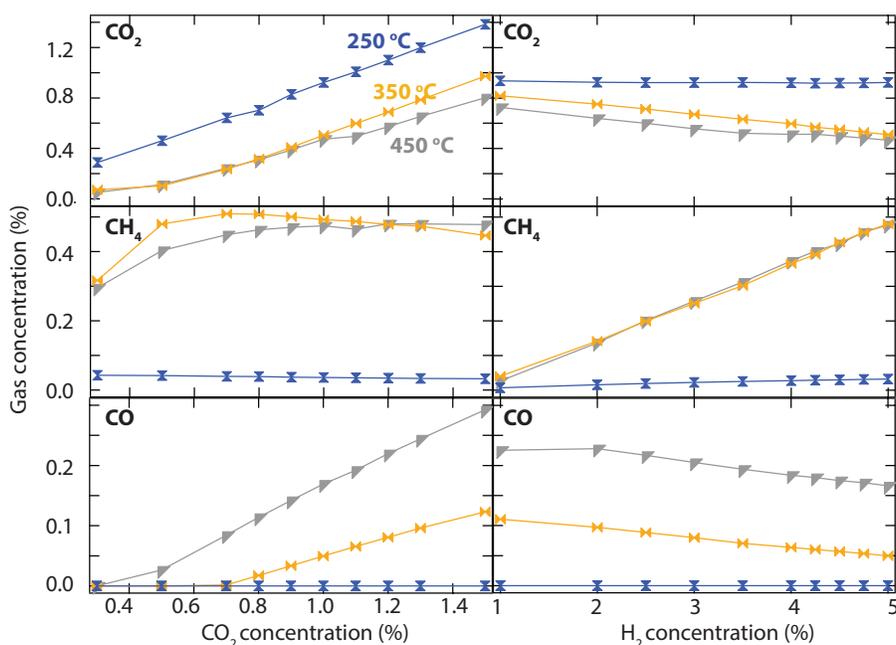


Fig. 3 Steady-state outlet concentration of CO₂ (top), CH₄ (middle) and CO (bottom) over Rh/CeO₂ as a function of inlet concentration of CO₂ at constant H₂ concentration of 5% (left column) and as a function of inlet concentration of H₂ at constant CO₂ concentration of 1% (right column) in Ar gas with a total flow rate of 2000 ml/min at atmospheric pressure.

Table 2 Assignment of IR absorption bands within the wavenumber region 1100-3700 cm^{-1} observed in this study.

Wavenumber (cm^{-1})	Species	Reference
1200-1600	Formate and carbonate-like species	18,23
1720	Bridge-bonded CO on Rh/Ce interface	21
1805	Bridge-bonded CO on Rh	19,20
2020	CO species linearly bonded on Rh	18,19
2800-3000	CH_x vibrations	23
3000-3700	Hydroxyl region	24

that the catalysts with the smallest metal particles (i.e. the catalysts supported on ceria) show the highest activity and selectivity for CO_2 methanation.

The most prominent result in this study is observed for the Rh/CeO₂ catalyst that managed to convert 44% CO_2 almost exclusively to CH_4 at 350 °C. An even higher CO_2 conversion is observed at 450 °C but, due to CO formation through the reverse water-gas shift reaction, the CH_4 selectivity decreases. Further evaluation of the Rh/CeO₂ catalyst revealed evidence of a maximum CH_4 formation around 380 °C. A linear relationship between CH_4 formation and H_2 : CO_2 ratio was observed at both 350 and 450 °C (Figure 3). The experiments for inlet CO_2 concentrations below 0.5% confirm that a high H_2 : CO_2 ratio leads to total conversion towards CH_4 formation. Ceria-based materials have aroused increasing interest as supports or catalysts toward CO_2 conversion due to the unique structural properties resulting from oxygen vacancies and reversible valence change (Ce^{4+} and Ce^{3+})¹⁷.

3.3 Spectroscopic surface speciation during CO_2 methanation

In situ FTIR spectroscopy in diffuse reflectance mode has been employed to study the surface interaction of CO_2 and H_2 for selected Rh- and Ni-based catalysts at temperatures between 250-400 °C, in order to provide insights to the CO_2 methanation reaction mechanism. The DRIFTS results for the hydrogen pulse experiments under a continuous flow of CO_2 for Rh/ Al_2O_3 (left panels), Rh/CeO₂ (middle panels) and Ni/CeO₂ (right panels) at 350 °C are shown in Figure 4. The top panels show the color coded intensities (blue corresponds to low intensity, red to high intensity) of the IR spectra in the interval 790-3800 cm^{-1} versus time. The bottom panels show the time evolution of the integrated IR peak areas between 1200-1600 cm^{-1} corresponding to carbonates and formate species, and around 2020 cm^{-1} corresponding to carbonyls. By presenting the data in color maps the dynamics of the evolution of the IR adsorption bands during the different phases of the experiment is clearly displayed. A peak centred around 2350 cm^{-1} , corresponding to gaseous carbon dioxide, is visible in all spectra.

The interaction of CO_2 and H_2 (in the feed) with the surface of the catalysts generates different surface species, which are assigned as illustrated in Table 2. For the Rh/ Al_2O_3 sample, a strong peak around 2020 cm^{-1} corresponding to linearly adsorbed CO species on Rh (Rh⁰-CO, carbonyl)^{18,19}, appears during CO_2 hydrogenation, suggesting CO_2 dissociation. The ad-

sorbed CO species disappear about 2 min after the H_2 flow has been turned off. In addition, some weak components at lower wavenumbers are observed and will be discussed below (see Figure 5 description).

The color map for the Rh/CeO₂ sample in Figure 4 (middle panels) shows a slightly different behaviour, formate and carbonate-like species^{18,23} form during the exposure to CO_2 and H_2 at 350 °C, which can be observed in the IR region 1200-1600 cm^{-1} (Figure 4, middle panels). In addition, a smaller peak centred at 2020 cm^{-1} appears corresponding to CO species linearly adsorbed on Rh (carbonyl), forming at the same time with the formate and carbonate species. When the H_2 flow is turned off the intensity of the formed surface species decreases. The bands plotted in the bottom panel (formates and carbonates/carbonyl) show a sharp increase at the switches from CO_2 to CO_2 + H_2 flow followed by a sharp decrease about four minutes after the H_2 flow is turned off.

The results for the Ni/CeO₂ sample are similar as for the Rh/CeO₂ sample with the strong peaks appearing between 1200-1600 cm^{-1} corresponding to formate and carbonate-like species (Figure 4, right panels). No carbonyl species are observed for the Ni/CeO₂ sample during CO_2 hydrogenation. A slower formation rate of formates and carbonate species is observed for the Ni sample compared to the Rh sample, even though they are much stronger for the Ni/CeO₂ sample. When the H_2 flow is turned off, a continuous decline of the formate and carbonate band is observed for about five min. It is interesting to note the hysteresis behaviour for the formate and carbonate species observed for the CeO₂ supported catalysts during the CO_2 hydrogenation, which is likely due to the active ceria support.

In order to investigate possible effects of the support, the experiments were repeated for pure alumina and ceria samples at 350 °C and the results are shown in Figure S2 (see Electronic Supplementary Information (ESI)[†]). Some weak carbonate/formate species are observed to form on the ceria sample, while alumina shows no clear adsorption bands, suggesting that ceria can interact with CO_2 . Additionally, no clear changes are observed for the two samples during the CO_2 + H_2 versus the CO_2 periods.

To better understand the changes that the formed surface species undergo during the transient experiment, a number of IR spectra are shown in Figure 5 when the flow of CO_2 + H_2 (48-50 min) is changed to only CO_2 flow (51-57 min) for Rh/ Al_2O_3 (left panel), Rh/CeO₂ (middle panel), and Ni/CeO₂ (right panel) at 350 °C. The spectra reveal noticeable changes of the position/intensity of the IR bands during the cycle. All significant changes observed in the spectra are contained in the region between 1200 and 2100 cm^{-1} . The insert numbers indicate the time (min) in the dynamic experiment where the spectra were recorded. The major changes in the IR spectra take place after the switch from CO_2 + H_2 flow (48-50 min) to CO_2 flow only (51-57 min).

For the Rh/ Al_2O_3 sample (Figure 5, left panel), a strong peak corresponding to linearly adsorbed CO species on Rh (IR band around 2020 cm^{-1}), appears during CO_2 hydrogenation in agreement to previous reports on CO_2 methanation over Rh/ Al_2O_3 ¹¹. A broad band around 1805 cm^{-1} is also detected, which pre-

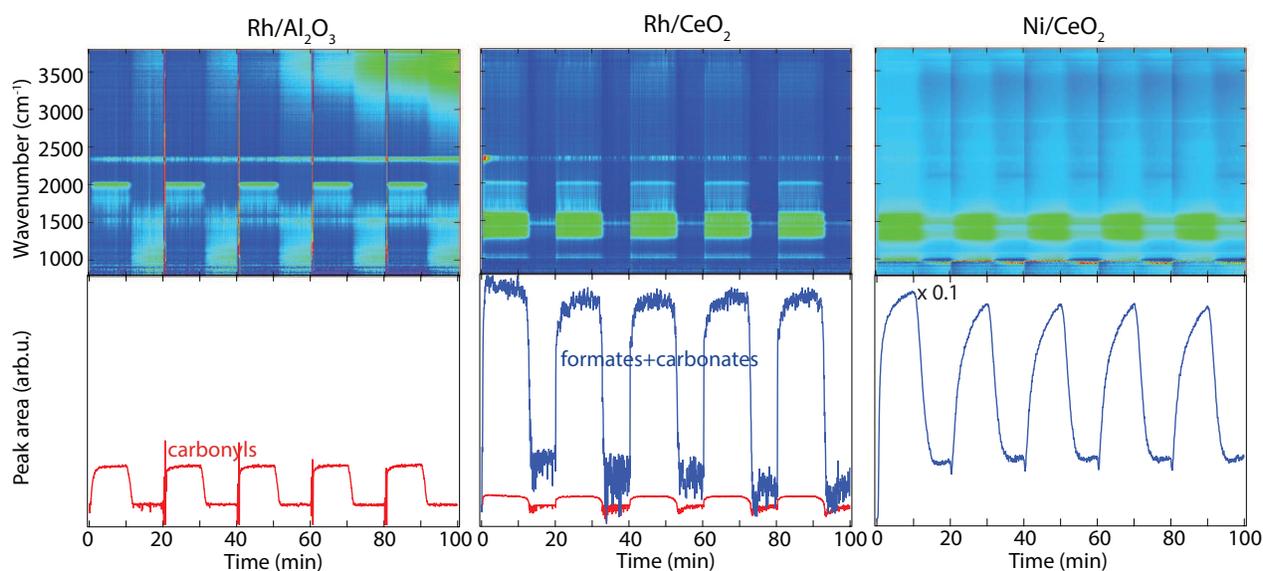


Fig. 4 Transient hydrogenation of 0.2% CO₂ over Rh/Al₂O₃ (left panels), Rh/CeO₂ (middle panels) and Ni/CeO₂ (right panels) during periodic variation of the feed gas composition between 0.8% H₂+0.2% CO₂ and 0.2% CO₂ at 350 °C for 10 min. The top panels show the color coded intensities (blue corresponds to low intensity, red to high intensity) of the IR bands in the region 790-3800 cm⁻¹ versus time. The bottom panels show the IR peak areas between 1200 and 1600 cm⁻¹ representing formate and carbonate species (blue lines) and around 2020 cm⁻¹ representing carbonyls (red lines).

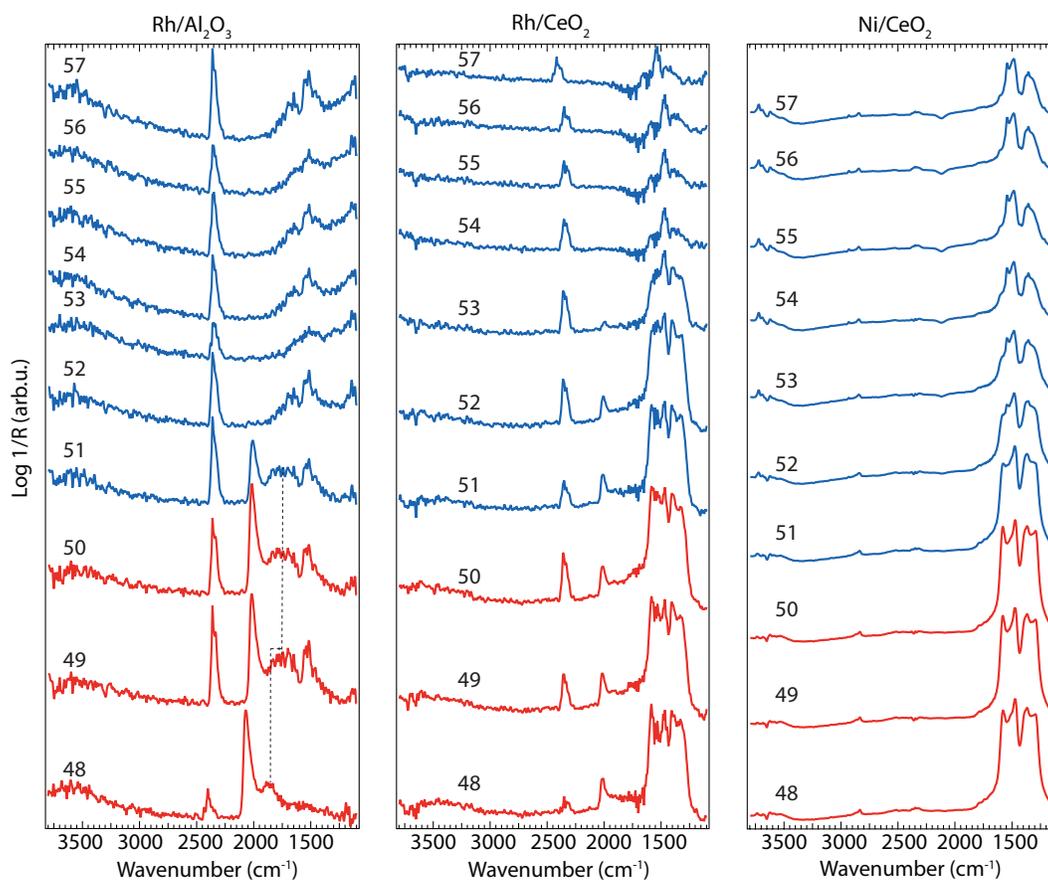


Fig. 5 Evolution of IR absorption bands in the wavenumber region 1100-3800 cm⁻¹ for the Rh/Al₂O₃ (left panel), Rh/CeO₂ (middle panel) and Ni/CeO₂ (right panel) catalysts exposed to CO₂ and H₂ while changing the feed gas composition from 0.8% H₂+0.2% CO₂ (48-50, red spectra) and 0.2% CO₂ (51-57, blue spectra) at an inlet gas temperature of 350 °C. The insert numbers indicate the time (min) in the dynamic experiment where the spectra were recorded.

viously has been attributed to bridge-bonded CO on Rh (Rh⁰-CO)^{19,20}. This band broadens and seems to appear at lower wavenumbers by the end of the CO₂+H₂ cycle (1720 cm⁻¹, denoted by the dotted lines in Figure 5) suggesting the formation of bridged bonded CO species positioned between Rh and Al atoms from the support, similar to previous reports on CO adsorption between Rh and Ce atoms²¹. Some additional weaker peaks in the region 1700-1500 cm⁻¹ appear towards the end of the CO₂+H₂ cycle (49-50 min) corresponding to carbonate or formate-like species. Two minutes after the H₂ flow is turned off, the band related to carbonyl species adsorbed on Rh disappears and the band around 1700 cm⁻¹ shifts towards lower wavenumbers (1650 cm⁻¹) indicating the formation of different surface carbonates. A band centred around 1520 cm⁻¹ is clearly visible through the entire time the sample is exposed to CO₂ (51-57 min).

For the Rh/CeO₂ sample (Figure 5, middle panel), strong peaks are observed in the IR region between 1590-1330 cm⁻¹, together with a weaker absorption band around 2020 cm⁻¹. The intensity of the formed surface species during CO₂ hydrogenation (formate and carbonate, and carbonyl species) shows a very slow diminution directly after the H₂ flow is turned off and only a broad peak centered around 1460 cm⁻¹ remains when the sample is exposed to CO₂ only, corresponding mostly to carbonate species²².


For the Ni/CeO₂ sample (Figure 5 right panel), during the transition between CO₂+H₂ to only CO₂ flow mostly the intensity of the formates and carbonates peaks in the region 1300-1600 cm⁻¹ decreases. The spectra during the CO₂ hydrogenation phase (48-50 min) resemble well the spectra recorded for the Rh/CeO₂ sample without the formation of carbonyl species. There are differences between the two samples during the CO₂ flow only (51-57 min). Stronger peaks are observed for the Ni/CeO₂ sample during the entire experiment. In addition to the carbonate and formate species, new peaks appear around 2800 cm⁻¹ and 3500-3700 cm⁻¹, corresponding to C-H and O-H vibrations from CH_x²³ and hydroxyl groups²⁴, respectively. The presence of CH_x species on the Ni containing species suggest the formation of different hydrocarbonated compounds on the surface of the catalysts, in contrast to the Rh containing samples, where only methane in the gas phase is detected suggesting the direct desorption of CH₄ as soon as it forms on the surface. The behaviour of the Ni/CeO₂ sample during the CO₂ flow is slightly different compared to the Rh/CeO₂ and Rh/Al₂O₃ catalysts discussed above and is likely that more formate species form on this sample.

3.4 Reaction mechanism during CO₂ methanation

Recently, it has been demonstrated that CO₂ can react with H₂ over Rh/γ-Al₂O₃ to produce methane at room temperature and atmospheric pressure¹². However, in the present study, we see that higher temperatures are needed for methane to be produced from CO₂ and H₂ over Rh/Al₂O₃. No significant methane production was observed below 250 °C (see Figure 2).

Different mechanisms have been proposed for CO₂ methanation over a variety of noble metal-based catalysts. The first mechanism (eq. (4) below) involves the adsorption of CO₂ on the sup-

port and its reaction with adsorbed H species formed on the metal which leads to a formate intermediate (COOH) at the metal-support interface. The formates can give rise to CO species adsorbed on the metal by the rWGS reaction, which subsequently are hydrogenated to methane²⁵. The second mechanism (eq. (5) below) involves the direct dissociation of CO₂ to CO and O adsorbed on the metal surface, with adsorbed CO being subsequently hydrogenated to CH₄^{10,12,19,26}.



In contrast to several previous studies on the methanation mechanism, Upham *et al.*²⁷ suggest another mechanism for CO₂ methanation over Ru-doped ceria, where CH₄ is not formed through intermediates of CO or a formate. IR spectroscopy measurements instead corresponds to a variety of surface carbonate spectra. This strengthened the idea of direct CO₂ adsorption and formation of carbonates on ceria supported catalysts, without adsorption and dissociation on the metal phase. The formed carbonates react with hydrogen to produce methane that directly desorbs from the surface of the catalysts.

The DRIFTS results presented in this work give insights on the methanation reaction mechanism and differences are observed between the studied catalysts. In Figures 4 and 5 the surface species formed when a mixture of CO₂+H₂ followed by a flow of CO₂ interacts with the surface of Rh/CeO₂, Rh/Al₂O₃ and Ni/CeO₂ are shown. As discussed above, for the Rh based catalysts, CO species adsorbed on metal are formed, suggesting that CO₂ dissociates on these catalysts. Since no carbonyl species are formed under the flow of CO₂ only, it is clear that CO₂ dissociation is favored by the presence of hydrogen which is likely to be dissociated on the metallic Rh surface. In contrast, no adsorbed CO species are observed on the Ni catalyst, suggesting a different reaction mechanism over this sample. The ability of CO₂ to dissociate over Rh/γ-Al₂O₃ has been evidenced by *in situ* DRIFTS experiments, which show the presence of bands that correspond to Rh-CO (carbonyls)¹². Similar results have been observed over Rh/TiO₂ catalysts²⁸.

Due to the limited wavelength resolution we are unable to separate between the different formate and carbonate species in the IR region between 1200-1700 cm⁻¹. However, the observed peak for C-H stretching at around 2800-2900 cm⁻¹ for the Ni-ceria sample indicates that more formates are formed on this sample, while for the Rh containing samples the absence of this peak may suggest the predominance of carbonate species, which is also supported by the presence of a smaller peak around 840 cm⁻¹ for these samples (IR region not shown), characteristic of carbonate species. We observe the formation of CO in the gas phase from the rWGS reaction over the Rh/CeO₂ catalyst (Figure 2). Additionally, the formation of formate and carbonate species is accompanied by the concomitant apparition of adsorbed CO species, suggesting the first reaction mechanism (through formate/carbonate species) over this sample. In contrast, no CO in the gas phase is observed for the Rh/Al₂O₃ catalyst up to 350 °C, suggesting the direct dissociation of CO₂, in agreement with previous reports¹⁰⁻¹², where formates were proposed to be spec-

tator species and to not contribute significantly to methane formation for the methanation reaction¹¹. No carbonyl bands are observed for the Ni/CeO₂ catalyst, only formate and carbonate bands suggesting a formate/carbonate pathway reaction mechanism. The DRIFTS results suggest that the metal-support interface for the Rh/CeO₂ and Ni/CeO₂ catalysts may play an important role in the CO₂ hydrogenation reaction, similar to the reports on Cu/CeO_x/TiO₂(111)²⁹.

4 Conclusions

Hydrogenation of CO₂ at ambient pressure conditions has been studied over a series of supported Pd-, Rh- and Ni-based catalysts prepared by impregnation. High selectivity to methane and high CO₂ conversion are obtained over the Rh-based catalysts. Our results show that it is possible to produce methane from CO₂ and H₂ at ambient pressure and relatively low temperature over Rh/CeO₂, Rh/Al₂O₃ and NiCeO₂ catalysts. Methane is the only hydrocarbon product observed in our analysis. The results of *in situ* DRIFTS experiments show that CO₂ adsorption and dissociation occurs over the Rh/Al₂O₃ catalyst in the presence of H₂, resulting in the formation of linear Rh-CO species, which accounts for the majority of the adsorbed species formed during CO₂ hydrogenation at 350 °C. In contrast the results show that the methanation reaction mechanism is different over the Rh/CeO₂ catalyst where CO is formed through formate and carbonate intermediate species.


The results, strengthened by previous studies indicate that a metal oxide like ceria can interact with CO₂ and thus, be a part of and promote the hydrogenation reaction by direct formation of surface carbonates and formates.

5 Acknowledgement

This work was financially supported by the Swedish Research Council through the Röntgen-Ångström collaborations "Catalysis on the atomic scale" (No. 349-2011-6491) and "Time-resolved *in situ* methods for design of catalytic sites within sustainable chemistry" (No. 349-2013-567) and the Competence Centre for Catalysis, which is financially supported by Chalmers University of Technology, the Swedish Energy Agency and the member companies: AB Volvo, ECAPS AB, Haldor Topsøe A/S, Volvo Car Corporation, Scania CV AB, and Wärtsilä Finland Oy.

References

- G.A. Olah, *Catal. Lett.*, 2004, **93**, 1-2.
- I. Ganesh, *Renewable and Sustainable Energy Reviews*, 2014, **31**, 221-257.
- W. Wang, S. Wang, X. Ma, J. Gong, *Chem. Soc. Rev.*, 2011, **40**, 3703-3727.
- G.W. Busser et al., *ACS Catal.*, 2015, **5**(9), 5530-5539.
- D.T. Whipple, P.J.A. Kenis, *J. Phys. Chem. Lett.*, 2010, **1**(24), 3451-3458.
- J.N. Park, E.W. McFarland, *J. Catal.*, 2009, **266**, 92-97.
- G.C. Chinchin, P.J. Denny, J.R. Jennings, M.S. Spencer, K.C. Waugh, *Appl. Catal.*, 1988, **36**, 1-65.
- M. Behrens, F. Studt, I. Kasatkin, S. Kühn, M. Hävecker, F. Abild-Pedersen, S. Zander, F. Girgsdies, P. Kurr, B.-L. Knief, M. Tovar, R. W. Fischer, J.K. Nørskov, R. Schlögl, *Science*, 2012, **336**, 893-897.
- F. Studt, I. Sharafutdinov, F. Abild-Pedersen, C. F. Elkjær, J. S. Hummelshøj, S. Dahl, I. Chorkendorff, J. K. Nørskov, *Nat. Chem.*, 2014, **6**, 320-324.
- A. Beuls, C. Swalus, M. Jacquemin, G. Heyen, A. Karelavic, P. Ruiz, *Appl. Catal. B*, 2012, **113-114**, 2-10.
- A. Karelavic, P. Ruiz, *Appl. Catal. B: Env.*, 2012, **113-114**, 237-249.
- M. Jacquemin, A. Beuls, P. Ruiz, *Cat. Today*, 2010, **157**, 462-466.
- S. Tada, T. Shimizu, H. Kameyama, T. Haneda, R. Kikuchi, *Int. J. Hydrog. Energy*, 2012, **37**, 5527-5531.
- S. Brunauer, P. H. Emmett and E. Teller, *Journal of the American Chemical Society*, 1938, vol. **60**, 309-319.
- P.-A. Carlsson, S. Mollner, K. Arnby, M. Skoglundh, *Chem Eng. Sci.*, 2004, **59**, 4313-4323.
- D. Pakhare, J. Spivey, *Chem. Soc. Rev.*, 2014, **43**, 7813-7837.
- F. Wang, M. Wei, D.G. Evans, X. Duan, *J. Mater. Chem. A*, 2016, **4**, 5773-5783.
- F. Solymosi, A. Erdohelyi, T. Bansagi, *J. Chem. Soc. Faraday Trans. 1*, 1981, **77**, 2645-2657.
- I.A. Fisher, A.T. Bell, *J. Catal.*, 1996, **162**, 54-65.
- H.Y. Luo, H.W. Zhou, L.W. Lin, D.B. Liang, C. Li, D. Fu, Q. Xin, *J. Catal.*, 1994, **145**, 232-234.
- A. Kiennemann, R. Breault, J.-P. Hindermann, M. Laurin, *J. Chem. Soc. Faraday Trans. 1*, 1987, **83**, 2119-2128.
- M. Marwood, R. Doepper, A. Renken, *Appl. Catal. A*, 1997, **151**, 223-246.
- R.J. Behm, S. Eckle, Y. Denkwitz, *J. Catal.*, 2010, **269**, 255-268.
- G. Busca, *Phys. Chem. Chem. Phys.*, 1999, **1**, 723-736.
- D.I. Kondarides, P. Panagiotopoulou, X.E. Verykios, *J. Phys. Chem. C*, 2011, **115**, 1220-1230.
- L.F. Liotta, G.A. Martin, G. Deganello, *J. Catal.*, 1996, **164**, 322-333.
- D.C. Upham, A.R. Derk, S. Sharma, H. Metiu, E.W. McFarland, *Catal. Sci. Technol.*, 2015, **5**, 1783-1791.
- A. Karelavic, P. Ruiz, *J. Catal.*, 2013, **301**, 141-153.
- J. Graciani, *Science*, 2014, **345**, 546-550.

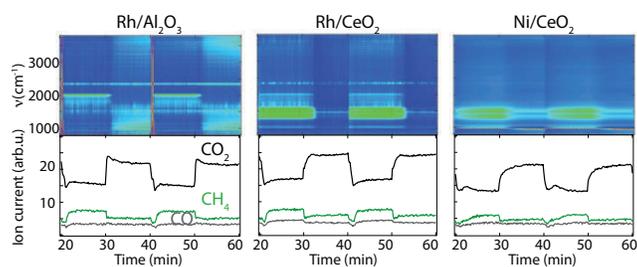

TOC: CO₂ methanation over Rh/Al₂O₃, Rh/CeO₂ and Ni/CeO₂ at 350°C highlighting the different surface speciation during reaction.