

Green Chemistry

Cutting-edge research for a greener sustainable future

Accepted Manuscript

View Article Online
View Journal

This article can be cited before page numbers have been issued, to do this please use: R. Feng, Q. Zhu, M. Chu, S. Jia, J. Zhai, H. Wu, P. Wu and B. Han, *Green Chem.*, 2020, DOI: 10.1039/D0GC03051A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Journal Name

PAPER

Electrodeposited Cu-Pd Bimetallic Catalysts for the Selective Electroreduction of CO₂ to Ethylene

Received 00th January 20xx,
Accepted 00th January 20xx

Ruting Feng,^a Qinggong Zhu,^b Mengen Chu,^a Shuaiqiang Jia,^a Jianxin Zhai,^a Haihong Wu^{*a}, Peng Wu^{*a}, Buxing Han^{*a,b}

DOI: 10.1039/x0xx00000x

www.rsc.org/

Cu-Pd bimetallic catalysts was fabricated on carbon paper (CP) by electrodeposition method via a dynamic hydrogen bubble template approach. At a potential of -1.2 V vs RHE, the Faradaic efficiency (FE) of C₂H₄ could reach 45.2% with a current density of 17.4 mA cm⁻² in an H-type electrolysis cell. Detailed studies suggest that the enhanced performance of Cu-Pd/CP was attributed mainly to the synergistic effect, low interfacial charge transfer resistance, as well as 3D architecture of the catalysts.

Carbon dioxide (CO₂) reduction has garnered intense interest with the global energy and environmental crises.^[1, 2] An ideal route for the chemical utilization of CO₂ is to develop catalytic processes for the selective conversion of CO₂ into value-added chemicals and fuels.^[3-5] Among all the developing techniques, the electrocatalytic reduction is a promising route for utilization of CO₂ as a carbon feedstock to value added-chemicals.^[6-11] Up to date, extensive efforts have been devoted to the development of electrocatalysts for CO₂ reduction reaction (CO₂RR) to higher value products.^[12-14]

Ethylene (C₂H₄) is a popular chemical commodity used in industry.^[15, 16] Compared with C₁ products, C₂H₄ possesses impressive energy densities and higher economic value.^[13, 17, 18] Currently, copper (Cu) is the promising candidate as a catalyst that could produce C₂ products, but often a wild range of products are formed with low product selectivity.^[19, 20] To overcome the poor selectivity of pure Cu toward C₂ product, various strategies have been proposed, including alloying,^[21] doping,^[22] changing the composition and morphology,^[4a] and creating special electrolytic devices.^[23] For instance, Cu-doped

carbon catalysts have been reported to enhance the electroreduction of CO₂ to C₂H₄.^[24] Plasma-activated oxide derived-Cu (OD-Cu) catalysts with high stability of Cu⁺ species have been reported to promote C₂ product formation.^[25] While significant progress has been achieved on CO₂RR to C₂H₄.^[26, 27] Exploration of electrochemical systems for electrocatalytic C-C coupling in aqueous electrolytes is still an open challenge due to low selectivity, activity, and large overpotential.^[28-30] Design of catalyst holds the key to address those challenges.^[31, 32]

Recently, Cu-based bimetallic catalysts have shown great potential in enhancing catalytic ability toward C₂ product by increasing strains and synergistic effects of atoms in the catalyst.^[20, 33, 34] Enhancement in the selectivity for C₂H₄ has been observed on various bimetallic catalysts. For example, Au-Cu bimetallic catalysts have been investigated to arise C₂H₄ selectivity with 46.7%.^[35] Ag-Cu nanoparticles showed a selectivity of CO₂RR toward C₂H₄ with FE of 41.3%.^[36] Besides, Cu-Ru bimetallic alloy could catalyze CO₂ conversion to C₂H₄ with FE of 19%.^[37] Nano porous Cu-Ag bimetallic catalyst was also reported to reduce CO₂ to C₂H₄ with FE of 60%.^[38] However, even after such extensive research efforts, achieving high selectivity for C₂H₄ on facile prepared bimetallic catalysts is still highly desired in this field.^[39, 40]

Self-supporting bimetallic catalysts by electrodeposition is a very useful technique that can form three-dimensional (3D) porous structure and increased surface area by a one-step strategy of potentiostatic co-electrodeposition utilizing hydrogen bubble dynamic templates.^[41, 42] Compared with other synthesized method, the corresponding technology is often known as electroplating, which can simplify the experimental process, further reduce the cost and increase the electrode efficiency due to their extraordinary chemical properties in the electrolyte during the electrodeposition.^[43] The electrocatalysts also provide some obvious advantages in CO₂RR, such as fast electron transfer rate, large specific area and high electrochemical performance.^[12]

In this work, we focus on enhancing the selectivity of CO₂RR to C₂H₄ on Cu-Pd bimetallic catalysts, which were prepared by galvanostatically electrodeposition using self-supporting technique.

^a Shanghai Key Laboratory of Green Chemistry and Chemical Processes, School of Chemistry and Molecular Engineering, East China Normal University, Shanghai 200062, P. R. China

^b Beijing National Laboratory for Molecular Sciences, CAS Key Laboratory of Colloid and Interface and Thermodynamics, CAS Research/Education Center for Excellence in Molecular Sciences, Institute of Chemistry, Chinese Academy of Sciences, Zhongguancun North First Street 2, Beijing, 100190, P. R. China

E-mail: hhwu@chem.ecnu.edu.cn; pwu@chem.ecnu.edu.cn; hanbx@iccas.ac.cn
Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI:10.1039/x0xx00000x

The resulting Cu-Pd bimetallic catalysts had a high selectivity toward C_2H_4 (45.2%) at applied potential of -1.2 V vs RHE and current density of 17.4 mA cm^{-2} in aqueous electrolyte. The high catalytic activity of bimetallic Cu-Pd catalysts was attributed to the synergistic effect between Cu and Pd, fast electron transfer rate, as well as 3D architecture of the catalyst.

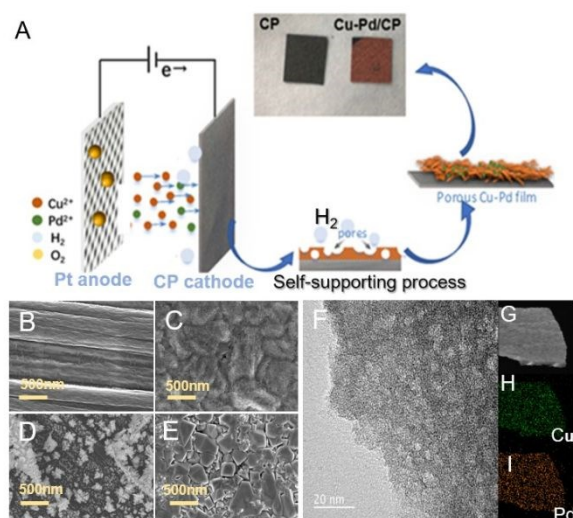


Fig. 1 A) Schematic illustration of the procedure for preparing Cu-Pd bimetallic catalysts; SEM images: B) CP; C) Cu/CP catalysts; D) Pd/CP catalysts; E) Cu-Pd/CP catalysts; F) TEM image of Cu-Pd/CP catalysts; G) The elemental mappings of Cu-Pd/CP catalysts. The images in green and red represent H) Cu and I) Pd, respectively.

The Cu-Pd bimetallic catalysts were synthesized by a facile electrodeposition method, which is schematically described in Fig. 1A. In the deposition process, Cu and Cu-Pd samples were electrodeposited in an acid solution containing Cu^{2+} and Pd^{2+} at pH=1. During the deposition, the dynamic hydrogen bubble was used as template to prepare functional porous materials. Cu-Pd was electrodeposited galvanostatically at a constant current density. The catalysts were characterized by scanning electron microscopy (SEM) and transmission electron microscopy (TEM). Fig. 1B-D provide the SEM images of CP, Cu/CP and Pd/CP. It is shown that a rough surface of Cu deposit and a half-baked dendritic 3D structure for Pd were formed on CP. Unlike these catalysts, Cu-Pd bimetallic catalysts shows observable structural changes (Fig. 1E) and a tetrahedron structure was formed with nanostructured features on the scale of 90-200 nm (Fig. 1F, TEM). We also examined Cu-Pd/CP catalysts using elemental distribution mappings (EDS, Fig. 1G-I), which show that Cu (green), and Pd (red) atoms are homogeneously distributed, forming a bimetallic structure.

According to X-ray diffraction (XRD, Fig. 3A), the diffraction peak located at 24.8° was assigned to (002) plane of the CP. Cu diffraction peaks of (111), (200), and (220) facets are present for the bimetallic samples. The diffraction peaks of these samples had an appreciable shift in comparison with that of Pd. No Pd-related peaks were found, indicative of the low amount of Pd in the

bimetallic catalysts. The Cu-Pd bimetallic samples also exhibited Cu_2O diffraction peaks of (110), (111), and (220), which associated with the presence of Cu_2O phase in the bimetallic catalysts.

X-ray photoelectron spectroscopy (XPS) further identified the element contents and valence states of Cu and Pd in the catalysts (Fig. 2B-C). The results of XPS investigations on Cu/CP and Pd/CP are consistent with the results of XRD. For Cu-Pd/CP It can be seen the Cu/Pd ratio is 6.83, which indicates the formation of bimetallic catalysts (Table S1). The binding energies Cu 2p spectra were fitted with two components, which are $Cu^I + Cu^0$ ($2p_{3/2}$, 932.4 eV; $2p_{1/2}$, 952.0 eV) and Cu^{II} ($2p_{3/2}$, 934.2 eV; $2p_{1/2}$, 954.0 eV) respectively. The intensities of Pd 3d_{5/2} peaks of Cu-Pd catalysts at 337.2 eV and 337.8 eV correspond to the metallic Pd⁰ and Pd^{II}, and the Pd 3d_{3/2} peaks at 342.5 eV and 342.8 eV corresponding to Pd⁰ and Pd^{II}. This indicates that O species exist on the catalysts surface. The presence of O species may yield enhancement in C_2H_4 production efficiency.^[38]

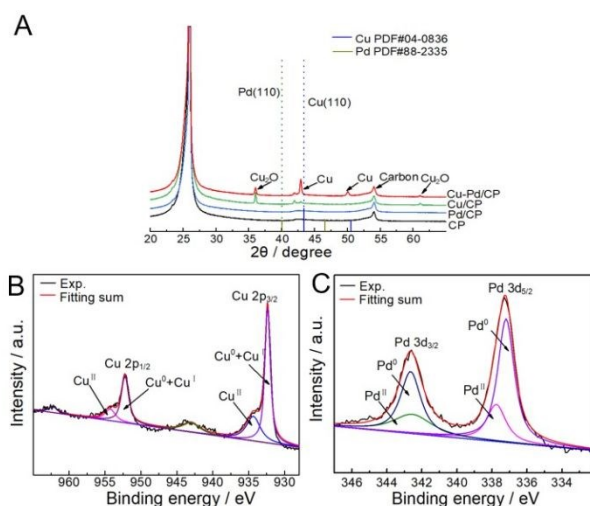


Fig. 2 A) XRD patterns of Cu-Pd/CP, Cu/CP, Pd/CP, CP; XPS spectra of B) Cu 2p and C) Pd 3d levels of catalysts.

The electrocatalytic performances of Cu-Pd/CP were investigated in CO_2 -saturated KCl aqueous solution in a typical three-electrode electrochemical system. The linear sweep voltammetry (LSV) was conducted to investigate the performance of Cu-Pd in 0.1 M KCl aqueous solution, and the LSV curves were swept in the potential range from 0 to -1.4 V (vs. RHE) at a sweep rate of 50 mV s^{-1} . As shown in Fig. 3A, the Cu-Pd/CP exhibited a higher current density than other electrodes (CP, Pd/CP, Cu/CP), suggesting that Cu-Pd bimetallic catalysts was favorable to the binding of CO_2 . In addition, the much higher current density of CO_2 -saturated catholyte than N_2 -saturated catholyte implied the reduction of CO_2 (Fig. S1).

Controlled potential electrolysis was performed using a typical H-type electrolysis cell in the same system. After electrolysis, the gas and liquid products were analyzed by gas chromatography (GC) and nuclear magnetic resonance (1H -NMR), respectively. The main gaseous products were C_2H_4 , H_2 and a trace amount of CO, no liquid product was detected by NMR. Fig. 3B shows the FE of main products over various electrodes, it indicates that CP and Pd/CP has little catalytic effect in electrocatalytic reduction of CO_2 to C_2H_4 . The

main product on Pd/CP was syngas, which contains H_2 , CO. On the Cu/CP, FE of C_2H_4 was 29.97% with a CO FE of 24.3%. Among these samples, Cu-Pd/CP was the best catalyst with a C_2H_4 FE of 45.23% at -1.2 V (vs. RHE). Comparing with the reported results using different bimetallic electrocatalysts (Table S2), the FE and current density were high in aqueous electrolyte by using H-type cell.

To gain kinetic insights for the CO_2RR to C_2H_4 on Cu-Pd catalysts, the current density for C_2H_4 at various overpotentials were measured. As shown in Fig. 3C, the onset potential over Cu-Pd/CP was -0.65 V, which was more positive than those of Cu/CP (-0.72 V) and Pd/CP (-0.88 V), indicating that the initial electron transfer to CO_2 to form an adsorbed CO_2^- intermediate was much easier over Cu-Pd/CP.^[44] We also studied the change of C_2H_4 over Cu-Pd/CP at different applied potentials. As the electrolytic potential increased, the FE of C_2H_4 increased first and then decreased. The FE of C_2H_4 reached 45.2% with a current density of 17.4 mA cm^{-2} at -1.2 V vs. RHE (Fig. 3D). The decrease in the FE of C_2H_4 at a high applied potential resulted from the enhancement in the production rate of H_2 .

The electrochemical activity of Cu-Pd/CP was also characterized according to the Randle-Sevcik equation. The reduction current density plotted against the root of the scan rate is illustrated in Fig. S2. According to the result, the Cu-Pd/CP has the largest slope among the electrodes, indicating the highest reduction rate for CO_2RR . This result is consistent with the electrochemical impedance spectroscopy (EIS) result (Fig. S3-4), which provides the charge transfer rate at the electrode/electrolyte interface. The results indicated that the charge transfer resistance (R_{ct}) of the Cu-Pd/CP was lower than that of the Cu/CP. The above result shows that Pd or Cu could not promote the generation of C_2H_4 product efficiently, and the excellent performance of Cu-Pd/CP can be attributed to the synergistic effect between Cu and Pd in the catalysts. On one hand, Cu-based bimetallic catalysts have shown great potential in enhancing catalytic ability toward C_2 product by increasing strains and synergistic effects of atoms in the catalyst. Oxygen-bearing Cu catalysts could enable the C-C coupling in the electrocatalytic CO_2RR systems. The mixed valence form of copper (Cu^0 and Cu^I) may be dominant species during the CO_2RR , which could be the most active species for C_2 product formation. The Cu^+/Cu^0 interfaces formed through stabilized Cu^+ facilitate $*CO-CO$ dimerization, promoting formation of C_{2+} products and suppressing conversion to C_1 products. On the other hand, Pd is known to be the excellent catalyst for CO_2RR to CO.^[21, 40] Trace amount of Pd could promote the adsorption of $*CO$ intermediate and facilitates their dimerization to form C_2 products.^[38, 45]

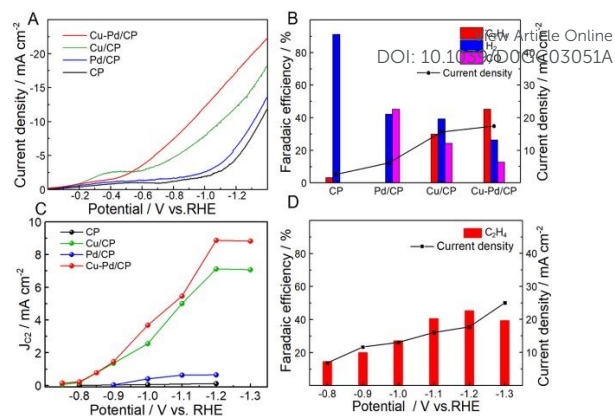


Fig. 3 A) LSV curves of various electrodes with a scan rate of 50 mV^{-1} ; B) the FE of C_2H_4 at -1.2 V (vs. RHE) over various electrodes; C) Partial current density of C_2H_4 over various electrodes at different applied potentials; D) the FE and current density of C_2H_4 over Cu-Pd/CP at different applied potentials in CO_2 -saturated 0.1 M KCl solution.

We also studied the electrolyte effect over Cu-Pd/CP electrode. In addition to 0.1 M KCl electrolyte, other electrolytes that contain different cations and anions were used in this work (Fig. S5). For example, in the NaCl electrolyte, H_2 was the main product. CO_2RR exhibited better performance for C_2H_4 with FE of 35% in 0.1 M KHCO_3 electrolyte. In 0.1 M KH_2PO_4 and K_2HPO_4 electrolyte, the FE of C_2H_4 was very low with H_2 as the main product. In KCl electrolyte, even if the electrolyte concentration is increased, the FE of C_2H_4 did not increase significantly, which indicates that 0.1 M KCl was the best electrolyte. We think that the electrolyte affects CO_2 reduction mainly in two ways. First, the alkali metal cation (such as Na^+ , K^+) in the electrolyte is known to influence the electrocatalytic ability of CO_2 reduction. Density functional theory (DFT) calculations have shown that the alkali metal cations influence the distribution of products formed as a consequence of electrostatic interactions between solvated cations present at the outer Helmholtz plane and adsorbed species having large dipole moments. Therefore, increasing alkali metal size leads to higher selectivity to C_2 products.^[46, 47] Second, the local buffering capability of cations could be able to increase the rate of proton-transfer reaction, which affects the activity and selectively for CO_2RR . When the cation concentration was too low or too high, it will inhibit the proton-transfer reaction. Therefore, a moderate concentration facilitates proton transfer and improves catalytic activity and selectivity.^[48, 49] These arguments are consistent with our experimental results.

We assume that the excellent activity of Cu-Pd bimetallic catalysts toward C_2H_4 resulted from the synergistic effect of Cu and Pd in Cu-Pd catalysts. Therefore, we prepared the Cu-Pd catalysts using different electrodeposition methods (CV and Amperometric mode), which may contain different atomic ratio of the elements (Table S1). The corresponding electrodes were then named as Cu-Pd/CP-CV, Cu-Pd/CP-IT (see experimental section in SI). The SEM image of Cu-Pd/CP-CV and Cu-Pd/CP-IT electrodes showed a symmetrical and a homogeneous morphology, respectively (Fig. S6). After electrolysis, we found FE of C_2H_4 was approximately 25% over both electrodes with high hydrogen evolution reaction (HER) than Cu-Pd/CP electrode (Fig. 4A). Therefore, we characterized the Cu-Pd catalysts prepared using different methods by XRD

(Figure S7) and XPS (Figure S8) to get more information about the surface element states and catalytic performance. Among the three methods, Cu-Pd/CP showed the lowest $(\text{Cu}^0 + \text{Cu}^I)/\text{Cu}^{\text{II}}$ and $\text{Pd}^0/\text{Pd}^{\text{II}}$ ratio, which suggests that the existence of oxygen vacancies in the catalysts (Table S1). Therefore, it is benefit to the adsorption of the intermediates and facilitates the formation of C_2H_4 . The EIS results (Figure S9, Table S3) also showed that Cu-Pd/CP had lower R_{ct} (Nyquist plot) and larger phase angle at low frequency region (Bode plot) than that of Cu-Pd/CP-CV and Cu-Pd/CP-IT, resulting in the increase of electron transfer and diffusion ability of Cu-Pd/CP.

The effect of deposition current density on the properties of the catalysts was also studied. Deposition of Cu-Pd bimetallic catalysts under different current density not only affected the co-deposition process, but also changed the morphology of the catalyst. Therefore, we fixed the total amount of electrons to 12 Coulomb and obtained Cu-Pd catalysts with different morphologies under different current density (Fig. S10). Fig. 4B shows that the deposition current density of Cu-Pd catalysts had great influence on the FE of C_2H_4 . It may be due to the different atomic amount in the catalysts. As shown in Fig. S11, the bimetallic solution has an intermediate potential between the other two monometallic solutions. It indicates that at high

deposition potential and high current density, the deposition tended to deposit Cu. At low deposition potential and low current density, the content of Pd in the catalysts increased. According to this tendency, the FE of C_2H_4 was first increased then decreased with increasing deposition current density, which indicates that a proper Cu-Pd ratio was beneficial to the reaction. This also can be known from the fact the FE of C_2H_4 over electrodeposited Cu/CP or Pd/CP was much lower (Fig. 3B).

The excellent activity of Cu-Pd catalysts may also result partially from 3D architecture of the film. Therefore, we performed the CO_2 reduction using Cu-Pd catalysts obtained from various deposition times. Fig. S12 shows that the amount of the catalyst increased with increasing deposition time. The CO_2RR current density increased continuously with deposition time, but the FE of C_2H_4 first increased and then decreased (Fig. 4C). This can be explained by the fact that the 3D structure gradually formed with increasing deposition time. This structure may provide more opportunity for the C-C coupling for the intermediates. When the film of 3D structure was thick enough (>10 min), excessive catalyst agglomeration is not conducive to the reaction.

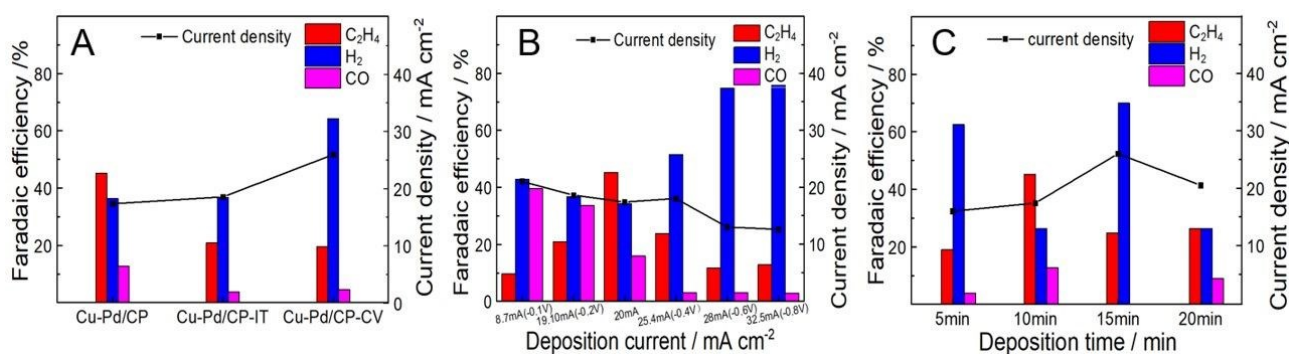


Fig. 4 the FE of C_2H_4 over Cu-Pd bimetallic catalysts A) using different electrodeposition methods; B) under different current density; C) obtained from various deposition time.

Conclusion

In summary, we developed a facile electrodeposition method to fabricate Cu-Pd catalysts onto conductive substrates through dynamic hydrogen bubble template approach. The synthesized Cu-Pd/CP is a highly effective catalyst for CO_2 reduction to C_2H_4 . The FE and current density of C_2H_4 could reach 45.23% and 17.4 mA cm^{-2} in 0.1 M KCl aqueous electrolyte respectively. Detailed study indicates that the synergistic effect between Cu and Pd in the Cu-Pd catalysts, low interfacial charge transfer resistance, 3D architecture of the catalysts, as well as suitable electrolyte are all favourable for the formation of C_2H_4 . We believe that the strategy to prepare bimetallic catalysts by co-electrodeposition coupling effective electrolyte can be used to design more efficient catalytic systems for CO_2 reduction to C_2 products.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The work was supported by National Natural Science Foundation of China (21533011, 21733011), the National Key Research and Development Program of China (2017YFA0403102), and Chinese Academy of Sciences (QZDY-SSW-SLH013).

Notes and references

1. M. He, Y. Sun and B. Han, *Angew. Chem. Int. Ed.*, 2013, **52**, 9620-9633.
2. Z. Sun, T. Ma, H. Tao, Q. Fan and B. Han, *Chem*, 2017, **3**, 560-587.

3. W. Lu, B. Jia, B. Cui, Y. Zhang, K. Yao, Y. Zhao and J. Wang, *Angew. Chem. Int. Ed.*, 2017, **56**, 11851-11854.
4. S. A. Abbas, S.-H. Kim, H. Saleem, S.-H. Ahn and K.-D. Jung, *Catalysts*, 2019, **9**.
5. L. Fan, C. Xia, F. Yang, J. Wang, H. Wang and Y. Lu, *Science Advances*, 2020, **6**, eaay3111.
6. Q. Zhu, J. Ma, X. Kang, X. Sun, J. Hu, G. Yang and B. Han, *Sci. China. Chem.*, 2016, **59**, 551-556.
7. H. Yang, L. Wu, H. Wang and J. Lu, *Chinese. J. Catal.*, 2016, **37**, 994-998.
8. A. Loiudice, P. Lobaccaro, E. A. Kamali, T. Thao, B. H. Huang, J. W. Ager and R. Buonsanti, *Angew. Chem. Int. Ed.*, 2016, **55**, 5789-5792.
9. X. Kang, Q. Zhu, X. Sun, J. Hu, J. Zhang, Z. Liu and B. Han, *Chem. Sci.*, 2016, **7**, 266-273.
10. Y. Chen and T. Mu, *Green. Chem.*, 2019, **21**, 2544-2574.
11. X. Sun, Q. Zhu, X. Kang, H. Liu, Q. Qian, Z. Zhang and B. Han, *Angew. Chem. Int. Ed.*, 2016, **55**, 6771-6775.
12. P. Moreno-Garcia, N. Schlegel, A. Zanetti, A. Cedeno Lopez, M. J. Galvez-Vazquez, A. Dutta, M. Rahaman and P. Broekmann, *ACS. Appl. Mater. Inter.*, 2018, **10**, 31355-31365.
13. A. Eilert, F. S. Roberts, D. Friebe and A. Nilsson, *J Phys Chem Lett*, 2016, **7**, 1466-1470.
14. Z. Q. Liang, T. T. Zhuang, A. Seifitokaldani, J. Li, C. W. Huang, C. S. Tan, Y. Li, P. De Luna, C. T. Dinh, Y. Hu, Q. Xiao, P. L. Hsieh, Y. Wang, F. Li, R. Quintero-Bermudez, Y. Zhou, P. Chen, Y. Pang, S. C. Lo, L. J. Chen, H. Tan, Z. Xu, S. Zhao, D. Sinton and E. H. Sargent, *Nat. Commun.*, 2018, **9**, 3828.
15. F. S. Roberts, K. P. Kuhl and A. Nilsson, *Angew. Chem. Int. Ed.*, 2015, **54**, 5179-5182.
16. S. Sen, D. Liu and G. T. R. Palmore, *Acs. Catal.*, 2014, **4**, 3091-3095.
17. C. W. Li and M. W. Kanan, *J. Am. Chem. Soc.*, 2012, **134**, 7231-7234.
18. Z. Tan, T. Peng, X. Tan, W. Wang, X. Wang, Z. Yang, H. Ning, Q. Zhao and M. Wu, *ChemElectroChem*, 2020, **7**, 2020-2025.
19. Y. Zheng, A. Vasileff, X. Zhou, Y. Jiao, M. Jaroniec and S. Z. Qiao, *J. Am. Chem. Soc.*, 2019, **141**, 7646-7659.
20. C. Chen, X. Sun, L. Lu, D. Yang, J. Ma, Q. Zhu, Q. Qian and B. Han, *Green. Chem.*, 2018, **20**, 4579-4583.
21. S. Ma, M. Sadakiyo, M. Heima, R. Luo, R. T. Haasch, J. I. Gold, M. Yamauchi and P. J. Kenis, *J. Am. Chem. Soc.*, 2017, **139**, 47-50.
22. Y. Zhou, F. Che, M. Liu, C. Zou, Z. Liang, P. De Luna, H. Yuan, J. Li, Z. Wang, H. Xie, H. Li, P. Chen, E. Bladt, R. Quintero-Bermudez, T. K. Sham, S. Bals, J. Hofkens, D. Sinton, G. Chen and E. H. Sargent, *Nat. Chem.*, 2018, **10**, 974-980.
23. J. Du, S. Li, S. Liu, Y. Xin, B. Chen, H. Liu and B. Han, *Chemical Science*, 2020, **11**, 5098-5104.
24. H. Ning, X. Wang, W. Wang, Q. Mao, Z. Yang, Q. Zhao, Y. Song and M. Wu, *Carbon*, 2019, **146**, 218-223.
25. H. Mistry, A. S. Varela, C. S. Bonifacio, I. Zegkinoglou, I. Sinev, Y. W. Choi, K. Kisslinger, E. A. Stach, J. C. Yang, P. Strasser and B. R. Cuenya, *Nat. Commun.*, 2016, **7**, 12123.
26. D. Ren, Y. Deng, A. D. Handoko, C. S. Chen, S. Malkhandi and B. S. Yeo, *Acs. Catal.*, 2015, **5**, 2814-2821.
27. J.-C. Lee, J.-Y. Kim, W.-H. Joo, D. Hong, S.-H. Oh, B. Kim, G.-D. Lee, M. Kim, J. Oh and Y.-C. Joo, *J. Mater. Chem. A.*, 2020, **8**, 11632-11641.
28. D. Raciti, K. J. Livi and C. Wang, *Nano. Lett.*, 2015, **15**, 6829-6835.
29. L. Zhang, Z. J. Zhao and J. Gong, *Angew. Chem. Int. Ed.*, 2017, **56**, 11326-11353. view Article Online
DOI: 10.1039/D0GC03051A
30. K. Yao, Y. Xia, J. Li, N. Wang, J. Han, C. Gao, M. Han, G. Shen, Y. Liu, A. Seifitokaldani, X. Sun and H. Liang, *J. Mater. Chem. A.*, 2020, **8**, 11117-11123.
31. F. Li, L. Chen, G. P. Knowles, D. R. MacFarlane and J. Zhang, *Angew. Chem. Int. Ed.*, 2017, **56**, 505-509.
32. X. Wang, Z. Chen, X. Zhao, T. Yao, W. Chen, R. You, C. Zhao, G. Wu, J. Wang, W. Huang, J. Yang, X. Hong, S. Wei, Y. Wu and Y. Li, *Angew. Chem. Int. Ed.*, 2018, **57**, 1944-1948.
33. M. J. Mao, M. D. Zhang, D. L. Meng, J. X. Chen, C. He, Y. B. Huang and R. Cao, *ChemCatChem*, 2020, **12**, 3530-3536.
34. S. Jia, Q. Zhu, H. Wu, M. e. Chu, S. Han, R. Feng, J. Tu, J. Zhai and B. Han, *Chinese. J. Catal.*, 2020, **41**, 1091-1098.
35. Y. Chen, Z. Fan, J. Wang, C. Ling, W. Niu, Z. Huang, G. Liu, B. Chen, Z. Lai, X. Liu, B. Li, Y. Zong, L. Gu, J. Wang, X. Wang and H. Zhang, *J. Am. Chem. Soc.*, 2020, DOI: 10.1021/jacs.0c04981.
36. J. Huang, M. Mensi, E. Oveisi, V. Mantella and R. Buonsanti, *J. Am. Chem. Soc.*, 2019, **141**, 2490-2499.
37. J. T. Billy and A. C. Co, *Appl. Catal. B-Environ.*, 2018, **237**, 911-918.
38. T. T. H. Hoang, S. Verma, S. Ma, T. T. Fister, J. Timoshenko, A. I. Frenkel, P. J. A. Kenis and A. A. Gewirth, *J. Am. Chem. Soc.*, 2018, **140**, 5791-5797.
39. L. Lu, X. Sun, J. Ma, D. Yang, H. Wu, B. Zhang, J. Zhang and B. Han, *Angew. Chem. Int. Ed.*, 2018, **57**, 14149-14153.
40. D. Chen, Q. Yao, P. Cui, H. Liu, J. Xie and J. Yang, *ACS Appl. Energy Mater.*, 2018, **1**, 883-890.
41. B. J. Plowman, L. A. Jones and S. K. Bhargava, *Chem. Commun.*, 2015, **51**, 4331-4346.
42. X. Lu and C. Zhao, *Nat. Commun.*, 2015, **6**, 6616.
43. P. Ganesan, A. Sivanantham and S. Shanmugam, *ACS. Appl. Mater. Inter.*, 2017, **9**, 12416-12426.
44. Q. Zhu, X. Sun, D. Yang, J. Ma, X. Kang, L. Zheng, J. Zhang, Z. Wu and B. Han, *Nat. Commun.*, 2019, **10**, 3851.
45. T. Takashima, T. Suzuki and H. Irie, *Electrochim. Acta*, 2017, **229**, 415-421.
46. J. Resasco, L. D. Chen, E. Clark, C. Tsai, C. Hahn, T. F. Jaramillo, K. Chan and A. T. Bell, *J. Am. Chem. Soc.*, 2017, **139**, 11277-11287.
47. A. S. Varela, W. Ju, T. Reier and P. Strasser, *Acs. Catal.*, 2016, **6**, 2136-2144.
48. M. R. Singh, Y. Kwon, Y. Lum, J. W. Ager, 3rd and A. T. Bell, *J. Am. Chem. Soc.*, 2016, **138**, 13006-13012.
49. J. Fu, W. Zhu, Y. Chen, Z. Yin, Y. Li, J. Liu, H. Zhang, J. J. Zhu and S. Sun, *Angew. Chem. Int. Ed.*, 2019, **58**, 14100-14103.