

## Oxidation of Alkanes by Dioxygen Catalysed by Photoactivated Iron Porphyrins

A. Maldotti,\*<sup>a</sup> C. Bartocci,<sup>a</sup> R. Amadelli,<sup>a</sup> E. Polo,<sup>a</sup> P. Battioni<sup>b</sup> and D. Mansuy\*<sup>b</sup>


<sup>a</sup> Centro di Fotochimica del CNR, Dipartimento di Chimica dell'Università di Ferrara, Via L. Borsari, 46 I-44100 Ferrara, Italy

<sup>b</sup> Laboratoire de Chimie et Biochimie Pharmacologiques et Toxicologiques, URA 400 CNRS, Université René Descartes, 45 rue des Saints-Pères, 75270 Paris Cedex 06, France

Cycloalkanes were oxidized by O<sub>2</sub> itself under mild conditions (22 °C; 200 Torr of O<sub>2</sub>) in the presence of catalytic amounts of a polyhalogenated porphyrin–iron(III)–hydroxo complex irradiated with light of wavelength between 350 and 450 nm; these oxidations occurred without consumption of a reducing agent, selectively transformed cyclohexane into cyclohexanone under appropriate conditions (about 0.2 turnover per min), and did not involve Fe<sup>V</sup>=O active species but, more probably, iron-alkylperoxo intermediates.

Iron porphyrins have been found to be efficient biomimetic catalysts for alkene epoxidation and alkane hydroxylation, by use of either various oxygen atom donors or of O<sub>2</sub> itself in the presence of a reducing agent, according to the monooxygenase reaction [eqn. (1)].<sup>1</sup> From a chemical point of view, it would be particularly interesting to find catalytic systems able to perform alkane oxidation by O<sub>2</sub> without the need for and consumption of a reducing agent. Iron polyhalogenated


porphyrins have recently been found to catalyse the oxidation of alkanes into alcohols and ketones under an O<sub>2</sub> pressure of *ca.* 10 atm, and temperatures of *ca.* 80 °C.<sup>2</sup>



This communication describes results showing for the first time that cycloalkanes are efficiently oxidized by O<sub>2</sub> itself

under mild conditions (22 °C; 1 atm: 200 Torr of O<sub>2</sub>) in the presence of catalytic amounts of iron(III) complexes of *meso*-tetrakis(2,6-dichlorophenyl)porphyrin, Fe<sup>III</sup>(tdcpp), under irradiation with light of wavelength between 350 and 450 nm. These oxidations occur without consumption of a reducing agent and, under appropriate conditions, cyclohexane is selectively transformed into cyclohexanone. Their mechanism is discussed in relation to the mechanism of oxidations catalysed by cytochrome P-450 and model systems.

Photoirradiation at 365 nm of deaerated solutions of Fe<sup>III</sup>(tdcpp)(OH) in cyclohexane led to its reduction into Fe<sup>II</sup>(tdcpp) as shown by visible spectroscopy. The quantum yield of this photoreduction of Fe<sup>III</sup>(tdcpp)(OH) was determined by a previously reported method<sup>3</sup> and found to be 10<sup>-4</sup>. Upon introduction of O<sub>2</sub> into the solution, the spectrum of Fe<sup>III</sup>(tdcpp)(OH) was restored. Identical irradiation of Fe(tdcp)(OH) in the cavity of an ESR spectrometer but in the presence of 5,5-dimethylpyrroline *N*-oxide (dmpo) as a spin trap<sup>4</sup> led to an ESR spectrum exhibiting the typical signals of the adduct between dmpo and ·OH radicals.<sup>5</sup> These results indicate that, upon irradiation, (tdcpp)Fe<sup>III</sup>-OH undergoes a homolytic cleavage of its iron-axial ligand bond [eqn. (2)], a type of reaction already observed for many other porphyrin-Fe<sup>III</sup>-L complexes.<sup>6-12</sup>



Irradiation (350–450 nm) of Fe(tdcp)(OH) in cyclohexane under a pressure of 200 Torr of O<sub>2</sub> led to the progressive appearance of cyclohexanone as a function of the irradiation time. Cyclohexanone formation followed zero-order kinetics allowing us to calculate a quantum yield of  $1.7 \times 10^{-3}$  for this reaction and a rate of 0.14 turnover per min (Table 1). Fe(tdcp)(OH) slowly disappeared during this reaction but 80

**Table 1** Oxidation of cycloalkanes by O<sub>2</sub> catalysed by photoirradiated iron porphyrins<sup>a</sup>


| Catalyst                | Products <sup>b</sup> | 10 <sup>3</sup> Φ <sub>ox</sub> <sup>c</sup> | Initial <sup>d</sup> rate | Turnover <sup>e</sup> |
|-------------------------|-----------------------|--|---------------------------|-----------------------|
| Substrate = cyclohexane |                       |  |                           |                       |
| Fe(tdcpp)(OH)           | one                   | 1.7  | 0.14                      | 80                    |
|                         | ol                    | <0.1   |                           | <2                    |
| Fe(tdcpp)(Cl)           | one                   | 0.25   | 0.02                      | 3                     |
|                         | ol                    | 0.55   |                           | 7                     |
| Fe(tdcpp)(OEt)          | one                   | 0.45   | 0.03                      | 10                    |
|                         | ol                    | 0.75   |                           | 18                    |
| Fe(tpp)(Cl)             | one                   | <0.1   | —                         | <2                    |
|                         | ol                    | <0.1   |                           | —                     |
| Fe(tmp)(OH)             | one                   | <0.1   | —                         | —                     |
|                         | ol                    | <0.1   |                           | —                     |
| Substrate = cyclooctane |                       |  |                           |                       |
| Fe(tdcpp)(OH)           | one                   | 6.3  | 0.55                      | 150                   |
|                         | ol                    | 1.0  |                           | 25                    |
| Fe(tdcpp)(Cl)           | one                   | 1.0  | 0.08                      | 170                   |
|                         | ol                    | 0.35   |                           | 60                    |

<sup>a</sup> In a typical experiment, a  $3 \times 10^{-5}$  mol dm<sup>-3</sup> solution of iron porphyrin in aerated cyclohexane (200 Torr O<sub>2</sub>) was irradiated in a 1 cm spectrophotometric cell with light of wavelength between 350 and 450 nm at 22 ± 1 °C as reported previously.<sup>3</sup> (Hanau Q400 mercury lamp; selection of required wavelength range by use of a glass cut-off filter.) Under these conditions, incident light was completely absorbed. Reaction products were determined by GC by comparison of their retention times with those of authentic samples, using iodobenzene as internal standard. Reported values are ±10%. <sup>b</sup> One = cyclohexanone for cyclohexane and cyclooctanone for cyclooctane; ol = cyclohexanol for cyclohexane and cyclooctanol for cyclooctane. <sup>c</sup> Moles of product per mole of absorbed photons. <sup>d</sup> Moles of products formed per mole of iron catalyst and per min, at the beginning of the reaction. <sup>e</sup> Moles of product formed per mole of consumed iron porphyrin.

moles of product were obtained per mole of consumed catalyst. Interestingly, cyclohexanol was only formed in very minor amounts in this reaction (Φ<sub>ox</sub> < 10<sup>-5</sup>). Replacement of Fe(tdcp)(OH) by Fe(tdcp)(Cl) or Fe(tdcp)(OEt) led to a much less efficient oxidation of cyclohexane and to a completely different cyclohexanol:cyclohexanone ratio [2:1 instead of 0.02:1 in the case of Fe(tdcp)(OH)] (Table 1). Under identical conditions, Fe<sup>III</sup> complexes of porphyrins less resistant towards oxidative degradation, like Fe(tpp) (tpp = *meso*-tetraphenylporphyrin) or Fe(tmp)(OH) [tmp = *meso*-tetrakis-(2,4,6-trimethylphenyl)porphyrin] led to the formation of both cyclohexanol and cyclohexanone with very low yields (Φ<sub>ox</sub> < 10<sup>-4</sup>).<sup>†</sup>

Irradiation of Fe(tdcp)(OH) in cyclooctane also led to the major formation of cyclooctanone with a relatively good quantum yield ( $6.3 \times 10^{-3}$ ) with 150 turnovers of the catalyst before its disappearance. However, in contrast to what was observed for cyclohexane, the alcohol:ketone ratio obtained with Fe(tdcp)(OH) was higher (0.17:1 instead of 0.02:1) and the alcohol and ketone yields did not markedly change upon replacement of Fe(tdcp)(OH) by Fe(tdcp)(Cl) (Table 1).

The following experiments have been done in order to discover whether the high-valent iron-oxo (formally Fe<sup>V</sup>=O) species, which are the active species in iron porphyrin-catalysed monooxygenations of substrates either by single oxygen atom donors or by O<sub>2</sub> and a reducing agent,<sup>1</sup> were also involved in the above described photoassisted oxidations. These active Fe<sup>V</sup>=O species are very efficient for the epoxidation of alkenes like cyclohexene or *cis*-stilbene,<sup>1</sup> even in the presence of an excess of alkane.<sup>13</sup> However, irradiation of Fe(tdcp)(OH) either in pure cyclohexene or in CH<sub>2</sub>Cl<sub>2</sub> containing 5% of *cis*-stilbene,<sup>‡</sup> under conditions identical to those used for cyclohexane, failed to give detectable amounts of the corresponding epoxides, whereas large amounts of allylic oxidation products were formed in the case of cyclohexene (5000 and 4500 turnovers after 30 min reaction for the formation of cyclohexenol and cyclohexenone, respectively). These results indicate that the major active species involved in the observed photoassisted oxidation of cycloalkanes catalysed by Fe<sup>III</sup>(tdcp)(OH) is not a (tdcp)Fe<sup>V</sup>=O complex. A likely mechanism for cyclohexanone formation in this reaction involves ·OH radicals formed by photocleavage of the Fe–OH bond of Fe(tdcp)(OH) [eqn. (2)] as a reactive species. This radical should easily abstract a hydrogen atom of cyclohexane, leading to the formation of an Fe<sup>II</sup>-cyclohexyl radical pair (Scheme 1). Reaction of O<sub>2</sub> with this pair of free radicals (which could exist as an Fe<sup>III</sup>-σ-alkyl complex<sup>1c</sup>) could lead to an Fe<sup>III</sup>-peroxoalkyl complex. Such complexes

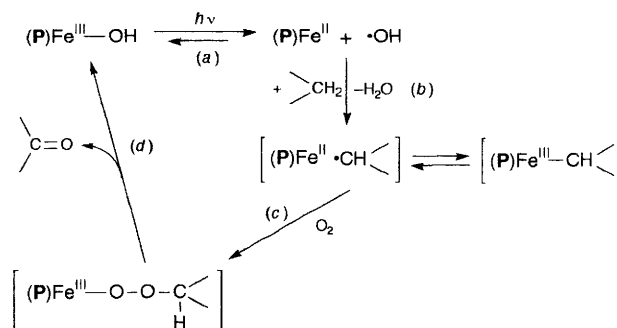


**Scheme 1**

<sup>†</sup> Oxidation of cumene by O<sub>2</sub> and photoirradiated Fe(tpp)(Cl) has been reported;<sup>12</sup> these authors mentioned that other substrates more difficult to oxidize were not hydroxylated by this Fe(tpp)(Cl) system.

<sup>‡</sup> In the case of reactions performed on *cis*-stilbene, irradiations were carried out at λ > 400 nm to avoid direct photochemistry of this aromatic alkene.

were found rapidly and selectively to decompose with formation of the corresponding ketone and the starting  $\text{Fe}^{\text{III}}$  complex.<sup>14</sup> Under the conditions used, this reaction would regenerate  $(\text{tdcpp})\text{Fe}^{\text{III}}\text{-OH}$ . The mechanism of Scheme 1 would explain the selective formation of cyclohexanone from cyclohexane and irradiated  $\text{Fe}(\text{tdcpp})(\text{OH})$  in catalytic amounts with the stoichiometry of eqn. (3). It would also



explain why this system is not able to epoxidize alkenes, as its active  $\cdot\text{OH}$  species is very prone to abstract hydrogen atoms from alkanes or alkenes (in allylic position) but not to add to alkene double bonds. It is noteworthy that step (a)<sup>11</sup> and steps (c + d)<sup>14</sup> have already been reported. The minor formation of alcohols from cyclohexane and cyclooctane and  $\text{Fe}(\text{tdcpp})(\text{OH})$  could derive from secondary reactions due to the formation of  $\text{ROO}\cdot$ <sup>12</sup> or  $\text{ROOH}$  (after steps b and c) and their further decomposition catalysed by  $\text{Fe}(\text{tdcpp})$ .<sup>15</sup>

This photoassisted oxidation of cyclohexane into cyclohexanone catalysed by  $\text{Fe}(\text{tdcpp})(\text{OH})$  is a new kind of selective activation and functionalization of alkanes by  $\text{O}_2$  under mild conditions, as it does not need any consumption of a reducing agent in contrast with most of the previously described comparable iron porphyrin-based systems and as its mechanism better corresponds to a dioxygenase rather than to a monooxygenase reaction.

Received, 26th July 1991; Com. 1/03873G

## References

- 1 For recent reviews: (a) T. J. McMurtry and J. T. Groves, in *Cytochrome P-450, Structure, Mechanism and Biochemistry*, ed. P. R. Ortiz de Montellano, Plenum press, New York and London 1986, pp. 1–28; (b) B. Meunier, *Bull. Soc. Chim. Fr.*, 1986, **II**, 4, 578; (c) D. Mansuy, P. Battioni and J. P. Battioni, *Eur. J. Biochem.*, 1989, **184**, 267; (d) T. Okamoto, K. Sasaki and M. Tachibana, *Bull. Inst. Chem. Res., Kyoto Univ.*, 1989, **67**, 169; (e) D. Mansuy, *Pure Appl. Chem.*, 1990, **62**, 741.
- 2 P. E. Ellis and J. E. Lyons, *Coord. Chem. Rev.*, 1990, **105**, 181.
- 3 C. Bartocci, A. Maldotti, G. Varani, P. Battioni, V. Carassiti and D. Mansuy, *Inorg. Chem.*, 1991, **30**, 1255.
- 4 E. G. Janzen, *Acc. Chem. Res.*, 1971, **4**, 31.
- 5 J. R. Harbour and M. L. Hair, *Can. J. Chem.*, 1974, **52**, 3549.
- 6 C. Bartocci, F. Scandola, A. Ferri and V. Carassiti, *J. Am. Chem. Soc.*, 1980, **102**, 7067.
- 7 C. Bizet, P. Morlière, D. Brault, O. Delgado, M. Bazin and R. Santus, *Photochem. Photobiol.*, 1981, **34**, 315.
- 8 A. Maldotti, C. Bartocci, C. Chiorboli, A. Ferri and V. Carassiti, *J. Chem. Soc., Chem. Commun.*, 1985, 881.
- 9 Y. Ozaki, K. Iniyama, H. Ogoshi and T. Kitagawa, *J. Am. Chem. Soc.*, 1987, **109**, 5583.
- 10 M. W. Peterson, D. S. Rivers and R. M. Richman, *J. Am. Chem. Soc.*, 1985, **107**, 2907.
- 11 A. Tohara and M. Sato, *Chem. Lett.*, 1989, 153.
- 12 D. N. Hendrickson, M. G. Kinnaird and K. S. Suslick, *J. Am. Chem. Soc.*, 1987, **109**, 1243.
- 13 J. F. Bartoli, O. Brigaud, P. Battioni and D. Mansuy, *J. Chem. Soc., Chem. Comm.*, 1991, 440.
- 14 R. D. Arasasingham, A. L. Balch, C. R. Cornman and L. Latos-Grazynski, *J. Am. Chem. Soc.*, 1989, **111**, 4357.
- 15 D. Mansuy, J. F. Bartoli and M. Momenteau, *Tetrahedron Lett.*, 1982, **23**, 2781.