

193-nm Photoresists Based on Norbornene Copolymers with Derivatives of Bile Acid

Jin-Baek Kim*, Bum-Wook Lee, Hyo-Jin Yun, and Young-Gil Kwon
 Department of Chemistry, Korea Advanced Institute of Science and Technology,
 373-1 Kusong-dong, Yusong-gu, Taejeon 305-701, Korea

(Received November 26, 1999; CL-991003)

We synthesized new chemically amplified photoresists for 193-nm lithography. Norbornene substituted with a derivative of bile acid was copolymerized with maleic anhydride by free radical polymerization. The resulting copolymers have good transmittance at 193 nm and possess excellent thermal stability up to 260 °C. With the standard developer, the resists formulated with the copolymers form 0.15–0.18 μm patterns at doses of 6–7 mJ cm^{-2} using an ArF excimer laser stepper.

In 1992, Fujitsu's researchers first proposed an alicyclic incorporated polymer, "alicyclic polymer", realizing both high transparency at 193 nm and good dry-etching resistance of the resist.^{1a} Since then, chemically amplified photoresists which have been designed for 193-nm lithography almost involve methacrylate-based polymers with pendant alicyclic moieties^{1–5} and cycloolefin-maleic anhydride copolymers.^{6–8} However, there have been difficulties in satisfying both high dry-etching resistance and good lithographic performance such as adhesion and resolution.

Previously we reported a norbornene copolymer with a derivative of cholic acid, poly(*t*-butyl 3 α -(5-norbornene-2-carbonyloxy)-7 α ,12 α -dihydroxy-5 β -cholan-24-oate-co-maleic anhydride) (poly(TBNDHC-co-MA)), for 193-nm lithography.⁹ Poly(TBNDHC-co-MA) had high transparency at 193 nm and showed better dry-etching resistance than the conventional KrF excimer laser resist for chlorine and oxygen mixed gas. The PMT etcher was used with flow rates of 20 sccm of chlorine and 4 sccm of oxygen at 800 W for 40 s. The resist formulated with poly(TBNDHC-co-MA) resolved 0.15 μm line and space patterns, but the patterns exhibited top-rounding profiles (Figure 1). The top-rounding is mainly caused by dark erosion due to dissolution of the unexposed resist in a developing solution. To improve the pattern profiles, the matrix polymer needs to be less hydrophilic than poly(TBNDHC-co-MA) while satisfying adhesion to silicon substrate.




Figure 1. Scanning electron micrograph of 0.15 μm line and space patterns with poly(TBNDHC-co-MA).

We synthesized norbornene monomer with a derivative of lithocholic acid, *t*-butyl 3 α -(5-norbornene-2-carbonyloxy)-5 β -cholan-24-oate (TBNC). As TBNC does not have a hydroxyl group, it is less hydrophilic than TBNDHC which has two secondary hydroxyl groups. TBNC¹⁰ was synthesized by one-step esterification of *t*-butyl lithocholate (TBLC) with 2-chlorocar-

bonyl-5-norbornene (CCN) in the presence of triethylamine. TBLC was synthesized by the method reported in the literature.¹¹ CCN was prepared by Diels-Alder reaction between cyclopentadiene and acryloyl chloride. As TBNC does not have any functional groups providing adhesion to silicon substrate, TBNC was copolymerized¹² with MA and 2-hydroxyethyl 5-norbornene-2-carboxylate (HENC) which has a primary hydroxyl group. HENC was synthesized by the method described in the literature.¹³ The copolymer was synthesized by free radical polymerization using 2,2'-azobisisobutyronitrile (AIBN) as an initiator.¹⁴ The chemical structure of the resulting copolymer is shown in Figure 2.

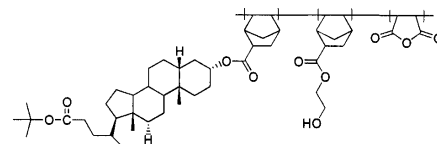


Figure 2. The chemical structure of poly(TBNC-co-HENC-co-MA).

A photoresist solution was prepared by dissolving 1.2 g of the copolymer and 0.024 g of triphenylsulfonium triflate as a photoacid generator in 6.0 g of propylene glycol monomethyl ether acetate (PGMEA). The photoresist solution was spin-coated on a hexamethyldisilazane treated silicon wafer and prebaked at 110 °C for 90 s. Exposure was carried out at 193 nm with a ISI ArF excimer laser stepper with 0.6 NA. The illumination was off-axis and the mask was binary. The wafer was baked at 110 °C for 90 s and developed by dipping in a 0.262 M tetramethylammonium hydroxide aqueous solution. The resist formulated with the copolymer gave patterns of flat tops as expected. However, 0.18 μm patterns exhibited footing (Figure 3 (a)). Furthermore, 0.16 μm patterns were not separated completely due to severe footing in the exposure area (Figure 3 (b)).

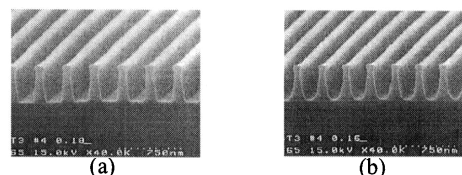


Figure 3. Scanning electron micrographs of 0.18 μm (a) and 0.16 μm (b) features with a thickness of 0.5 μm printed with poly(TBNC-co-HENC-co-MA) at a dose of 6 mJ cm^{-2} .

To investigate the cause of footing, the photoresist solution was spin-coated on NaCl cells and then the cells were prebaked at 110 °C for 90 s. The cells were exposed at a dose of 50 mJ cm^{-2} using a deep UV exposure tool. The exposed cells were

baked for 90 s at 100 °C, 110 °C, and 130 °C, respectively. FT-IR spectra were measured before exposure, after postexposure bake (PEB) at 100 °C, 110 °C, and 130 °C, respectively (Figure 4). In Figure 4, the band intensity around 3700–2500 cm⁻¹ due to carboxyl and hydroxyl groups decreases as the PEB temperature increases from 110 °C to 130 °C. It indicates that esterification reactions of primary hydroxyl groups with carboxyl groups generated from deprotection reactions of *t*-butoxycarbonyl groups occur as the PEB temperature increases from 110 °C to 130 °C. From the result of the change of FT-IR spectra on PEB temperature, it was thought that footing was caused by cross-linking reaction due to primary hydroxyl groups of HENC. Meanwhile, no sign of esterification reaction between secondary hydroxyl group in TBNHC and carboxyl groups was detected up to 130 °C under the same condition described above.

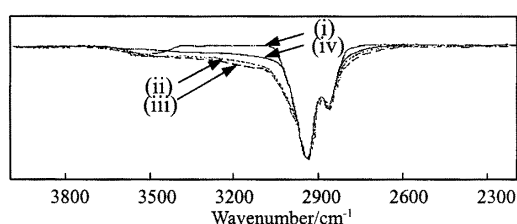


Figure 4. FT-IR spectra of poly(TBNC-co-HENC-co-MAN) before exposure (i), post-exposure-baked at 100 °C (ii), 110 °C (iii), and 130 °C (iv).

In order to improve pattern profiles, we synthesized *t*-butyl 3 α -(5-norbornene-2-carboxyloxy)-12 α -hydroxy-5 β -cholan-24-oate (TBNHC) which has intermediate hydrophilicity between TBNDHC and TBNC, by one-step esterification of *t*-butyl deoxycholate (TBDC) with CCN in the presence of triethylamine.¹⁵ TBDC was synthesized by the method described in the literature.¹¹ Poly(TBNHC-co-MA) was synthesized by free radical polymerization using AIBN as an initiator.¹⁶ The chemical structure of the resulting copolymer is shown in Figure 5.

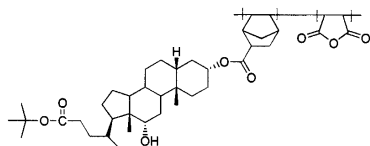


Figure 5. The chemical structure of poly(TBNHC-co-MA).

Photoresist solution was prepared in the same way as for the poly(TBNC-co-HENC-co-MA). Lithographic evaluation was also performed using the same procedure as for the poly(TBNC-co-HENC-co-MA). The resist formulated with




Figure 6. Scanning electron micrograph of 0.15 μm line and space patterns with a thickness of 0.38 μm printed with poly(TBNHC-co-MA) at a dose of 7 mJ cm⁻².

poly(TBNHC-co-MA), 0.15 μm line and space patterns are well defined with flat tops and without footing (Figure 6).

In conclusion, it was found that the degree of hydrophilicity of a matrix polymer affected the shape of patterns. Besides, type of hydroxyl group used to enhance adhesion to silicon substrate had decisive influence on resolution of the patterns.

The authors would like to acknowledge the financial support of Ministry of Commerce, Industry & Energy (B38-979-5406-01). The authors also wish to thank Dr. Ki-Ho Baik and Dr. Jae-Chang Jung of Hyundai Electronics Co., Ltd. for lithographic evaluation and Dr. Seong-Ju Kim and Mr. Dong-Chul Seo of Korea Kumho Petrochemical Co., Ltd. for useful discussion.

References and Notes

- 1 a) Y. Kaimoto, K. Nozaki, S. Takechi, and N. Abe, *Proc. SPIE*, **1672**, 66 (1992). b) S. Takechi, M. Takahashi, A. Kotachi, K. Nozaki, E. Yano, and I. Hanyu, *J. Photopolym. Sci. Technol.*, **9**, 475 (1996).
- 2 a) K. Nakano, K. Maeda, S. Iwasa, J. Yano, Y. Ogura, and E. Hasegawa, *Proc. SPIE*, **2195**, 194 (1994). b) K. Maeda, K. Nakano, S. Iwasa, and E. Hasegawa, *Proc. SPIE*, **3049**, 55 (1997).
- 3 R. D. Allen, I. Y. Wan, G. M. Wallraff, R. A. DiPietro, D. C. Hofer, and R. R. Kunz, *J. Photopolym. Sci. Technol.*, **8**, 623 (1995).
- 4 N. Shida, T. Ushiroguchi, K. Asakawa, and M. Nakase, *J. Photopolym. Sci. Technol.*, **9**, 457 (1996).
- 5 K. Yamashita, M. Endo, M. Sasago, N. Nomura, H. Nagano, S. Mizuguchi, T. Ono, and T. Sato, *J. Vac. Sci. Technol.*, **B 11**, 2692 (1993).
- 6 a) U. Okoroanyanwu, T. Shimokawa, J. Byers, D. Medeiros, C. G. Willson, Q. J. Niu, J. M. J. Fréchet, and R. D. Allen, *Proc. SPIE*, **3049**, 84 (1997). b) U. Okoroanyanwu, J. Byers, T. Shimokawa, and C. G. Willson, *Chem. Mater.*, **10**, 3328 (1998). c) D. Pasini, E. Low, R. P. Meagley, J. M. J. Fréchet, C. G. Willson, and J. D. Byers, *Proc. SPIE*, **3678**, 94 (1999).
- 7 J. C. Jung, C. K. Bok, and K. H. Baik, *Proc. SPIE*, **3333**, 11 (1998).
- 8 M. Suwa, H. Iwasawa, T. Kajita, M. Yamamoto, and S. I. Iwanaga, *Proc. SPIE*, **3333**, 26 (1998).
- 9 J. B. Kim, B. W. Lee, J. S. Kang, D. C. Seo, and C. H. Roh, *Polymer*, **40**, 7423 (1999).
- 10 TBNC was obtained in a yield of 75% as a white powder. ¹H-NMR (CDCl₃, 300 MHz, TMS): 0.69 (3H, s, 18-methyl), 0.89 (3H, s, 19-methyl), 0.97 (3H, d, *J* = 6 Hz, 21-methyl), 1.01–2.02 (26H, m), 1.43 (9H, s, *t*-butyl), 2.19 (4H, m), 2.85 (2H, m), 3.16 (1H, m), 4.50 (1H, m, 3-H), 5.91 (1H, m, *endo*-olefinic proton), 6.11 (2H, m, *exo*-olefinic protons), 6.15 (1H, m, *endo*-olefinic proton). FT-IR (cm⁻¹): 3492 (OH), 2942 (alicyclic CH), 1729 (C=O of ester), 1151 (C-O of ester).
- 11 F. M. Houlihan, T. I. Wallow, O. Nalamasu, and E. Reichmanis, *Macromolecules*, **30** (21), 6517 (1997).
- 12 Feed ratio of the monomers is TBNC : HENC : MA = 42.5 : 7.5 : 50 (mol%). Poly(TBNC-co-HENC-co-MA) was obtained in a yield of 32% as a white powder. The *M_w* and MWD were 4970 g mol⁻¹ and 1.5, respectively. The *T_d* was 261.1 °C and *T_g* was not detected. The absorbance of the polymer was 0.30 μm^{-1} at 193 nm. Copolymers having feed ratio less than 7.5 mol% HENC cannot be used for lithographic evaluation due to loss of adhesion to silicon substrate.
- 13 J. C. Jung, M. H. Jung, and K. H. Baik, *J. Photopolym. Sci. Technol.*, **11**, 481 (1997).
- 14 Polymerization was carried out in dry toluene using 1.0 mol% of AIBN at 65 °C under vacuum in a sealed ampoule for 20 h.
- 15 TBNHC was obtained in a yield of 72% as a white powder. ¹H-NMR (CDCl₃, 300 MHz, TMS): δ = 0.67 (3H, s, 18-methyl), 0.89 (3H, s, 19-methyl), 0.98 (3H, d, *J* = 6 Hz, 21-methyl), 1.02–2.03 (25H, m), 1.43 (9H, s, *t*-butyl), 2.19 (4H, m), 2.85 (2H, m), 3.16 (1H, m), 3.99 (1H, m, *J* = 3 Hz, 12-H), 4.51 (1H, m, 3-H), 5.92 (1H, m, *endo*-olefinic proton), 6.09 (2H, m, *exo*-olefinic protons), 6.14 (1H, m, *endo*-olefinic proton). FT-IR (cm⁻¹): 3488 (OH), 2943 (alicyclic CH), 1730 (C=O of ester), 1154 (C-O of ester).
- 16 Polymerization was carried out in dry THF using 1.0 mol% of AIBN at 65 °C under vacuum in a sealed ampoule for 20 h. Feed ratio of the monomers is TBNHC : MA = 50 : 50 (mol%). Poly(TBNHC-co-MA) was obtained in a yield of 31% as a white powder. The *M_w* and MWD were 5160 g mol⁻¹ and 1.6, respectively. The *T_d* was 259.4 °C and *T_g* was not detected. The absorbance of the polymer was 0.31 μm^{-1} at 193 nm.