

# Accepted Manuscript

Synthesis, structure, and properties of  $\text{EuErCuS}_3$

Anna V. Ruseikina, Leonid A. Solovyov, Vladimir A. Chernyshev, Aleksandr S. Aleksandrovsky, Oleg V. Andreev, Svetlana N. Krylova, Alexander S. Krylov, Dmitriy A. Velikanov, Maxim S. Molokeev, Nikolai G. Maximov, Maxim V. Grigoriev, Alexander A. Garmonov, Alexey V. Matigorov



PII: S0925-8388(19)32553-8

DOI: <https://doi.org/10.1016/j.jallcom.2019.07.059>

Reference: JALCOM 51347

To appear in: *Journal of Alloys and Compounds*


Received Date: 19 May 2019

Revised Date: 29 June 2019

Accepted Date: 5 July 2019

Please cite this article as: A.V. Ruseikina, L.A. Solovyov, Vladimir.A. Chernyshev, A.S. Aleksandrovsky, O.V. Andreev, S.N. Krylova, A.S. Krylov, Dmitriy.A. Velikanov, M.S. Molokeev, N.G. Maximov, M.V. Grigoriev, A.A. Garmonov, A.V. Matigorov, Synthesis, structure, and properties of  $\text{EuErCuS}_3$ , *Journal of Alloys and Compounds* (2019), doi: <https://doi.org/10.1016/j.jallcom.2019.07.059>.

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

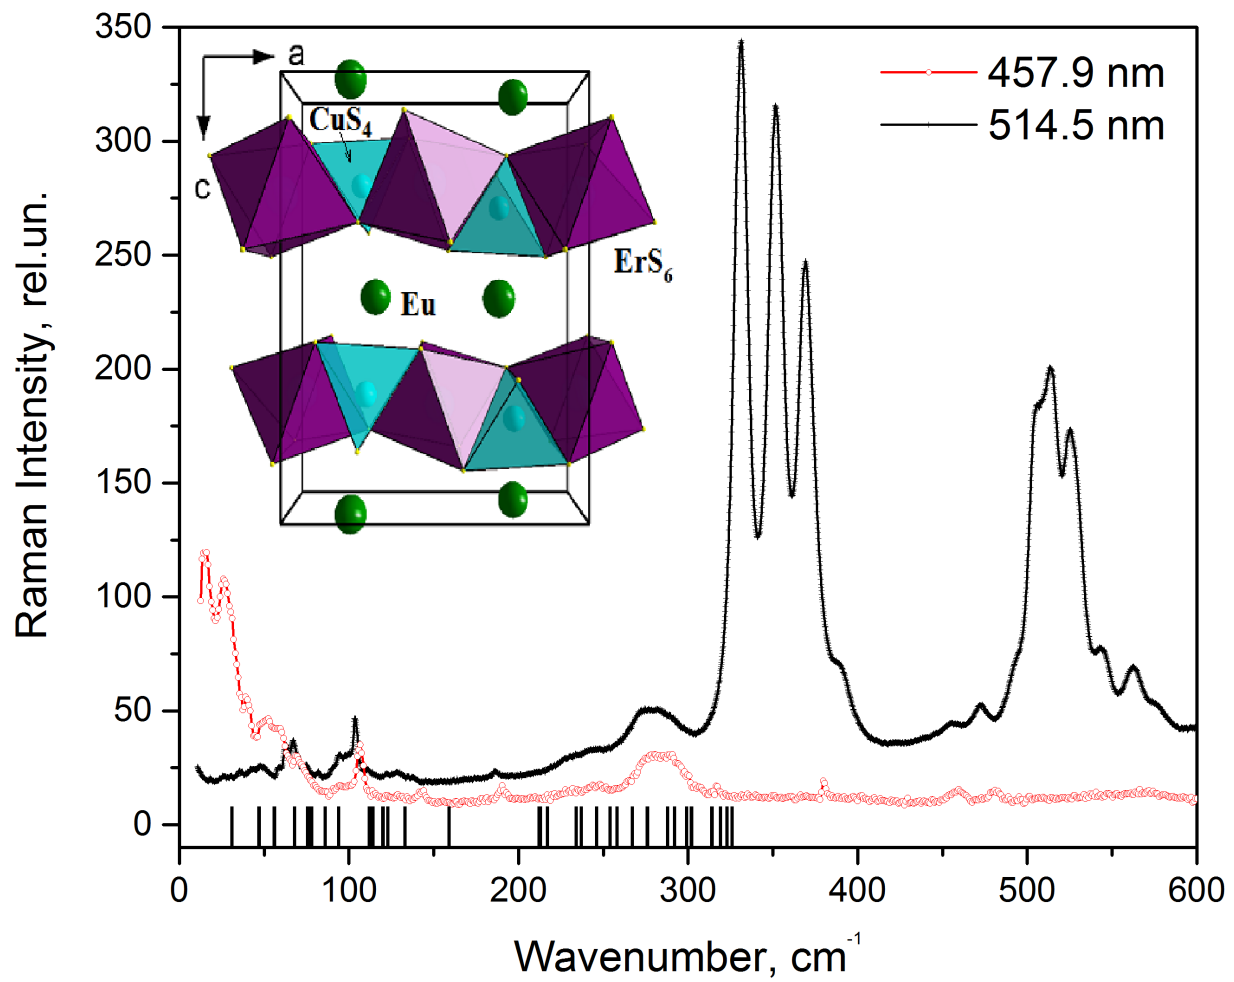

**Synthesis, Structure, and Properties of EuErCuS<sub>3</sub>**

Anna V. Ruseikina<sup>a</sup>, Leonid A. Solovyov<sup>b</sup>, Vladimir A. Chernyshev<sup>c</sup>,  
Aleksandr S. Aleksandrovsky<sup>d,e</sup>, Oleg V. Andreev<sup>a</sup>, Svetlana N. Krylova<sup>d</sup>,  
Alexander S. Krylov<sup>d</sup>, Dmitriy A. Velikanov<sup>d</sup>, Maxim S. Molokeev<sup>f,g</sup>,  
Nikolai G. Maximov<sup>h</sup>, Maxim V. Grigoriev<sup>a</sup>, Alexander A. Garmonov<sup>i</sup>,  
Alexey V. Matigorov<sup>a</sup>

<sup>a</sup>Institute of Chemistry, University of Tyumen, Tyumen 625003, Russia

<sup>b</sup>Institute of Chemistry and Chemical Technology, Federal Research Center KSC SB RAS, Krasnoyarsk 660049, Russia

<sup>c</sup>Institute of Natural Sciences and Mathematics, Ural Federal University, Ekaterinburg 620002, Russia

<sup>d</sup>Laboratory of Coherent Optics, Kirensky Institute of Physics, Federal Research Center KSC SB RAS, Krasnoyarsk 660036, Russia

<sup>e</sup>Department of Photonics and Laser Technologies, Siberian Federal University, Krasnoyarsk 660079, Russia

<sup>f</sup>Laboratory of Crystal Physics, Kirensky Institute of Physics, Federal Research Center KSC SB RAS, Krasnoyarsk 660036, Russia

<sup>g</sup>Siberian Federal University, Krasnoyarsk 660079, Russia

<sup>h</sup>Institute of Chemistry and Chemical Technology SB RAS, Federal Research Center “Krasnoyarsk Science Center SB RAS”

<sup>i</sup>Institute of Physics and Technology, University of Tyumen, Tyumen 625003, Russia

Corresponding author:

Institute of Chemistry, University of Tyumen, Perekopskaya 15a, Tyumen 625003, Russia

Phone: 89129905701

E-mail: adeschina@mail.ru

**Abstract**

The crystal structure of the first-synthesized compound  $\text{EuErCuS}_3$  was determined from X-ray powder diffraction data: orthorhombic crystal system, space group  $Pnma$ , structural type  $\text{Eu}_2\text{CuS}_3$ :  $a = 10.1005(2) \text{ \AA}$ ,  $b = 3.91255(4) \text{ \AA}$ ,  $c = 12.8480(2) \text{ \AA}$ ;  $V = 507.737(14) \text{ \AA}^3$ ,  $Z = 4$ , and  $\rho_x = 6.266 \text{ g/cm}^3$ . The temperatures and enthalpies of reversible polymorphic transitions and incongruent melting of the compound were determined by DSC:  $T_{\alpha \leftrightarrow \beta} = 1524 \text{ K}$ ,  $\Delta H_{\alpha \leftrightarrow \beta} = 2.3 \pm 0.2 \text{ kJ}\cdot\text{mol}^{-1}$ ;  $T_{\beta \leftrightarrow \gamma} = 1575 \text{ K}$ ,  $\Delta H_{\beta \leftrightarrow \gamma} = 0.7 \pm 0.1 \text{ kJ}\cdot\text{mol}^{-1}$ ;  $T_{\gamma \leftrightarrow \delta} = 1602 \text{ K}$ ;  $\Delta H_{\gamma \leftrightarrow \delta} = 1.3 \pm 0.1 \text{ kJ}\cdot\text{mol}^{-1}$  and  $T_m = 1740 \pm 6 \text{ K}$ ,  $\Delta H_{cr} = -3.5 \pm 0.3 \text{ kJ}\cdot\text{mol}^{-1}$ . IR spectra were recorded in the range from 50 to  $400 \text{ cm}^{-1}$ . The compound was found to be IR-transparent in the range  $4000\text{--}400 \text{ cm}^{-1}$ . The compound was characterized by Raman spectroscopy. The observed spectra featured both Raman lines and luminescence. Ab initio calculations of the  $\text{EuErCuS}_3$  crystal structure and phonon spectrum were performed, the frequencies and types of fundamental modes were determined, and the involvement of constituent ions in the IR and Raman modes was assessed from an analysis of the ab initio displacement vectors. The vibrational spectra were interpreted.  $\text{EuErCuS}_3$  manifests a ferrimagnetic transition at 4.8 K. Its microhardness is 2850 MPa. The obtained data can serve as the basis for predicting the properties of  $\text{EuLnCuS}_3$  compounds. Valence states for Eu (2+) and Er (3+) are proved both by the XRD and optical methods. Optical band gap was found to be 1.934 eV from diffuse reflectance spectrum.

**Keywords:** inorganic materials; thermochemistry; spectroscopy; magnetic measurements; optical spectroscopy; X-ray diffraction.

**1. Introduction**

Triple and quadruple chalcogenides of rare-earth elements have been intensively studied in recent years due to their specific properties, which make them promising materials in the field of infrared and nonlinear optics

[1]. They are important as refractory materials with semiconducting properties and promise high temperature superconductors [2]. Synthesis and study of the crystal structures of complex chalcogenides is an important step in the search for new materials with desirable properties [1].

Complex rare-earth chalcogenides  $ALnCuS_3$  and  $ALn_3CuS_6$  ( $A^{2+} = Pb, Eu, Sr, \text{ or } Ba$ ) have specific electric [1–7], thermal [8–12], magnetic [1,13–15], and optical [1,9,12,15] properties. X-ray powder diffraction analyses of the samples annealed at 1170 K indicated three types of orthorhombic crystal structures in the  $EuLnCuS_3$  ( $Ln = La\text{--}Ho, Tm\text{--}Lu$ ) series [13,16,17] (Table 1).

**Table 1**

The structural types (STs) of  $EuLnCuS_3$  ( $Ln = La\text{--}Lu$ ) compounds were determined in the samples annealed at 1170 K.

EuLnCuS <sub>3</sub> structural type												
La	Ce	Pr	Nd	Sm	Gd	Tb	Dy	Ho	Er	Tm	Yb	Lu
									-			

The background cell coloring denotes the structural type (ST) in which the  $EuLnCuS_3$  compound crystallizes: crosshatched cells –  $Eu_2CuS_3$  ST, dark gray cells –  $Ba_2MnS_3$  ST, horizontal-striped cells –  $KZrCuS_3$  ST, and hyphenated white cells – an undetermined ST.

The  $EuLnCuS_3$  ( $Ln = Tb, Dy, \text{ and } Tm$ ) compounds that contain magnetic  $Ln^{3+}$  ions manifest a ferrimagnetic transition at 5.4, 5.3, and 5.4 K, respectively; in the compounds containing nonmagnetic  $Ln^{3+}$  ions ( $Ln = Y, Eu, \text{ and } Lu$ ), ferromagnetic ordering of  $Eu^{2+}$  moments takes place at 3.4–4.4 K [13,14].

The  $ALnCuS_3$  ( $A = Sr, Eu; Ln = Gd, Dy, \text{ and } Ho$ ) compounds manifest three polymorphic transitions at temperatures above 1400 K upon heating and cooling as shown by differential scanning calorimetry (DSC) [8,18,19]. For  $EuHoCuS_3$ , the polymorphic transition temperatures and

enthalpies are  $T_{\alpha\leftrightarrow\beta}= 1516$  K,  $\Delta H_{\alpha\leftrightarrow\beta}=3.7$  kJ/mol;  $T_{\beta\leftrightarrow\gamma}=1562$  K,  $\Delta H_{\beta\leftrightarrow\gamma}=1.2$  kJ/mol; and  $T_{\gamma\leftrightarrow\delta} = 1591$  K,  $\Delta H_{\gamma\leftrightarrow\delta}= 2.2$  kJ/mol [18]. High-temperature polymorphs have not been obtained by cooling or quenching. The  $\text{EuLnCuS}_3$  compounds melt incongruently:  $\text{EuLaCuS}_3$  ( $1539\pm 4$  K),  $\text{EuCeCuS}_3$  ( $1524\pm 3$  K),  $\text{EuPrCuS}_3$  ( $1497\pm 3$  K),  $\text{EuNdCuS}_3$  ( $1470\pm 4$  K) [9, 17]),  $\text{EuGdCuS}_3$  ( $1720\pm 5$  K) [8],  $\text{EuHoCuS}_3$  ( $1721\pm 5$  K) [18] and  $\text{EuDyCuS}_3$  ( $1721\pm 4$  K) [19].

We failed to find any piece of data on the crystal structure, thermal, optical, or magnetic properties of  $\text{EuErCuS}_3$  in the literature. The lack of data related to the properties and physicochemical characteristics of the compound  $\text{EuErCuS}_3$  limits the definite anticipation of potential fields of its practical application.

The purposes of this research were: first, to prepare the compound  $\text{EuErCuS}_3$  and determine its structure, second, to characterize it by physicochemical methods, third, to determine its optical and magnetic properties. The special goal is related to the verification of valence states of two rare earth ions, Eu and Er in the crystal structure under investigation. It is known that most stable valence of RE ions is 3+, and if no precautions are taken, they tend to attain this valence state even while occupying sites with nominal valence 2+, due to inclusion of, e.g. oxygen-containing defects, like in the case of doping of fluorite crystals with RE. Some hosts are especially favorable for stabilizing divalent RE ions like single crystalline  $\alpha$ -SBO doped with europium. In the case of the crystal structure under consideration, i.e.,  $\text{EuErCuS}_3$ , the competition between Eu and Er for occupying either divalent or trivalent positions may be of interest. It must be noted that in earlier studied compounds (see references above) Eu is found to be in divalent state, in accordance with the additional stability of  $f^7$  shell of  $\text{Eu}^{2+}$  ion. In the compound under study the investigation of valence states of RE ions can be done with the help of XRD or optical spectroscopy.

## 2. Experimental

The compound  $\text{EuErCuS}_3$  was prepared by alloying a batch of composition  $2\text{EuS} : 1\text{Er}_2\text{S}_3 : 1\text{Cu}_2\text{S}$  [17–19].  $\text{Cu}_2\text{S}$  was prepared by heating the constituent elements (Cu (99.99 %, Red Chemist, Ltd., Russia) and S (99.99 %, the manufacturer is Komponent-reactive, Russia)) to 1420 K for 24 hours in an evacuated and sealed-off double-walled silica glass ampoule, followed by 30-min isothermal exposure at the same temperature. The  $\text{Cu}_2\text{S}$  sample prepared by the technique, described above is orthorhombic, space group is  $Ab2m$  [20], with the unit cell parameters  $a = 13.53(3)$  Å,  $b = 27.47(3)$  Å,  $c = 11.88(1)$  Å. The DSC curves for this sample featured peaks that corresponded to the polymorphic transitions  $\alpha\text{-Cu}_2\text{S} \rightarrow \beta\text{-Cu}_2\text{S}$  at 376 K and  $\beta\text{-Cu}_2\text{S} \rightarrow \gamma\text{-Cu}_2\text{S}$  at 708 K and the melting peak of the compound at 1402 K, in accordance with the research data [21]. Single-phase EuS and  $\text{Er}_2\text{S}_3$  samples were prepared from  $\text{Ln}_2\text{O}_3$  (99.99%, Red Chemist, Ltd., Russia) in the  $\text{H}_2\text{S}$  and  $\text{CS}_2$  flow at 1300 K [16,22–24].  $\delta\text{-Er}_2\text{S}_3$  is a monoclinic compound, space group is  $P2_1/m$  [25,26], with  $a = 17.42(2)$  Å,  $b = 3.976(4)$  Å,  $c = 10.04(1)$  Å,  $\beta = 98.5(5)^\circ$ . EuS is cubic, space group is  $Fm\bar{3}m$  [27,28], with  $a = 5.968(1)$  Å. According to the data of energy dispersive X-ray spectrometric analysis, the ratio of the rare-earth element and sulfur is  $m_{\text{found}}(\text{Eu}) = 82.7(7)$  mass. %,  $m_{\text{found}}(\text{S}) = 17.3(2)$  mass. % and  $m_{\text{found}}(\text{Er}) = 78.0(8)$  mass. %,  $m_{\text{found}}(\text{S}) = 21.7(2)$  mass. % respectively. The oxygen content in the test portion of the sample  $\text{Er}_2\text{S}_3$  was 0.3 mass. %.

A  $2\text{EuS}:1\text{Er}_2\text{S}_3:1\text{Cu}_2\text{S}$  batch was pounded in an agate mortar and then alloyed in a graphite crucible placed inside an argon (99.998%, the manufacturer of technical gases is “Kislorod-servis”, Russia)-filled silica glass reactor, or in an evacuate and sealed-off silica glass ampoule. The synthesized samples were annealed in evacuated and sealed-off silica glass ampoules at 1170 K for 1500 hours [16,29].

X-ray diffraction experiments were carried out by means of a DRON-7 diffractometer and a PANalytical X'Pert PRO diffractometer both equipped with a PIXcel detector (Fe-filtered  $\text{CoK}_\alpha$  radiation). The X-ray

diffraction patterns were scanned at 298 K over the angle range  $10^\circ \leq 2\theta \leq 125(145)$  with  $0.013^\circ$  steps; the total accumulation time was 13 h. Unit cell parameters were determined by the ITO program [30]. Apart from the major phase, the refined model included identified microimpurities: 1 mass. %  $\text{Er}_2\text{O}_2\text{S}$ . Phase identification was with reference to the ICDDPDF4+2012 file. The observed systematic absences showed that the  $\text{EuErCuS}_3$  structure (after annealing at 1170 K) belongs to space group *Pnma* (for general reflections  $hkl$ , no systematic absences were observed, so the unit cell is primitive; for reflections  $0kl$ :  $k + l = 2n$ ; for  $hk0$ :  $h = 2n$ ; for  $h00$ :  $h = 2n$ ; for  $0k0$ :  $k = 2n$ ; and for  $00l$ :  $l = 2n$ ). The dataset for the isostructural compound  $\text{Eu}_2\text{CuS}_3$  was used as reference model [31]. The crystal structure was specified by the difference derivative minimization (DDM) method [32] in the anisotropic approximation for all atoms with account for preferred orientation, anisotropic peak broadening, surface roughness and displacement ( $R_{\text{DDM}} = 5.3\%$ ;  $R_{\text{Bragg}} = 2.9\%$ ). The crystallographic data are referred to the data in Cambridge Crystallographic Data Centre (CCDC #1911666), that can be downloaded from the site ([www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif)). Crystal structures were visualized in the program package Diamond 3 [33].

The microstructural analysis of the polished samples was performed by means of metallographical microscope AxioVert.A1. Scanning electron microscopy (SEM) was performed on a JEOLJSM-6510 LV equipped with an energy dispersive spectrometer.

Differential scanning calorimetry experiments were carried out on a Setsys Evolution 1750 (TG–DSC 1600) with the aid of the PtRh 6%–PtRh 30% thermocouple. The complex was calibrated according to the data of melting temperatures and melting enthalpies of standard substances (Sn, Pb, Zn, Al, Ag, Au, Cu, and Pd). Prior to an experiment, the working chamber of the complex was evacuated and then filled with argon. The recording parameters were the following: the sample size: 100–110 mg, heating rate: 5



K/min, argon flow rate: 25 mL/min, and alundum crucible capacity: 100  $\mu$ L. The heat absorption onset temperature was determined as the intersection point of a tangent with the baseline in the program package Setsoft Software 2000 with a linear baseline from first to last point. The temperatures and enthalpies of the thermal events appearing in replica measurements are aligned with the thermoanalytical error bar. TG curves showed a 0.025 wt. % weight loss in a EuErCuS<sub>3</sub> sample in the range 1678–1745 K.

A durometric analysis of a polished sample was performed by the Vickers method on an HMV-G21 [34]. The exposure time was 15 s; the load was 10 kg-force (98.07 N).

The room-temperature magnetic properties of EuErCuS<sub>3</sub> were studied on a vibrating sample magnetometer with a Puzey electromagnet [35]. The sample weight was 0.0543 g. Low-temperature magnetic susceptibility was studied on a SQUID magnetometer [36] in a 10-Oe magnetic field. Temperature-dependent magnetic susceptibility was measured in the ZFC (zero-field cooling) and FC (nonzero-field cooling) modes. A magnetic moment versus magnetic field plot for EuErCuS<sub>3</sub> was constructed by 768 datapoints in the range from 0 to 9650 Oe. The magnetic field was varied in 10-20 Oe steps.

IR spectra in the range 600–50  $\text{cm}^{-1}$  were recorded with 2- $\text{cm}^{-1}$  resolution on a VERTEX 70V (BRUKER) FT-IR vacuum spectrometer equipped with a SiC IR source and an RT-DTGS detector with a polyethylene window and a T240/3wide-band amplifier. Prior to measurements the spectrometer was evacuated to a residual pressure of less than 0.2 gPa. A cast complex sulfide sample was pounded in an agate mortar; the thus-prepared powder was placed on a diamond crystal of a Platinum ATR single-reflection ATR accessory for measurements.

IR absorption spectra in the range 4000–400  $\text{cm}^{-1}$  were measured on a FTIR spectral Varian Excalibur HE 3600.

Raman spectra were excited by polarized 514.5-nm and 457.9-nm beams of a Spectra-Physics Stabilite 2017 200-mW argon laser (250  $\mu$ W on the test sample). The laser beam was focused on the test sample by an Olympus BX41 updated microscope through an Olympus MPlan 100x object lens with the digital aperture 0.9. The scattered beam was collected through the same object lens and targeted to the spectrometer. Spectra in the 180° (back-scattered) geometry were obtained on a Horiba Jobin Yvon T64000 spectrometer with a triple monochromator in the dispersion subtraction mode in the frequency range 15–3600  $\text{cm}^{-1}$ . The used detector was a liquid nitrogen-cooled CCD matrix. The focused laser beam diameter was  $\sim 2 \mu\text{m}$ .

The ab initio calculations of the  $\text{EuErCuS}_3$  crystal structure and phonon spectrum were carried out in the framework of density functional theory (DFT) [37] using the B3LYP exchange-correlation functional [38,39] to take into account both local and nonlocal Hartree–Fock exchanges. The calculations were carried out in the program CRYSTAL14 [40,41]. For europium and erbium, the ECP53MWB and ECP57MWB quasi-relativistic pseudo-potentials [42,43] were used with the attached valence basis set ECP53MWB and ECP57MWB-I, respectively [44]. The Gaussian primitives with exponents less than 0.1 were removed from the basis sets. For copper, the full-electron basis set [45] was used, available on the CRYSTAL program site as «Cu\_86-4111(41D)G\_doll\_2000» [41]. For sulfur, the DURAND pseudo-potential with the attached valence basis set was used [41,46]. The exponents in the two outer orbitals of the valence basis set were changed into 0.24 and 0.27. 125 IBZ points were used. The use of pseudo-potentials for the description of core electronic shells of rare-earth ions, the 4f shell inclusive, with the valence orbitals involved in chemical bonding described by valence basis sets, makes it possible to successfully reconstitute the lattice structure and lattice dynamics in the compounds that have a lanthanide ion sublattice [47,48]. The crystal structure was first calculated,

followed by phonon spectrum calculations for crystal structure optimization.

Calculation details are found elsewhere [47].

Diffuse reflection spectrum of  $\text{EuErCuS}_3$  was measured using Shimadzu UV-3600 spectrometer.

### 3. Results and discussion

#### 3.1. Crystal Structure

The  $\text{EuErCuS}_3$  diffraction pattern (Fig. 1) was indexed in terms of orthorhombic space group  $Pnma$ ,  $\text{Eu}_2\text{CuS}_3$  structural type, with the unit cell parameters  $a = 10.1005(2)$  Å,  $b = 3.91255(4)$  Å,  $c = 12.8480(2)$  Å;  $V = 507.737(14)$  Å<sup>3</sup>,  $Z = 4$ ,  $\rho_x = 6.266$  g/cm<sup>3</sup>. The unit cell parameters calculated in the DFT frame with the B3LYP functional ( $a = 10.126$  Å,  $b = 3.896$  Å,  $c = 12.600$  Å,  $V = 497.044$  Å<sup>3</sup>) correlated with the experimental values.

The  $\text{EuErCuS}_3$  structure is described by two-dimensional layers ( $\text{CuErS}_3$ ) in plane  $b$ – $a$  built of distorted tetrahedra  $\text{CuS}_4$  and octahedral  $\text{ErS}_6$ , with  $\text{Eu}^{2+}$  ions in between. The atomic coordinates and selected interatomic distances for  $\text{EuErCuS}_3$  are listed in Table 2 and Table 3, respectively. The selected bond angles are given in Table 4.

**Table 2.**

Atomic coordinates in the  $\text{EuErCuS}_3$  structure.

Atom	Wyck.	Site	x	y	z
Eu	4c	.m.	0.76479(16)	0.25	0.00169(9)
Er	4c	.m.	0.01020(11)	0.25	0.74489(9)
Cu	4c	.m.	0.24037(24)	0.25	0.22147(14)
S1	4c	.m.	0.05556(47)	0.25	0.11536(34)
S2	4c	.m.	0.42054(49)	0.25	0.10848(35)
S3	4c	.m.	0.25808(44)	0.25	0.82710(28)

**Table 3.**

Interatomic distances (d) in the  $\text{EuErCuS}_3$  structure.

Bond	d, Å	Bond	d, Å	Bond	d, Å
Eu—S1 <sup>i</sup>	3.2800(49)	Er—S1 <sup>iv</sup>	2×2.7372(32)	Cu—S1	2.312(5)
Eu—S1 <sup>ii</sup>	2×3.0629(37)	Er—S2 <sup>v</sup>	2×2.7181(33)	Cu—S2	2.328(5)

Eu—S2 <sup>ii</sup>	2×3.0552(39)	Er—S3	2.7174(45)	Cu—S3 <sup>vii</sup>	2×2.3810(23)
Eu—S3 <sup>iii</sup>	2×2.9529(29)	Er—S3 <sup>vi</sup>	2.7093(45)	<Cu—S>	2.350(2)
<Eu—S>	3.060(2)	<Er—S>	2.723(2)		

The parenthesized values are mean interatomic distances. Symmetric positions: (i) 1+x, y, z; (ii) 1-x, -0.5+y, -z; (iii) 1-x, -0.5+y, 1-z; (iv) -x, -0.5+y, 1-z; (v) 0.5-x, -y, 0.5+z; (vi) -0.5+x, 0.5-y, 1.5-z; (vii) 0.5-x, -y, -0.5+z; (viii) 1-x, 0.5+y, -z; (ix) 1-x, 0.5+y, 1-z; (x) -x, 0.5+y, 1-z; (xi) 0.5-x, 1-y, 0.5+z; and (xii) 0.5-x, 1-y, -0.5+z

**Table 4.**

Selected bond angles in the EuErCuS<sub>3</sub> structure.

Angle	$\omega$ , deg	Angle	$\omega$ , deg
S1 <sup>i</sup> —Eu—S1 <sup>ii</sup>	71.83(11)	S1 <sup>iv</sup> —Er—S2 <sup>v</sup>	88.34(10)
S1 <sup>i</sup> —Eu—S2 <sup>ii</sup>	139.01(7)	S1 <sup>iv</sup> —Er—S2 <sup>xi</sup>	178.90(14)
S1 <sup>i</sup> —Eu—S3 <sup>iii</sup>	74.83(11)	S1 <sup>iv</sup> —Er—S3	88.20(12)
S1 <sup>ii</sup> —Eu—S1 <sup>viii</sup>	79.39(11)	S1 <sup>iv</sup> —Er—S3 <sup>vi</sup>	89.76(12)
S1 <sup>ii</sup> —Eu—S2 <sup>ii</sup>	74.13(11)	S2 <sup>v</sup> —Er—S2 <sup>xi</sup>	92.06(14)
S1 <sup>ii</sup> —Eu—S2 <sup>viii</sup>	122.99(12)	S2 <sup>v</sup> —Er—S3	90.77(12)
S1 <sup>ii</sup> —Eu—S3 <sup>iii</sup>	89.37(9)	S2 <sup>v</sup> —Er—S3 <sup>vi</sup>	91.25(12)
S1 <sup>ii</sup> —Eu—S3 <sup>ix</sup>	146.64(13)	S3—Er—S3 <sup>vi</sup>	177.09(9)
S2 <sup>ii</sup> —Eu—S2 <sup>viii</sup>	79.63(12)	S1—Cu—S2	105.28(18)
S2 <sup>ii</sup> —Eu—S3 <sup>iii</sup>	82.7(1)	S1—Cu—S3 <sup>vii</sup>	109.97(13)
S2 <sup>ii</sup> —Eu—S3 <sup>ix</sup>	136.17(13)	S2—Cu—S3 <sup>vii</sup>	110.51(13)
S3 <sup>iii</sup> —Eu—S3 <sup>ix</sup>	82.98(10)	S3 <sup>vii</sup> —Cu—S3 <sup>xii</sup>	110.50(16)
S1 <sup>iv</sup> —Er—S1 <sup>x</sup>	91.24(14)		

Bond valence sum calculation is sometimes used for determination of valence states from the XRD data. Commonly it is considered as indirect method with low fidelity. Nevertheless, we tried these calculations for EuErCuS<sub>3</sub> in view of problematic valence states of metal ions. To our surprise, the conformity in the case of this specific material appeared to be almost perfect. According to our bond valence sum calculations with the parameters outlined in [49] as presented in Table 5, the valence states of Eu, Er and Cu ions in EuErCuS<sub>3</sub> are close to 2, 3 and 1, respectively. Later the optical evidence for valence state of RE ions will be discussed.

**Table 5.** Bond valence calculations for Eu, Er and Cu in  $\text{EuErCuS}_3$ .

Bond	Dist., Å	R, Å	B	BVal
Eu—S3	2.953	2.584	0.37	0.369
Eu—S3	2.953	2.584	0.37	0.369
Eu—S2	3.055	2.584	0.37	0.280
Eu—S2	3.055	2.584	0.37	0.280
Eu—S1	3.063	2.584	0.37	0.274
Eu—S1	3.063	2.584	0.37	0.274
Eu—S1	3.281	2.584	0.37	0.152
			Sum	1.998
Er—S3	2.709	2.460	0.37	0.510
Er—S3	2.718	2.460	0.37	0.498
Er—S2	2.718	2.460	0.37	0.498
Er—S2	2.718	2.460	0.37	0.498
Er—S1	2.737	2.460	0.37	0.473
Er—S1	2.737	2.460	0.37	0.473
			Sum	2.950
Cu—S1	2.311	1.898	0.37	0.328
Cu—S2	2.327	1.898	0.37	0.314
Cu—S3	2.381	1.898	0.37	0.271
Cu—S3	2.381	1.898	0.37	0.271
			Sum	1.183

A  $\text{EuErCuS}_3$  powder consists of planar particles with linear sizes of 1 to 10  $\mu\text{m}$  (Fig. 3). Energy dispersive X-ray spectrometric analysis was performed at 5 different locations on the sample surface. The chemical composition of the sample agrees with the theoretical contents of the elements.

### 3.2. Thermal Properties and Microhardness

The DSC heating curves for a polycrystalline  $\text{EuErCuS}_3$  sample feature three endotherms in the range 1524-1610 K induced by first-order phase transformations, namely, polymorphic transitions (Fig. 3). Similar transitions were detected in  $\text{ALnCuS}_3$  ( $A = \text{Sr}$  or  $\text{Eu}$ ) isostructural compounds [8,18]. The polymorphs of the compound are denoted in the increasing order of temperatures like in the case of  $\text{EuErCuS}_3$ . The temperatures and enthalpies of phase transitions, determined by the heating curves, are listed in the Table 6.

**Table 6.**Physicochemical characteristics of  $\text{EuErCuS}_3$ 

Temperatures (K) and enthalpies ( $\text{kJ}\cdot\text{mol}^{-1}$ ) of phase transitions								
$T_{\alpha\leftrightarrow\beta}$	$\Delta H_{\alpha\leftrightarrow\beta}$	$T_{\beta\leftrightarrow\gamma}$	$\Delta H_{\beta\leftrightarrow\gamma}$	$T_{\gamma\leftrightarrow\delta}$	$\Delta H_{\gamma\leftrightarrow\delta}$	$T_{\text{cr}}$	$\Delta H_{\text{cr}}$	
1524 $\pm$ 2	2.3 $\pm$ 0.2	1575 $\pm$ 3	0.7 $\pm$ 0.1	1602 $\pm$ 3	1.3 $\pm$ 0.1	1735 $\pm$ 10*	-3.5 $\pm$ 0.3*	
$\chi_{\text{obs}}\cdot 10^7,$ $\text{m}^3\cdot\text{mol}^{-1}$	$\text{C}\cdot 10^4,$ $\text{m}^3\cdot\text{K}\cdot\text{mol}^{-1}$		Band gap, eV		Sample color	H, MPa	$T_{\text{c}},\text{K}$	
	obs	calc	obs	calc			obs	calc
7.99	2.45	2.43	1.93	2.56	Red- brown	2850 $\pm$ 150	4.8 $\pm$ 0.2	5.0

\*As shown by DSC cooling curves.

The phase transitions occur within a narrow temperature range less than 10 K. The thermal features are completely reproduced upon cooling, so the transitions may be regarded to be rapid. Quenching of samples to aqueous NaCl solutions failed to yield high-temperature phases of the compound.

The  $\text{EuErCuS}_3$  compound is formed in  $\text{EuS-CuErS}_2$  quasi-binary section in  $\text{Cu}_2\text{S-Er}_2\text{S}_3\text{-EuS}$  triangle.  $\text{EuErCuS}_3$  compound melts incongruently. According to the XRD and SEM data, the single-phase samples of compound  $\text{EuErCuS}_3$  having been crystallized from the melt during DSC were found to change into the three-phase compounds. The microstructure of the sample contains primary brown crystals of the phase of  $\text{EuS}$  ( $H = 1300$  MPa) surrounded by the  $\text{EuErCuS}_3$  phase crystals being of light brown colour ( $H = 2850$  MPa). In the sample the eutectic consisting of elongated grains of the  $\text{EuErCuS}_3$  and  $\text{CuErS}_2$  phases was observed between the grains of the  $\text{EuErCuS}_3$  phase. The diffraction peaks of all phases were detected on a diffraction pattern. The temperature of incongruent melting of the compound with change in composition of the samples remains constant. The Tamman triangle indicates that thermal effect of incongruent melting belongs to  $\text{EuErCuS}_3$  compound. This phase transformation scheme, i.e.  $\text{EuErCuS}_3$  (cr.)  $\rightleftharpoons$   $\text{EuS}$  (cr.) + l is indicative of incongruent melting. Since the thermal effect of incongruent melting on the heating curve is blurry, both the temperature of

the starting phase transition and the enthalpy were determined from the cooling curve. The exothermic effect of the solidification, produced in the course of cooling ( $\Delta H = - 9.8 \text{ J}\cdot\text{g}^{-1}$ ), was tentatively divided into two peaks ( $\Delta H = - 2.6 \text{ J/g}$  и  $\Delta H = - 7.2 \text{ J}\cdot\text{g}^{-1}$ ). The first exothermic peak, turning up in the temperature interval 1735-1740 K characterizes the formation of the primary crystals EuS ( $\Delta H = - 0.5 \text{ kJ}\cdot\text{mol}^{-1}$ ), the second thermal effect shows the result of interaction of the formed crystals EuS with the liquid with the formation of the EuErCuS<sub>3</sub> compound ( $\Delta H = - 3.5 \text{ kJ}\cdot\text{mol}^{-1}$ ). Since under cooling we can observe the supercooling effect, the temperature data concerning this phase transition are given tentatively.

The microhardness value measured for EuErCuS<sub>3</sub> (Table 6) exceeds the microhardness of isoformula compounds (for EuLaCuS<sub>3</sub>, H = 2050 MPa [17]), in correlation with the decreasing Ln<sup>3+</sup> radii.

### 3.3. Magnetic Properties

The 298 K magnetic moment of the test sample rises linearly with field intensity, a trend typical of a paramagnetic state (Fig. 4). The molar magnetic susceptibility  $\chi$  was calculated from the plot (Fig. 4, Table 6).

The temperature-dependent magnetic susceptibility below 14 K shows a transition to an ordered anisotropic magnetic structure at  $4.8\pm 0.2$  K (Fig.5). The reciprocal magnetic susceptibility near the phase transition departs from the linear trend; this departure is typical for ferrimagnets and correlates with a similar behavior observed for EuGdCuS<sub>3</sub> (where the transition temperature is 5.37 K [13]).

In Néel' theory, the temperature-dependent reciprocal magnetic susceptibility for a two-sublattice ferrimagnet is described by the relationship [50]

$$\frac{1}{\chi} = \frac{T}{C} + \frac{1}{\chi_0} - \frac{\sigma}{T - \theta} \quad (1)$$



Where  $C$  is the Curie constant; and  $x_0$ ,  $\sigma$ , and  $\theta$  are the fitting parameters (including  $C$ ).

Processing of the experimental data (Fig.5) gave a value of  $2.45 \cdot 10^{-4} \text{ m}^3 \cdot \text{K} \cdot \text{mol}^{-1}$  for  $C$  (for  $\text{EuGdCuS}_3$ ,  $C = 1.95 \cdot 10^{-4} \text{ m}^3 \cdot \text{K} \cdot \text{mol}^{-1}$  [13]). The relationship  $C = \mu_0 \frac{N_A}{3k} \left( \mu_{\text{Eu}}^2 + \mu_{\text{Er}}^2 \right)$  (where  $\mu$  is the magnetic moment equal to  $7.94 \mu_{\text{B}}$  and  $9.58 \mu_{\text{B}}$  for  $\text{Eu}^{2+}$  and  $\text{Er}^{3+}$ , respectively [51,52]) gave  $C = 2.43 \cdot 10^{-4} \text{ m}^3 \cdot \text{K} \cdot \text{mol}^{-1}$  for the paramagnetic state of  $\text{EuErCuS}_3$ . The thus-calculated values of the Curie constant were used to calculate  $\chi$  for 298 K:  $8.23 \cdot 10^{-7}$  and  $8.19 \cdot 10^{-7} \text{ m}^3 \cdot \text{mol}^{-1}$ ; these  $\chi$  values coincide, to within 3%, with the experimentally determined value  $\chi = 7.99 \cdot 10^{-7} \text{ m}^3 \cdot \text{mol}^{-1}$  (for  $\text{EuGdCuS}_3$ ,  $\chi \approx 6.3 \cdot 10^{-7} \text{ m}^3 \cdot \text{mol}^{-1}$  [13]). The calculations of the Curie temperature (at which  $\frac{1}{x} = 0$ ) through the parameters ( $C$ ,  $x_0$ ,  $\sigma$ , and  $\theta$ ) of model (1) by the relationship (2) give  $T_c = 5.0 \text{ K}$ .

$$T_c = \theta - \frac{C}{x_0} + \frac{1}{2} \sqrt{\left( \theta - \frac{C}{x_0} \right)^2 + 4C \left( \frac{\theta}{x_0} + \sigma \right)} \quad (2)$$

### 3.4. Vibrational Spectroscopy

Figure 6 shows Raman spectra recorded at various excitation wavelengths. The noticeable differences between the observed spectra indicate that luminescence spectra were recorded together with the vibrational spectrum. The joint analysis of these spectra makes it possible to exclude the luminescence contribution and recognize the lines that reliably belong to the vibrational frequencies of the crystal unit cell.

Selection rules were calculated for interpreting the observed vibrational spectra. The result is shown in Table 7. The crystal belongs to space group  $Pnma$ . According to the calculations, 36 modes were expected to appear in the Raman spectrum and 27 modes in IR absorption spectra.



**Table 7.**

Irreducible representations, classification of modes, and Raman tensors for EuErCuS<sub>3</sub> (space group *Pnma*, No.62)

Atom	Phonon modes at point G		
Eu	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
Er	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
Cu	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
S	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
S	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
S	2A <sub>g</sub> +A <sub>u</sub> +B <sub>1g</sub> +2B <sub>1u</sub> +2B <sub>2g</sub> +B <sub>2u</sub> +B <sub>3g</sub> +2B <sub>3u</sub>		
Classification of modes			
G <sub>ram</sub> =12A <sub>g</sub> + 6B <sub>1g</sub> + 12B <sub>2g</sub> + 6B <sub>3g</sub>			
G <sub>ir</sub> =11B <sub>1u</sub> + 5B <sub>2u</sub> + 11B <sub>3u</sub> (acoustic modes are not included)			
G <sub>ac</sub> =B <sub>1u</sub> + B <sub>2u</sub> + B <sub>3u</sub>			
G <sub>meh</sub> = 12A <sub>g</sub> + 6A <sub>u</sub> + 6B <sub>1g</sub> + 12B <sub>1u</sub> + 12B <sub>2g</sub> + 6B <sub>2u</sub> + 6B <sub>3g</sub> + 12B <sub>3u</sub>			
Raman tensors			
A <sub>g</sub> $\begin{bmatrix} 0 & d & 0 \\ d & 0 & 0 \\ 0 & 0 & 0 \end{bmatrix}$	B <sub>1g</sub> $\begin{bmatrix} 0 & 0 & e \\ 0 & 0 & 0 \\ e & 0 & 0 \end{bmatrix}$	B <sub>2g</sub> $\begin{bmatrix} 0 & 0 & 0 \\ 0 & 0 & f \\ 0 & f & 0 \end{bmatrix}$	B <sub>3g</sub> $\begin{bmatrix} a & 0 & 0 \\ 0 & b & 0 \\ 0 & 0 & c \end{bmatrix}$

Lattice dynamics calculations were performed for providing the full-value interpretation of the observed vibrational spectra.

Referring to Fig. 6, we note that luminescence contribution observed in the range above 310 cm<sup>-1</sup> under 514.5 nm excitation is easily assignable to the transition from excited electronic energy level <sup>2</sup>H<sub>11/2</sub> of Er<sup>3+</sup> ion to the ground state. Luminescence from <sup>4</sup>S<sub>3/2</sub> and <sup>4</sup>F<sub>9/2</sub> levels of Er<sup>3+</sup> ion is also detected though it is positioned outside the Raman spectrum region and is visible in Fig.6., while no detectable luminescence from excited states of Eu<sup>3+</sup> ion were observed. Under 457.9 nm excitation, Raman peaks are preserved in the spectrum, while <sup>2</sup>H<sub>11/2</sub> peaks completely disappear. On the contrary, for 457.9 nm excitation, the luminescence from <sup>4</sup>F<sub>7/2</sub> state of Er<sup>3+</sup> ions is in the low wave number part of Raman spectrum. Presence of luminescence from several Er<sup>3+</sup> excited levels This is the spectroscopic evidence of the purity of valence states Er<sup>3+</sup> and Eu<sup>2+</sup> earlier derived from the XRD data.

### 3.5 Ab initio Lattice Dynamics Calculations and the Interpretation of Observed Vibrational Spectra

The types of phonon modes were determined and the involvement of ions in vibrational modes was evaluated based on the displacement vectors derived from ab initio calculations (Tables 8-10). In the IR spectrum (Table 8), rare-earth ions are appreciably involved in low-frequency modes. Europium is involved in the modes with frequencies up to  $133\text{ cm}^{-1}$ . The  $B_{2u}$  mode at  $93\text{ cm}^{-1}$  involves both Eu and Er. Erbium is involved in the modes with frequencies of up to  $145\text{ cm}^{-1}$ . Copper vibrations appear in the IR modes with frequencies of up to  $294\text{ cm}^{-1}$ . The greatest involvement of copper is in the  $117.6\text{ cm}^{-1}(B_{1u})$ ,  $118.1\text{ cm}^{-1}(B_{2u})$ , and  $129\text{ cm}^{-1}(B_{3u})$  modes. Sulfur is involved in all IR modes. The  $320.5\text{ cm}^{-1}(B_{1u})$  and  $324\text{ cm}^{-1}(B_{3u})$  high-frequency IR modes mostly arise from sulfur vibrations. Three more modes can be distinguished at  $243$ ,  $245$ , and  $258\text{ cm}^{-1}$  ( $B_{2u}$ ,  $B_{1u}$ , and  $B_{3u}$ , respectively), also arising from sulfur vibrations. Thus, the IR modes that arise from sulfur vibrations can be solely distinguished. For other ions, such modes are difficult to distinguish; every mode involves several ions of different types. For example, the low-frequency IR mode ( $B_{3u}$ ,  $62\text{ cm}^{-1}$ ) involves all ions (Eu, Er, Cu, and S), and it is difficult to distinguish the dominant contribution from any one of them. However, this mode has a low intensity. According to the calculations, the  $212.9\text{ cm}^{-1}(B_{2u})$ ,  $213.4\text{ cm}^{-1}(B_{3u})$ , and  $259\text{ cm}^{-1}(B_{1u})$  modes have high intensities. Sulfur is substantially involved in these modes.

**Table 8.**

Calculated IR vibrational frequencies ( $\nu_{\text{calc}}$ ,  $\text{cm}^{-1}$ ) and intensities ( $I_{\text{calc}}$ ,  $\text{km/mol}$ ) in  $\text{EuErCuS}_3$ .

Vibrations	$\nu_{\text{calc}}$	$I_{\text{calc}}$	Involved ions	Vibrations	$\nu_{\text{calc}}$	$I_{\text{calc}}$	Involved ions
$B_{3u}$	62	36,09	Eu, Er, Cu, S1, S2, S3	$B_{2u}$	243	640,72	S1, S2 <sup>S</sup>

B <sub>1u</sub>	65	1,82	Eu <sup>S</sup> , S1, S2	B <sub>1u</sub>	245	69,05	S1 <sup>S</sup> , S2, S3
B <sub>2u</sub>	93	11,69	Eu <sup>S</sup> , Er <sup>S</sup> , Cu, S2 <sup>W</sup> , S3	B <sub>3u</sub>	258	506,11	S1, S2, S3 <sup>S</sup>
B <sub>3u</sub>	100	28,43	Eu, Er, Cu, S1, S2, S3	B <sub>1u</sub>	259	1447,84	Er <sup>W</sup> , Cu <sup>W</sup> , S1, S2, S3
B <sub>3u</sub>	105	62,48	Eu <sup>S</sup> , Er, Cu, S1, S2, S3	B <sub>3u</sub>	269	37,9	Cu, S1, S2, S3 <sup>S</sup>
B <sub>1u</sub>	112	25,84	Er, Cu, S1, S2, S3 <sup>W</sup>	B <sub>1u</sub>	279	106,85	Cu, S1, S2, S3 <sup>S</sup>
B <sub>1u</sub>	117,6	0,18	Eu, Er, Cu <sup>S</sup> , S1, S2	B <sub>3u</sub>	290	0,62	Cu, S1, S2 <sup>S</sup> , S3
B <sub>2u</sub>	118,1	47,99	Eu, Cu <sup>S</sup> , S3	B <sub>2u</sub>	294	251,33	Cu, S3 <sup>S</sup>
B <sub>3u</sub>	123,6	10,73	Eu, Cu, S1, S2	B <sub>1u</sub>	300	10,08	S1, S2 <sup>S</sup> , S3 <sup>S</sup>
B <sub>3u</sub>	129	148,97	Er, Cu <sup>S</sup> , S1, S2, S3	B <sub>1u</sub>	309	20,55	Cu <sup>W</sup> , S1 <sup>S</sup> , S2, S3
B <sub>1u</sub>	133	430,77	Eu <sup>S</sup> , Er, Cu, S1, S2	B <sub>3u</sub>	311	14,18	Cu <sup>W</sup> , S1, S2 <sup>S</sup> , S3
B <sub>1u</sub>	145	1,66	Er <sup>S</sup> , S1, S2, S3	B <sub>1u</sub>	320,5	12,41	S1, S2, S3 <sup>S</sup>
B <sub>2u</sub>	212,9	1950,47	Er <sup>W</sup> , S1, S2	B <sub>3u</sub>	324	0,16	S1 <sup>S</sup> , S2, S3 <sup>S</sup>
B <sub>3u</sub>	213,4	2113,62	Er <sup>W</sup> , Cu <sup>W</sup> , S1, S2, S3				

Notations: «s» stands for a strong and «w» for a weak displacement of ions involved in the mode

According to the calculations, the lowest-frequency Raman mode (A<sub>g</sub>, 31 cm<sup>-1</sup>) considerably involves erbium and europium (Table 9), i.e. considerable involvement of erbium is in the first four low-frequency modes at 31 cm<sup>-1</sup> (A<sub>g</sub>), 47 cm<sup>-1</sup> (A<sub>g</sub>), 56 cm<sup>-1</sup> (B<sub>1g</sub>), and 67.8 cm<sup>-1</sup> (B<sub>3g</sub>) and in two higher frequency B<sub>2g</sub> modes at 95 and 160 cm<sup>-1</sup>, while in the Raman modes with frequencies higher than 160 cm<sup>-1</sup>, involvement of erbium is insignificant. Europium is strongly involved in the modes with frequencies of up to 86 cm<sup>-1</sup>; its involvement in higher-frequency modes is far weaker and is insignificant only below 160 cm<sup>-1</sup>. Thus, both erbium and europium appear in the modes with frequencies of up below 160 cm<sup>-1</sup>. Europium is the major participant in the B<sub>3g</sub> mode at 67 cm<sup>-1</sup> (Fig. 6), while in the B<sub>2g</sub> mode at 93 cm<sup>-1</sup>, erbium is strong. A considerable involvement of copper is in the modes with frequencies of up to 128 cm<sup>-1</sup>. In the modes with frequencies higher than 218 cm<sup>-1</sup>, copper involvement is weak. Sulfur is involved in all Raman modes. However, modes dominated by sulfur ions appear at 230 cm<sup>-1</sup> (B<sub>1g</sub>), 244 cm<sup>-1</sup> (B<sub>3g</sub>), 274 cm<sup>-1</sup> (A<sub>g</sub>), 284 cm<sup>-1</sup> (B<sub>3g</sub>).

The  $A_u$  modes, which are IR- and Raman-inactive, were also obtained by the calculations (Table 10). In the low-frequency  $A_u$  mode ( $68.5 \text{ cm}^{-1}$ ), involvement of erbium considerable; erbium is also involved in the third lowest frequency mode ( $111 \text{ cm}^{-1}$ ). In the  $80.5\text{-cm}^{-1}$  mode europium appears. The  $A_u$  modes with frequencies higher than  $111 \text{ cm}^{-1}$  almost do not involve rare-earth ions, however, the involvement of sulfur is considerable.

**Table 9.**

Calculated Raman vibrational frequencies ( $v_{\text{calc}}$ ,  $\text{cm}^{-1}$ ) in  $\text{EuErCuS}_3$ .

Vibrations	$v_{\text{calc}}$	Involved ions	Vibrations	$v_{\text{calc}}$	Involved ions
$A_g$	31	$\text{Eu}^{\text{S}}, \text{Er}^{\text{S}}, \text{Cu}, \text{S1}, \text{S2}^{\text{S}}, \text{S3}$	$B_{3g}$	216,5	$\text{S1}^{\text{S}}, \text{S2}$
$A_g$	47	$\text{Eu}, \text{Er}^{\text{S}}, \text{Cu}^{\text{S}}, \text{S1}, \text{S2}, \text{S3}^{\text{S}}$	$B_{1g}$	216,6	$\text{S1}^{\text{S}}, \text{S2}, \text{S3}$
$B_{1g}$	56	$\text{Er}^{\text{S}}, \text{Cu}, \text{S1}, \text{S2}, \text{S3}$	$A_g$	218	$\text{Er}^{\text{W}}, \text{Cu}, \text{S1}^{\text{S}}, \text{S2}^{\text{S}}, \text{S3}$
$B_{3g}$	67,8	$\text{Eu}, \text{Er}^{\text{S}}, \text{Cu}, \text{S1}, \text{S2}, \text{S3}$	$B_{1g}$	246	$\text{S1}, \text{S2}^{\text{S}}$
$A_g$	76	$\text{Eu}^{\text{S}}, \text{Er}^{\text{W}}, \text{Cu}^{\text{S}}, \text{S1}, \text{S2}, \text{S3}$	$B_{2g}$	247	$\text{Cu}^{\text{W}}, \text{S1}^{\text{S}}, \text{S2}, \text{S3}$
$B_{3g}$	77	$\text{Eu}^{\text{S}}, \text{Er}, \text{Cu}, \text{S1}, \text{S2}^{\text{W}}, \text{S3}$	$B_{3g}$	249	$\text{S1}, \text{S2}^{\text{S}}$
$B_{2g}$	79	$\text{Eu}^{\text{S}}, \text{Er}, \text{Cu}^{\text{W}}, \text{S1}, \text{S2}, \text{S3}$	$B_{2g}$	255	$\text{Cu}^{\text{W}}, \text{S1}, \text{S2}^{\text{S}}, \text{S3}$
$B_{1g}$	80,3	$\text{S2}, \text{S3}$	$B_{2g}$	257	$\text{S1}, \text{S2}, \text{S3}^{\text{S}}$
$B_{2g}$	86	$\text{Eu}^{\text{S}}, \text{Cu}, \text{S1}, \text{S2}^{\text{W}}, \text{S3}$	$A_g$	270	$\text{Cu}, \text{S1}, \text{S2}^{\text{W}}, \text{S3}^{\text{S}}$
$B_{2g}$	95	$\text{Eu}^{\text{S}}, \text{S2}$	$A_g$	277	$\text{S1}^{\text{S}}, \text{S2}^{\text{S}}$
$B_{1g}$	115,8	$\text{Er}^{\text{S}}, \text{Cu}, \text{S1}, \text{S2}, \text{S3}$	$B_{3g}$	291	$\text{Cu}^{\text{W}}, \text{S3}^{\text{S}}$
$B_{2g}$	116,3	$\text{Eu}^{\text{W}}, \text{Er}^{\text{W}}, \text{Cu}^{\text{S}}, \text{S3}$	$B_{1g}$	296	$\text{Cu}^{\text{W}}, \text{S3}^{\text{S}}$
$B_{3g}$	117,9	$\text{Er}^{\text{W}}, \text{Cu}^{\text{S}}, \text{S2}$	$B_{2g}$	302	$\text{Cu}^{\text{W}}, \text{S1}, \text{S2}^{\text{S}}, \text{S3}^{\text{S}}$
$A_g$	122	$\text{Eu}, \text{Cu}^{\text{S}}, \text{S3}$	$B_{2g}$	303	$\text{S1}^{\text{S}}, \text{S2}, \text{S3}^{\text{S}}$
$B_{2g}$	123,9	$\text{Eu}, \text{Er}, \text{Cu}, \text{S1}, \text{S2}$	$A_g$	317	$\text{Cu}^{\text{W}}, \text{S1}, \text{S2}^{\text{S}}, \text{S3}$
$A_g$	128	$\text{Cu}^{\text{S}}, \text{S1}^{\text{S}}, \text{S3}$	$B_{2g}$	320,7	$\text{S1}^{\text{S}}, \text{S2}, \text{S3}^{\text{S}}$
$A_g$	137	$\text{Eu}, \text{Er}^{\text{W}}, \text{Cu}^{\text{S}}, \text{S2}, \text{S3}$	$A_g$	325	$\text{S1}^{\text{S}}, \text{S2}, \text{S3}$
$B_{2g}$	160	$\text{Eu}, \text{Er}, \text{Cu}, \text{S1}, \text{S2}$	$B_{2g}$	328	$\text{Cu}^{\text{W}}, \text{S1}, \text{S2}^{\text{S}}, \text{S3}$
		$\text{Eu}, \text{Er}^{\text{S}}, \text{S1}^{\text{W}}, \text{S2}^{\text{W}}$			

**Table 10.**

Vibrational frequencies ( $v_{\text{calc}}$ ,  $\text{cm}^{-1}$ ) of Raman silent modes in  $\text{EuErCuS}_3$

Vibrations	$v_{\text{calc}}$	Involved ions
$A_u$	68,5	$\text{Er}^{\text{S}}, \text{Cu}^{\text{W}}, \text{S1}, \text{S2}, \text{S3}^{\text{W}}$
$A_u$	80,5	$\text{Eu}^{\text{S}}, \text{Er}^{\text{W}}, \text{Cu}, \text{S2}^{\text{W}}, \text{S3}$
$A_u$	111	$\text{Eu}, \text{Er}^{\text{S}}, \text{S3}$

$A_u$	211	$S1^S, S2, S3$
$A_u$	244	$S1^S, S2$
$A_u$	292	$Cu^W, S3^S$

A comparison of the vibrational frequencies of Raman- and IR-active modes calculated in terms of DFT with the B3LYP functional with the experimental data appear in Figs. 6 and 7.

The calculated IR absorption spectrum corresponds with the observed one. The low-frequency IR modes involve all ions (Eu, Er, Cu, and S), and it is difficult to distinguish the dominant contribution from any one of them. The strongest lines, according to the calculations, are related to sulfur vibrations and appear in the range from 210 to 260  $\text{cm}^{-1}$ . The low-frequency Raman vibrations are also related to the vibrations of all ions (lattice vibrations). The vibrations in the range 67-300  $\text{cm}^{-1}$  have been identified. According to the calculations, the high-frequency modes are associated with strong displacements of sulfur ions, so the high-frequency vibrations that emerge in the observed spectrum in the range 230 - 300  $\text{cm}^{-1}$  are assigned to the vibrations of sulfur ions.

### 3.6. Electronic Structure Calculations and Bandgap Measurement

The band structure and the density of states obtained in terms of DFT with the B3LYP functional are shown in the Fig. 8. The path in the Brillouin zone is plotted through the most highly symmetric points for the orthorhombic lattice. The path is made through  $\Gamma$ -X-Z-U-Y-S-T-R- $\Gamma$ . The coordinates of points are (0,0,0), (1/2,0,0), (0,0,1/2), (1/2,0,1/2), (0,1/2,0), (1/2,1/2,0), (0,1/2,1/2), (1/2,1/2,1/2), (0,0,0) respectively. Bilbao Crystallographic Server was used. Since for europium and erbium pseudo-potentials that replaced their core shells including 4f were used the band structure do not include 4f states. The bandgap was calculated to be 2.56 eV. The bandgap was defined as the difference in energy between the top of the valence band and the bottom of the conduction band (it is "HOMO-LUMO"

gap). The bandgap is direct ( $\Gamma$ - $\Gamma$ ). The calculation was carried out for the ideal crystal structure. In this case the  $f$ - orbitals of rare-earth ions were replaced by a pseudopotential. The difference between the measured (1.934 eV) and calculated (2.56 eV) forbidden gap values may be due to these facts. (The impurity of  $\text{Er}_2\text{O}_2\text{S}$  (1%) is present in the sample. According to experimental data, the band gap value of  $\text{Er}_2\text{O}_2\text{S}$  is about 4 eV [53]. Therefore the difference between the measured and calculated band gap values cannot be explained by the presence of this impurity.)

The projected DOS onto the whole set of atomic orbitals of an Eu, Er, Cu and S atoms was calculated near to bandgap (Fig. 8C). According to the calculations, the DOS of sulfur locate near to top of valence band and bottom of conduction band. The DOS of rare-earth and copper locate near to top of valence band.  $\text{EuErCuS}_3$  is a mid-gap, direct-bandgap semiconductor.

Fig. 9 presents Kubelka-Munk function determined according to the measured diffuse reflection spectrum of  $\text{EuErCuS}_3$ . The agreement between the experimental value of  $E_g$  and the calculated one is not perfect, however, it can be considered as a satisfactory one. Additionally, the position of  $H_{13/2}$  energy level of  $\text{Er}^{3+}$  ion within the bandgap can be identified from the the data of reflectance spectra. This energy level is observable as the narrow peak at the left side of Kubelka-Munk function, and the maximum of this peak is at 1.546 micron ( $6468 \text{ cm}^{-1}$ ), approximately in the same region where Er luminescence of Er ion is observed in oxides [54].

#### 4. Conclusions

This article addresses the synthesis, structure, optical, magnetic, durometric, and thermal properties of the new complex sulfide  $\text{EuErCuS}_3$ . The compound crystallizes in a  $\text{Eu}_2\text{CuS}_3$ -type structure, which is typical for the  $\text{EuLnCuS}_3$  compounds that contain mid-series lanthanides ranged from samarium to erbium.  $\text{EuErCuS}_3$ , which contains the magnetic ion  $\text{Er}^{3+}$ , experiences a ferrimagnetic transition at 4.8 K. The compound manifests

three reversible polymorphic transitions in the temperature range 1524-1720 K. It melts in congruently at 1740 K. The magnetic and thermal properties of  $\text{EuErCuS}_3$  are compliant with the data published for the  $\text{ALnCuS}_3$  ( $A = \text{Sr, Eu}$ ;  $\text{Ln} = \text{La-Lu}$ ) isostructural compounds [8,13,14]. Ab initio crystal structure and phonon spectrum calculations have been performed for  $\text{EuErCuS}_3$  in terms of the LCAO-MO approach and density functional theory with the use of the B3LYP hybrid functional. The results of the calculations enabled us to interpret the observed vibrational spectra. Valence state of RE ions ( $\text{Er}^{3+}$  and  $\text{Eu}^{2+}$ ) was checked by combination of XRD and luminescence spectroscopy. Optical band gap was found to be 1.934 eV from diffuse reflectance spectrum. The difference between the measured and calculated values may be due to the fact that in the calculations the f-orbitals of the rare-earth ions were replaced by a pseudopotential. The calculation was carried out in order to reproduce the dynamics of the crystal lattice. For this purpose this approach is fully justified. Moreover, the calculation was carried out for an ideal crystal structure.

Vibrational modes of  $\text{EuErCuS}_3$  lattice are identified in the experimental Raman spectrum.

### **Supporting Information**

Structural cif file; atom coordinates; bond lengths; Raman, luminescence and IR spectra; SEM micrograph; thermal curves.

### **Author contributions**

All authors reviewed and commented on the manuscript.

### **Acknowledgements**

The work was supported by the State budget allocated to the fundamental research in the Ministry of Science and Education, Russian Federation of (Project No. V.45.3.3); by RFBR Grant 17-02-00754; by the Ministry of



### References

- [1] L.D. Gulay, M. Daszkiewicz, V.Ya. Shemet, A. Pietraszko. Crystal structure of the  $R_2PbS_4$  ( $R = Yb$  and  $Lu$ ) compounds. *J. Alloys Compd.* 453 (2008) 143–146. doi: 10.1016/j.jallcom.2006.11.110
- [2] L.D. Gulay, I.D. Olekseyuk, M. Wolcyrz, J. Stepien-Damm, Crystal structures of the  $RCuPbS_3$  ( $R = Tb, Dy, Ho, Er, Tm, Yb$  and  $Lu$ ) compounds, *J. Alloys Comp.* 399 (2005) 189-195. doi:10.1016/j.jallcom.2005.03.036
- [3] L.A. Koscielski, J.A. Ibers, The structural chemistry of quaternary chalcogenides of the type  $AMM'Q_3$ , *Z. Anorgan. Allgem. Chem.* 638 (2012) 2585–2593. doi: 10.1002/zaac.201200301
- [4] T.D. Brennan, J.A. Ibers,  $LaPbCuS_3$ : Cu(I) insertion into the  $a-La_2S_3$  framework, *J. Solid State Chem.* 97 (1992) 377–382. doi:10.1016/0022-4596(92)90046-X
- [5] M. Ohta, S. Hirai, T. Mori, Y. Yajima, T. Nishimura, K. Shimakage, Effect of nonstoichiometry on thermoelectric properties of  $\gamma-Tb_2S_{3-x}$ , *J. Alloys Compd.* 418(2006) 209–212. doi:10.1016/j.jallcom.2005.10.065
- [6] M. Ohta, H. Yuan, S. Hirai, Y. Yajima, T. Nishimura, K. Shimakage, Thermoelectric properties of  $Th_3P_4$ -type rare-earth sulfides  $Ln_2S_3$  ( $Ln = Gd, Tb$ ) prepared by reaction of their oxides with  $CS_2$  gas, *J. Alloys Compd.* 451 (2008) 627–631. doi:10.1016/j.jallcom.2007.04.078
- [7] V.O. Aliev, N.R. Akhmedova, S.M. Agapasheva, O.M. Aliev, Crystal growth and physicochemical properties of structural analogs of krupkaite, *Inorg. Mater.* 45 (2009) 717-722. doi: 10.1134/S0020168509070024
- [8] A.V. Ruseikina, O.V. Andreev, E.O. Galenko, S.I. Koltsov, Trends in thermodynamic parameters of phase transitions of lanthanide sulfides



- SrLnCuS<sub>3</sub> (Ln = La–Lu), *J. Therm. Anal. Calorim.* 128 (2017) 993–999. doi: 10.1007/s10973-016-6010-9
- [9] Yu.A. Murashko, A.V. Ruseikina, A.A. Kislitsyn, O.V. Andreev, Optical and Thermal Properties of the EuLnCuS<sub>3</sub> (Ln = La, Pr, Sm, Gd), *Inorg. Materials*. 51 (2015) 1213–1218. doi:10.1134/S0020168515120079
- [10] R.M. Rojas, M.J. Torralvo, L.C. Otero-Diaz, Thermal behaviour and microstructural characterization of lanthanide sulphides, *J. Therm. Anal. Calorim.* 38 (1992) 961–971. <https://doi.org/10.1007/BF01979429>
- [11] K. Matsumoto, L. Li, S. Hirai, E. Nakamura, D. Murayama, Y. Ura, S. Abe, Large magnetocaloric effect in sintered ferromagnetic EuS, *Cryogenics* (2016), <http://dx.doi.org/10.1016/j.cryogenics.2016.08.001>
- [12] A.V. Ruseikina, L.A. Solov'ev, O.V. Andreev, Crystal structures and properties of SrLnCuS<sub>3</sub> (Ln = La, Pr), *Russ. J. Inorg. Chem.* 59 (2014) 196–201. doi: 10.1134/S0036023614030188.
- [13] M. Wakeshima, F. Furuuchi, Y. Hinatsu, Crystal structures and magnetic properties of novel rare-earth copper sulfides, EuRCuS<sub>3</sub> (R = Y, Gd–Lu), *J. Phys: Condens Matter.* 16 (2004) 5503–5518. doi:10.1088/0953-8984/16/30/012
- [14] F. Furuuchi, M. Wakeshima, Y. Hinatsu, Magnetic properties and (151) Eu Mossbauer effects of mixed valence europium copper sulfide Eu<sub>2</sub>CuS<sub>3</sub>, *J. Solid State Chem.* 177 (2004) 3853–3858. doi:10.1016/j.jssc.2004.04.034
- [15] P. Wu, A.E. Christuk, J.A. Ibers, New Quaternary Chalcogenides BaLnMQ<sub>3</sub> (Ln = Rare Earth; M = Cu, Ag; Q=S, Se). Structure and Property Variation vs Rare-Earth Element, *J. Solid State Chem.* 110 (1994) 337–344. doi: 10.1006/jssc.1994.1177
- [16] A.V. Ruseikina, O.V. Andreev, Regularities of Change in the Structural Parameters of EuLnCuS<sub>3</sub> (Ln = La–Nd, Sm, Gd, Ho), *Russ. J. Inorg. Chem.* 62 (2017) 160–167. doi:10.1134/S0036023617020140

- [17] A.V. Ruseikina, O.V. Andreev, Phase Equilibria in the  $\text{Cu}_2\text{S}$ – $\text{La}_2\text{S}_3$ – $\text{EuS}$  System, *Russ. J. Inorg. Chem.* 62 (2017) 610–618. doi: 10.1134/S0036023617050199
- [18] A.V. Ruseikina, Zh. A. Demchuk, Crystal structure and properties of  $\text{AHoCuS}_3$  (A = Sr or Eu), *Russ. J. Inorg. Chem.* 62 (2017) 27-32. doi:10.1134/S0036023617010168
- [19] A.V. Ruseikina, O.V. Andreev, Phase Equilibria in Systems  $\text{DyCuS}_2$ – $\text{EuS}$  and  $\text{Cu}_2\text{S}$ – $\text{Dy}_2\text{S}_3$ – $\text{EuS}$ , *Russ. J. Inorg. Chem.* 63 (2018) 1494–1500. doi: 10.1134/S0036023618110141
- [20] W. Cook, L. Shiozawa, F. Augustine, The Cu-S Phase Diagram, *J. Appl. Phys.* 41 (1970) 3058-3063.
- [21] D.J. Chakrabarti, D. E. Laughlin, The Cu-S (Copper-Sulfur) System, *Bulletin of Alloy Phase Diagrams* 4 (1983) 254-271. <https://link.springer.com/content/pdf/10.1007/bf02868665.pdf>
- [22] L. Li, S. Hirai, E. Nakamura, H. Yuan, Influences of  $\text{Eu}_2\text{O}_3$  characters and sulfurization conditions on the preparation of  $\text{EuS}$  and its large magnetocaloric effect, *J. Alloys Compd.* 687 (2016) 413-420. <http://dx.doi.org/10.1016/j.jallcom.2016.06.053>
- [23] L. Li, S. Hirai, H. Yuan, Influences of  $\text{Yb}_2\text{O}_3$  characters and sulfurization conditions on preparation of  $\text{Yb}_2\text{S}_3$ , *J. Alloys Compd.* 618 (2015) 742–749. <http://dx.doi.org/10.1016/j.jallcom.2014.08.109>
- [24] A.V. Ruseikina, L.A. Solovyov, M.V. Grigoriev, O.V. Andreev, Crystal structure variations in the series  $\text{SrLnCuS}_3$  (Ln = La, Pr, Sm, Gd, Er and Lu), *Acta Cryst.* C75 (2019) 584–588. <https://doi.org/10.1107/S2053229619004984>
- [25] T. Schleid, F. Lissner, Einkristalle von  $\text{A-Nd}_2\text{S}_3$ ,  $\text{U-Ho}_2\text{S}_3$ ,  $\text{D-Er}_2\text{S}_3$  und  $\text{E-Lu}_2\text{S}_3$  durch Oxidation reduzierter Chloride der Lanthanide mit Schwefel, *Z. Anorgan. Allgem. Chem.* 615 (1992) 19 26. <https://doi.org/10.1002/zaac.19926150905>

- [26] C.M. Forster, W.B. White, Optical absorption edge in rare earth sesqui sulfides, *Mater. Res. Bull.* 41 (2006) 448-454.  
<https://doi.org/10.1016/j.materresbull.2005.07.035>
- [27] V.A. Obolonchik, L.A. Ivanchenko, Properties of europium chalcogenides. Scientific thought, Kiev, 1980.
- [28] K.G. Subhadra, Rao B. Raghavendra, D.B. Sirdeshmukh, X-ray determination of the Debye-Waller factors and Debye temperatures of europium monochalcogenides. *Pramana - J. Phys.* 38 (1992) 681–683.  
doi:10.1007/bf02875064
- [29] P. P. Fedorov, Anneal time determined by studying phase transitions in solid binary systems, *Russ. J. Inorg. Chem.* 37 (1992) 973-968
- [30] J.W. Visser, A fully automatic program for finding the unit cell from powder data, *J. Appl. Cryst.* 2 (1969) 89-95.  
<https://doi.org/10.1107/S0021889869006649>
- [31] P. Lemoine, D. Carré, M. Guittard, Structure du Sulfure d'Europium et de Cuivre  $\text{Eu}_2\text{CuS}_3$ , *Acta Crystallog.* 42 (1986) 390-391. doi: 10.1107/S0108270186096063
- [32] L.A. Solovyov, Full-profile refinement by derivative difference minimization, *J. of Applied Crystallography.* 37 (2004) 743-749. doi: 10.1107/S0021889804015638
- [33] Brandenburg K. Diamond – Visual Crystal Structure Information System Crystal Impact, Postfach 1251, D-53002 Boon.
- [34] A.G. Kolmakov, V.F. Terentyev, M.B. Bakirov, Hardness Measurement Methods, Second Edition, Internet Engineering, Moscow, 2005.  
[http://www.pseudology.org/science/Metody\\_izmer\\_tverdosti2.pdf](http://www.pseudology.org/science/Metody_izmer_tverdosti2.pdf)
- [35] D.A. Velikanov, Vibration magnetometer. RF patent for the invention № 2341810. Publ. 12.20.2008, Bulletin № 35  
<http://www.freepatent.ru/patents/2341810>

- [36] D.A. Velikanov, Magnetometer with a superconducting quantum interferometric sensor. RF patent for the invention № 2481591. Publ. 10.05.2013, Bulletin № 13. <http://www.freepatent.ru/patents/2481591>
- [37] V. G. Tsirelson, Quantum chemistry. Molecules, molecular systems and solids, third edition, Binom. Knowledge Lab, Moscow, 2014.
- [38] A.D. Becke, Density-functional thermochemistry. III. The role of exact exchange, *J. Chem. Phys.* 98 (1993) 5648-5652. doi: 10.1063/1.464913
- [39] P.L. Stephens, F.J. Devlin, C.F. Chabalowski, M.J. Frisch, Ab Initio Calculation of Vibrational Absorption and Circular Dichroism Spectra Using Density Functional Force Fields, *J. Phys. Chem.* 98 (1994) 11623-11627. doi: 10.1021/j100096a001
- [40] R. Dovesi, R. Orlando, A. Erba, C.M. Zicovich-Wilson, B. Civalleri, S. Casassa, L. Maschio, M. Ferrabone, M. De La Pierre, P. D'Arco, Y. Noel, M. Causa, M. Rerat, B. Kirtman, Crystal14: A Program for the Ab Initio Investigation of Crystalline Solids, *Int. J. Quantum Chem.* 114 (2014) 1287-1317. doi:10.1002/qua.24658
- [41] Crystal. <http://www.crystal.unito.it/index.php> (accessed 29 October 2018).
- [42] M. Dolg, H. Stoll, A. Savin, H. Preuss, Energy-adjusted pseudopotentials for the rare earth elements, *Theor. Chim. Acta.* 75 (1989) 173-194. doi: 10.1007/BF00528565
- [43] M. Dolg, H. Stoll, H. Preuss, A combination of quasi relativistic pseudopotential and ligand field calculations for lanthanoid compounds, *Theor. Chim. Acta* 85 (1993) 441-450. doi:10.1007/BF01112983
- [44] Energy-consistent Pseudopotentials of the Stuttgart/Cologne Group. <http://www.tc.uni-koeln.de/PP/clickpse.en.html> (accessed 29 October 2018).

- [45] K. Doll, N.M. Harrison, Chlorine adsorption on the Cu(111) surface, *Chemical Physics Letters* 317 (2000) 282-289. doi: 10.1016/S0009-2614(99)01362-7
- [46] T. Ouazzani, A. Lichanot, C. Pisani and C. Roetti, Relaxation and electronic structure of surfaces in lithium sulphide: A Hartree-Fock ab initio approach, *J. Phys. Chem. Solids* 54 (1993) 1603-1611. doi: 10.1016/0022-3697(93)90356-V
- [47] V.A. Chernyshev, A.E. Nikiforov, V.P. Petrov, A.V. Serdtsev, M.A. Kaschenko, S.A. Klimin. Structure and Lattice Dynamics of Rare-Earth Ferroborate Crystals: Ab Initio Calculation, *Phys. Sol. St.* 58 (2016)1642-1650. doi: 10.1134/S1063783416080096
- [48] V.A. Chernyshev, V.P. Petrov, A.E. Nikiforov, Lattice dynamics of rare-earth titanates with the structure of pyrochlore  $R_2Ti_2O_7$  (R = Gd, Tb, Dy, Ho, Er, Tm, Yb, and Lu): Ab initio calculation, *Phys. Sol. St.* 57 (2015) 996-1002. doi: 10.1134/S1063783415050078
- [49] N.E. Brese and M. O'Keeffe. Bond-valence parameters for solids. *Acta Cryst. B*47 (1991) 192-197. doi.org/10.1107/S0108768190011041
- [50] Néel L. Magnetism and Local Molecular Field, *Science* 174 (1971) 985-992. doi: 10.1126/science.174.4013.985
- [51] N.V. Kudrevatykh, A.S. Volegov, Magnetism of rare earth metals and their intermetallic compounds, pub. UralUniversity, Yekaterinburg, 2015. [http://elar.urfu.ru/bitstream/10995/36121/1/978-5-7996-1604-5\\_2015.pdf](http://elar.urfu.ru/bitstream/10995/36121/1/978-5-7996-1604-5_2015.pdf)
- [52] J. Jensen, A.R. Mackintosh. Rare Earth Magnetism. Structures and Excitations, Clarendon Press, Oxford, 1991. <https://www.fys.ku.dk/~jjensen/Book/Ebook.pdf>
- [53] W. Sun, X. Yang, M. Yu, L. Wang, Q. Zhang. Experimental and theoretical studies on the stable synthesis of a laser protective coating material erbium oxysulfide. *J Mater Sci: Mater Electron* 29 (2017) 2406-2415. doi: 10.1007/s10854-017-8159-9

- [54] Xiao Xia Zhang, King Fai Li, Kok Wai Cheah, Xianju Zhou, Peter A. Tanner. 1.54 and 1.75  $\mu\text{m}$  infrared luminescence of  $\text{Y}_2\text{O}_3:\text{Er}^{3+}$ . Chem. Phys. Lett. 400 (2004) 331–335.

ACCEPTED MANUSCRIPT

## Captions

**Fig. 1.** Measured (1), calculated (2), and difference (3) X-ray diffraction profiles of a  $\text{EuErCuS}_3$  sample after DDM structure refinement. The bars indicate the peaks positions of the major phase and  $\text{Er}_2\text{O}_2\text{S}$ .

**Fig. 2.** [010] perspective projections of the  $\text{EuErCuS}_3$  structure.

**Fig. 3.** SEM micrograph and thermal curves for a  $\text{EuErCuS}_3$  sample. The DSC curve is black, the TG curve is green.

**Fig. 4.** Magnetic moment versus magnetic field for  $\text{EuErCuS}_3$ .


**Fig. 5.** Temperature-dependent reciprocal magnetic susceptibility for a  $\text{EuErCuS}_3$  sample.

**Fig. 6.** Raman and luminescence spectra of the  $\text{EuErCuS}_3$  crystal excited by 514.5- and 457.9-nm laser beams. The bars indicate the calculated Raman frequencies of  $\text{EuErCuS}_3$ .


**Fig. 7.** IR spectrum of  $\text{EuErCuS}_3$ . The bars indicate the calculated IR vibrational frequencies in  $\text{EuErCuS}_3$ .  $\text{EuErCuS}_3$  is IR-transparent in the wave number window  $4000\text{--}400\text{ cm}^{-1}$ .

**Fig. 8.**  $\text{EuErCuS}_3$  band structure and the density of states.


**Fig. 9.** Diffuse reflection spectra of  $\text{EuErCuS}_3$ .

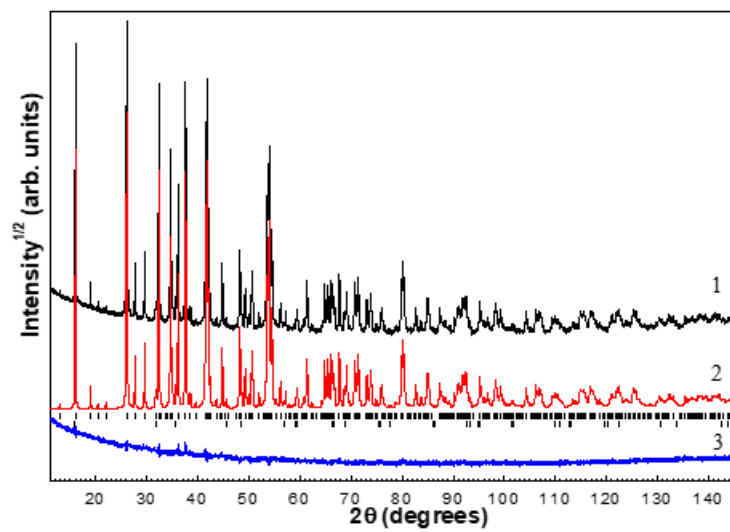




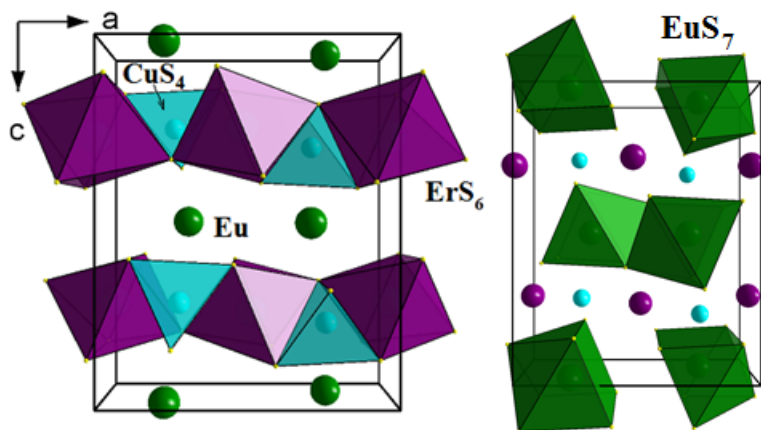


ACCEPTED MANUSCRIPT


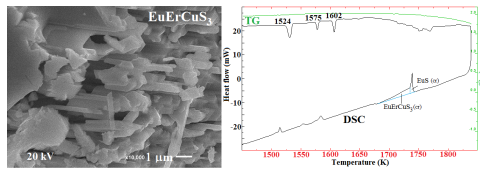


ACCEPTED MANUSCRIPT

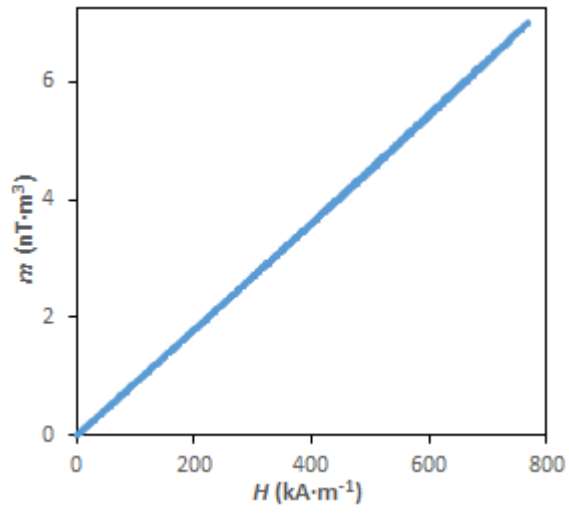



ACCEPTED MANUSCRIPT

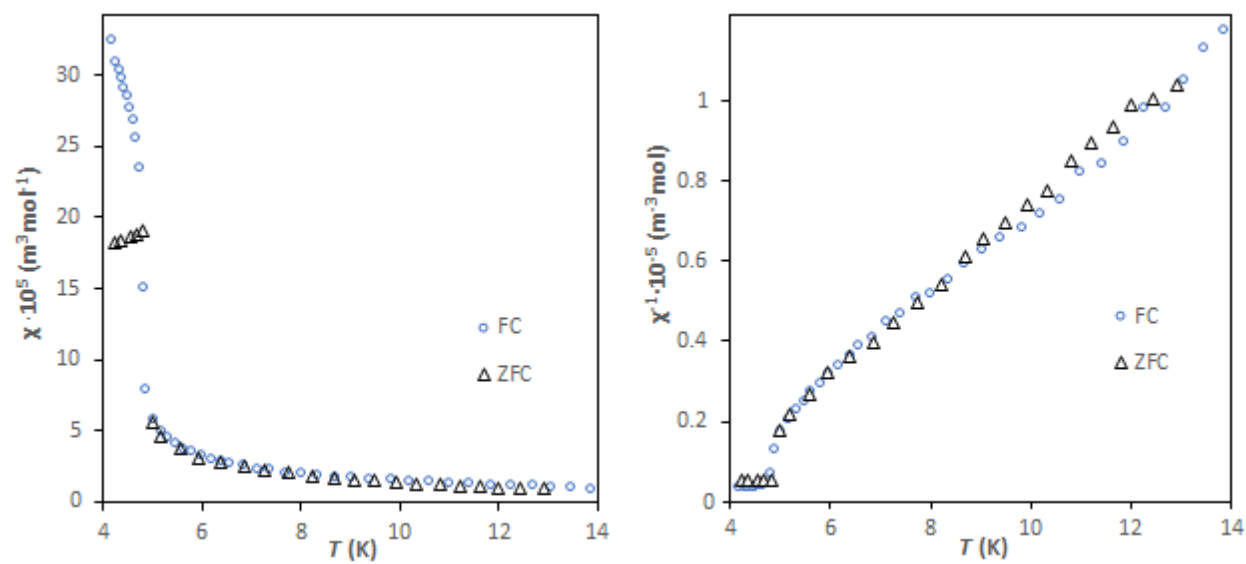


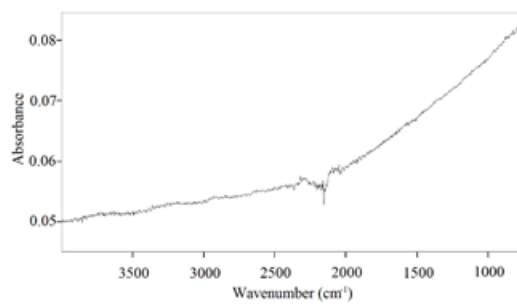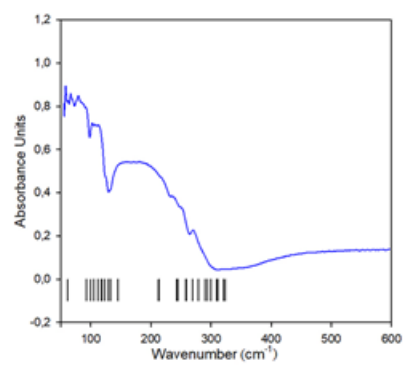

ACCEPTED MANUSCRIPT

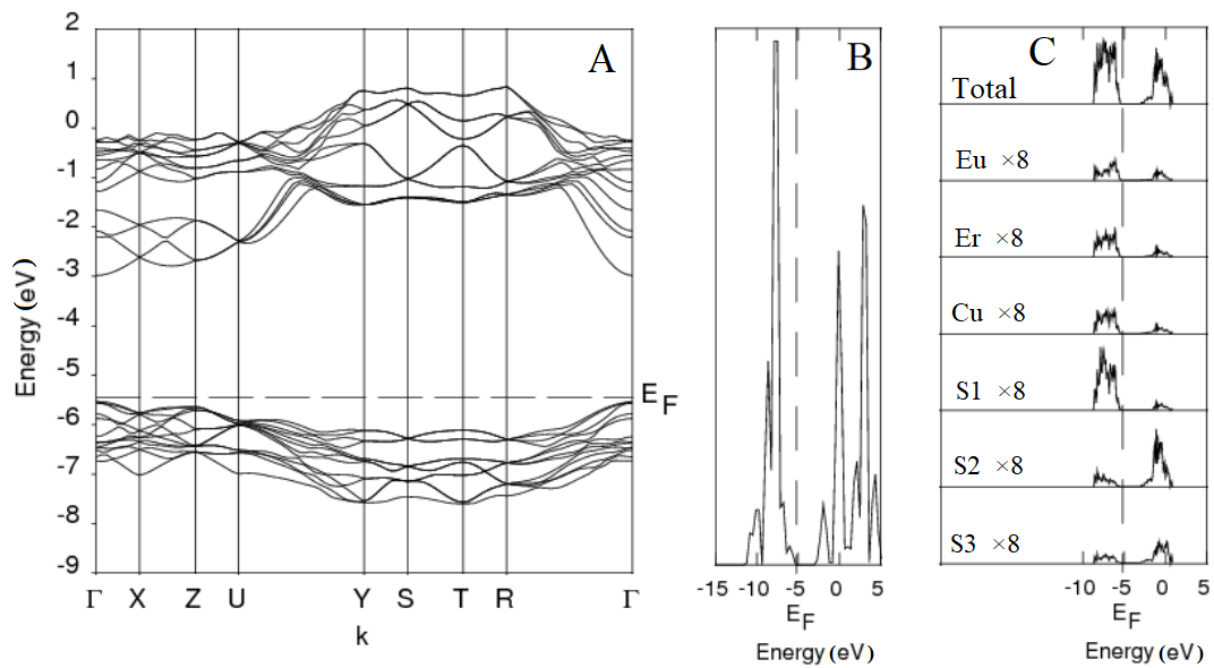

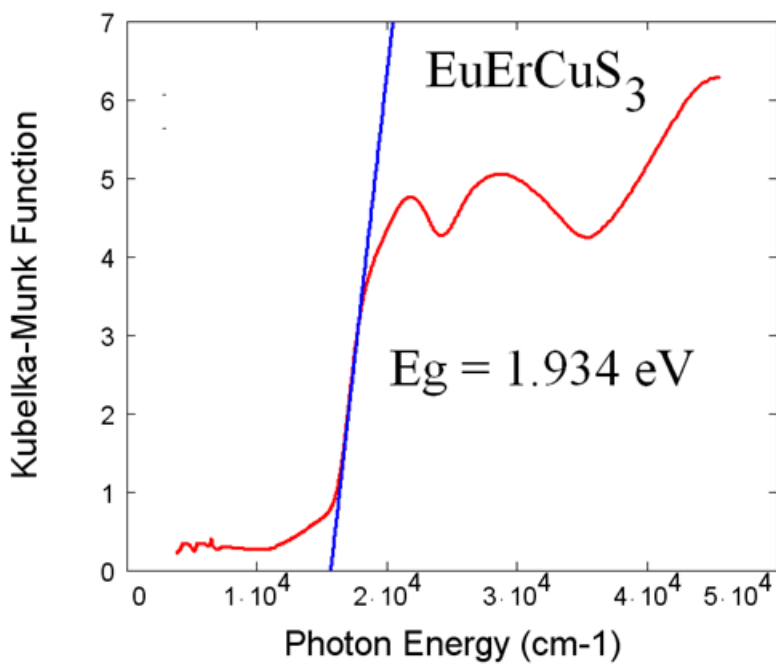

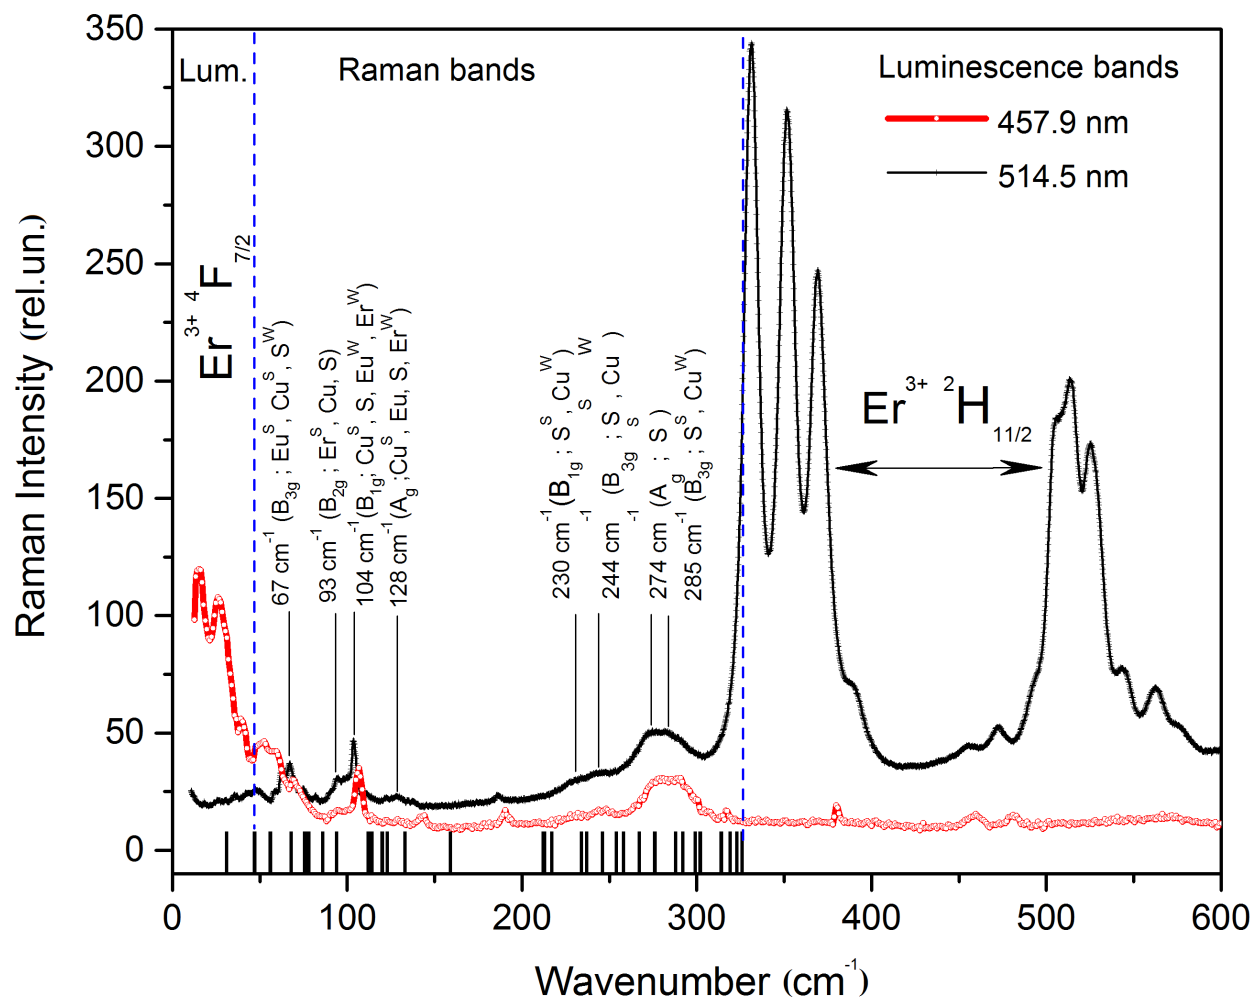



**Highlights**

1. The  $\text{EuLnCuS}_3$  compound exhibit ferrimagnetic properties at low temperature.
2. The polymorphic transitions for  $\text{EuLnCuS}_3$  are identified at high temperature.
3.  $\text{EuErCuS}_3$  is a wide-gap semiconductor.
4. Valence purity of  $\text{Eu}^{2+}$  is proved via both XRD and optical techniques
5. The ab initio calculation of the Raman and infrared spectra of  $\text{EuErCuS}_3$ , made for Pnma symmetry, agrees well with experiment.