

Phosphomolybdic Acid Supported on Silica Gel as an Efficient and Reusable Catalyst for Cyanosilylation of Aldehydes

Santosh T. Kadam and Sung Soo Kim*

Department of Chemistry, Inha University, Incheon 402-751, Korea. *E-mail: sungsoo@inha.ac.kr

Received March 18, 2008

Phosphomolybdic acid supported on silica gel (PMA-SiO₂) is an efficient catalyst for the activation of TMSCN for the facile cyanosilylation of various aldehydes. Cyano transfer from TMSCN to aldehyde proceeds smoothly at rt in presence of 0.8 mol % of PMA-SiO₂ leading to a range of cyanosilylether in excellent yield (mostly over 93%) within short reaction time (30 min). The catalyst can be recovered and reused several times without loss of activity.

Key Words : PMA-SiO₂, Heterogeneous catalysis, Cyanosilylation, Aldehydes

Introduction

Cyanosilylation of carbonyl compound is an efficient procedure for synthesis of silylated cyanohydrins. Cyanohydrins represents one of the most valuable synthon that can be elaborated into a variety of useful synthetic building blocks, such as α -hydroxy acids, α -hydroxy aldehyde, 1,2-diols, α -amino alcohol.¹⁻⁵ Because of their importance in organic synthesis and life science, a large body of work has been devoted to the development of synthesis of cyanohydrin. One of the most common methods to prepare cyanohydrin involves the cyanosilylation of carbonyl compound using TMSCN (trimethylsilyl cyanide). Transfer of cyano group from TMSCN to carbonyl compound can be catalyzed by plethora of reagents,⁶⁻¹⁵ including Lewis acids, Lewis base, metal alkoxide, bifunctional catalyst and inorganic salts. Our group has developed numerous chiral and achiral catalytic systems for the cyanosilylation of carbonyl compound.¹⁶⁻²⁷ Phosphomolybdic acid belongs to the class of heteropolyacids (HPA). HPA are several times stronger than H₂SO₄, TsOH, BF₃·Et₂O and ZnCl₂.²⁸ This makes it possible to carry out reaction in low concentration and lower temperature. Synthetically a variety of method has been developed and commercialized using HPA as catalysts. For example oxidation of alcohol,²⁹ Fries rearrangement of phenyl acetate,³⁰ regioselective ring opening of aziridines,³¹ chemoselective deprotection of isopropylidene acetals³² and hydrolysis of *tert*-butyldimethylsilyl ether³³ have been reported with HPA.

Results and Discussion

In continuation of our efforts to explore the synthetic utility of phosphomolybdic acid,³⁴ we report herein cyanosilylation of aldehydes with TMSCN using 0.8 mol% of phosphomolybdic acid supported on silica gel. Anisaldehyde (1 mmol) reacts with TMSCN (1.2 mmol) at rt in presence of 0.8 mol % of PMA-SiO₂⁴⁵ to give 97% yield within 10 min. Accordingly we further examine the structurally diverse aldehydes like aliphatic, aromatic and heterocyclic aldehydes. Aromatic aldehydes with electron-donating groups such as

anisaldehyde, *p*-tolualdehyde and 2-hydroxy-4-methoxy benzaldehyde produce 97, 91 and 94% yield, respectively (entries 1, 2 and 3). Naphthaldehyde gave the corresponding silylether in excellent yield (entry 6). The effect of substituent on aromatic ring plays very important role in cyanosilylation. Even unsubstituted benzaldehyde gives no

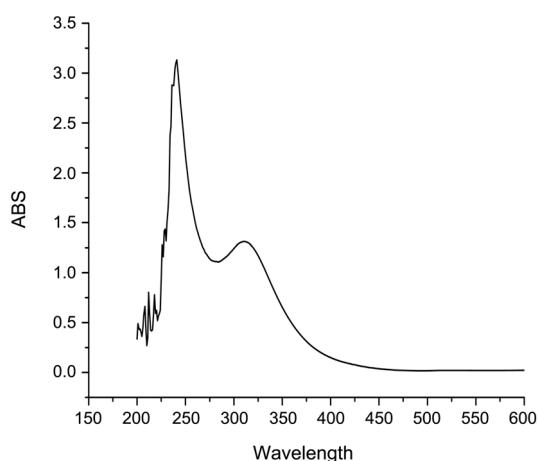


Figure 1. UV-Visible Spectrum of PMA + THF.

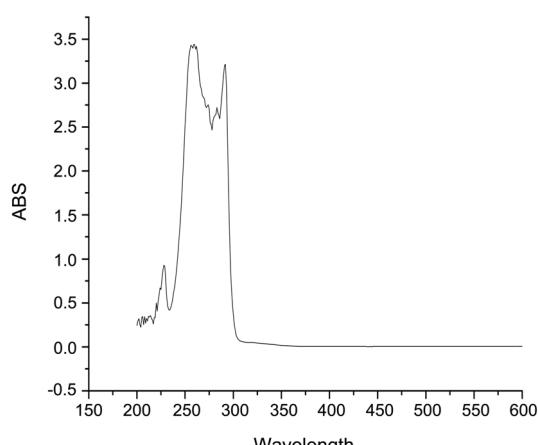


Figure 2. UV-Visible Spectrum of Reaction Mixture.

Table 1. Cyanosilylation of various aldehydes with TMSCN catalyzed by PMA-SiO₂^a

Entry	Substrate	Product (3) ^b	Time (min)	Yield (%) ^c		
					PMA-SiO ₂ , 0.8 mol %	OTMS
1	4-MeO-C ₆ H ₄ CHO	3a	10	97		
			24h	87 ³⁵		
			12h	60 ³⁶		
			0.5h	69 ³⁷		
			10	91 ³⁸		
2	4-Me-C ₆ H ₄ CHO	3b	12	91		
			24h	92 ³⁵		
			12h	80 ³⁶		
3	4-MeO-2-OHC ₆ H ₃ CHO	3c	10	94		
4	3-OPh-C ₆ H ₄ CHO	3d	18	88		
5	2-Cl-C ₆ H ₄ CHO	3e	35	64		
6	C ₁₀ H ₇ CHO	3f	8	97		
			5h	90 ³⁹		
			0.5h	94 ³⁷		
			0.5h	99 ⁴⁰		
			10	85 ³⁸		
			15	97		
7	C ₆ H ₅ CH=CHCHO	3g	24h	94 ³⁵		
			12h	63 ³⁶		
			3h	75 ⁴²		
			1h	81 ⁴¹		
			0.5h	75 ³⁷		
8	C ₆ H ₅ CH ₂ CHO	3h	5	98		
9	(Me) ₂ -CHCHO	3i	23	77		
10	(Me) ₂ CHCHCH ₂ CH(Me)-CH ₂ CHO	3j	28	82		
11	Me(CH ₂) ₂ CHO	3k	8	95		
12	Me(CH ₂) ₄ CHO	3l	16	90		
13	C ₆ H ₉ CHO	3m	20	93		
14	C ₆ H ₁₁ CHO	3n	12	93		
			2h	99 ⁴⁰		
			0.5h	94 ⁴⁴		
15	3-CNC ₆ H ₄ CHO	3o	3h	58 ^d		
16	C ₄ H ₃ OCHO	3p	12h	NR		

^a60 mg of PMA-SiO₂ (0.008 mmol) was added to a mixture of 1.0 mmol of benzaldehyde and 1.2 mmol of TMSCN in THF. ^bAll products were characterized and compared by ¹H, ¹³C NMR with literature [16-21]. ^cIsolated yield. ^d1.8 mol % catalyst used.

product. Trifluoro-*p*-tolualdehyde, 3- and 4-chlorobenzaldehyde are also unable to yield corresponding cyanosilylether even after overnight reaction. Among all the electron-withdrawing chlorine substituent only 2-chlorobenzaldehyde produces 64% yield within 35 min (entry 5). Unsaturated branched citral is smoothly converted to cyanosilylether in 82% yield in 28 min (entry 10). Cinnamaldehyde gives 97% yield within 15 min (entry 7). Aliphatic and branched aliphatic aldehydes were silylated in good to high yield. Butyraldehyde and hexanal gives 95 and 90% of yield in 8 and 16 min, respectively (entries 11 and 12). But isobutyraldehyde requires longer reaction time (23 min) with less

Table 2. Reusability of the Catalyst for Cyanosilylation of Anis-aldehyde

No	Number of cycles	Time (min)	Yield (%)
1	1	10	95
2	2	24	94
3	3	45	94

yield compared to other aliphatic aldehydes (entry 9). Cyclic aliphatic aldehydes such as 1,2,3,6-tetrahydrobenzaldehyde and cyclohexane carboxaldehyde undergo cyanosilylation in 20 and 12 min both with 93% yield (entries 13 and 14). Acid sensitive 2-furaldehyde is heterocyclic compound which is unable to produce corresponding silylether under this reaction condition. 3-Cyanobenzaldehyde produces only 58% yield in quite long reaction time (entry 15).

PMA-SiO₂ can be reused three successive runs with slight decrease in yield and slight increase in reaction time (Table 2). The UV-visible spectrum of reaction mixture is recorded to identify the presence of PMA in solution. Figure 1 shows the characteristic absorption band of PMA (PMA + THF) at 310 nm⁴⁴ and Figure 2 is the for reaction mixture that shows the absence of PMA. This clearly indicates that there is no leaching of PMA from silica. PMA-SiO₂ is active and effective catalytic system considering the reaction time and yield comparing to literature catalytic systems³⁵⁻⁴³ (Table 1).

Conclusion

We have described a simple, convenient and efficient protocol for the cyanosilylation of aldehydes using a phosphomolybdic acid supported on silica gel as reusable catalyst. The notable features of this method are mild reaction condition, simplicity in operation and environmentally friendly. Benzaldehyde containing electron-withdrawing groups and 2-furaldehyde are generally quite unreactive towards the cyanosilylation. The catalyst can be recovered by simple filtration and reused in subsequent runs.

Experimental

¹H NMR (200 MHz) spectra were recorded with Varian Gemini 2000 spectrometer. Chemical shifts are reported in CDCl₃ with tetramethylsilane as an internal standard. ¹³C NMR data were collected on a Varian Gemini 400 spectrometer (100 MHz). Some compounds are also identified by HRMS (EI+) by Jeol DMX.

Spectroscopic data for selected compounds.

2-(4-Methoxyphenyl)-2-(trimethylsilyloxy)acetonitrile (entry 1): ¹H NMR (200 MHz, CDCl₃): δ = 0.204 (s, 9H), 3.82 (s, 3H), 5.43 (s, 1H), 6.90-6.93 (d, 2H), 7.37-7.39 (d, 2H). ¹³C NMR (100 MHz, CDCl₃): δ = -0.10, 55.38, 63.38, 114.22, 119.32, 127.86, 128.46, 160.33. HRMS (EI): m/z [M+H]⁺ calcd. for C₁₂H₁₇NO₂Si: 235.1029; found: 235.1026.

2-(2-Hydroxy-4-methoxyphenyl)-2-(trimethylsilyloxy)acetonitrile (entry 3): ¹H NMR (200 MHz, CDCl₃): δ = 0.199 (s, 9H), 3.78 (s, 3H), 5.78, (s, 1H), 7.26 (d, 2H) 7.29

(d, 1H), 9.24 (s, 1H). ^{13}C NMR (100 MHz, CDCl_3): $\delta = -0.199, 55.33, 58.87, 104.90, 1.633, 119.49, 128.85, 153.084, 160.11$.

(E)-4-Phenyl-2-(trimethylsilyloxy)but-3-enenitrile (entry 7): ^1H NMR (200 MHz, CDCl_3) $\delta = 0.25$ (s, 9H), 5.10-5.12 (d, 1H), 6.19-6.2 (d, 1H), 6.79-6.8 (d, 1H) 7.35-7.39 (m, 5H). ^{13}C NMR (100 MHz, CDCl_3): $\delta = -0.02, 62.34, 118.48, 127.07, 128.45, 128.84, 128.89, 134.08, 135.16$. HRMS (EI): m/z [M+H] $^+$ calcd. for $\text{C}_{13}\text{H}_{17}\text{NOSi}$: 231.1079; found: 231.1075.

2-(Cyclohex-3-enyl)-2-(trimethylsilyloxy)acetonitrile (entry 13): ^1H NMR (200 MHz, CDCl_3): $\delta = 0.21$ (s, 9H), 1.60-2.12 (m, 7H), 4.23-4.27 (m, 1H), 5.70 (s, 2H). ^{13}C NMR (100 MHz, CDCl_3): $\delta = -0.305, 23.93, 24.49, 26.80, 39.20, 65.84, 119.07, 124.89, 126.93$. HRMS (EI): m/z [M+H] $^+$ calcd. for $\text{C}_{11}\text{H}_{19}\text{NOSi}$: 209.1236; found: 209.1236.

Acknowledgments. Authors thank the Center for Biological Modulators for financial support. Korea research Foundation should also be mentioned for BK21 provided to Inha University.

References

- North, M. *Tetrahedron: Asymmetry* **2003**, *14*, 147.
- Brunel, J. M.; Holmes, P. I. *Angew. Chem. Int. Ed.* **2004**, *43*, 2752.
- Gregory, R. J. H. *Chem. Rev.* **1999**, *99*, 3649.
- Furin, G. G.; Vyazankina, O. A.; Gostevsky, B. A.; Vyazankin, N. S. *Tetrahedron* **1988**, *44*, 2675.
- Rasmussen, J. K.; Heilmann, S. M.; Krebski, L. R.; Larson, G. L. *Ed. JAI Press London* **1991**, *1*, 65.
- Ryu, D. H.; Corey, E. J. *J. Am. Chem. Soc.* **2004**, *126*, 8106.
- Ryu, D. H.; Corey, E. J. *J. Am. Chem. Soc.* **2005**, *127*, 5384.
- Jacobsen, E. N.; Fuerst, D. E. *J. Am. Chem. Soc.* **2005**, *127*, 8964.
- Hamsshma, Y. S. D.; Shibasaki, K. M. *J. Am. Chem. Soc.* **1999**, *121*, 2641.
- Fetterly, B. M.; Verkade, J. H. *Tetrahedron Lett.* **2005**, *46*, 8061.
- Hayashi, M.; Miyamoto, Y.; Inoue, T.; Oguni, N. *J. Org. Chem.* **1993**, *58*, 1515.
- Hatano, M.; Lkeno, T.; Miyamoto, T.; Ishihara, K. *J. Am. Chem. Soc.* **2005**, *127*, 10776.
- Karimi, B.; Ma'man, L. *Org. Lett.* **2004**, *4813*.
- Song, J. J.; Gallou, J. T.; Reeves, J. T.; Tan, Z.; Yee, N. K.; Senanake, C. H. *J. Org. Chem.* **2006**, *71*, 1273.
- Wang, L.; Huang, X.; Jiang, J.; Liu, X.; Feng, X. *Tetrahedron Lett.* **2006**, *47*, 1581.
- Kim, S. S.; Rajagopal, G.; Song, D. G. *J. Organomet. Chem.* **2004**, *689*, 1734.
- Kim, S. S.; Rajagopal, G. *Synthesis* **2007**, *2*, 215.
- Kim, S. S.; Lee, S. H.; Kwak, J. M. *Tetrahedron: Asymmetry* **2006**, *17*, 1165.
- Kim, S. S.; Song, D. H. *Eur. J. Org. Chem.* **2005**, *1777*.
- Kim, S. S.; Lee, S. H. *Synthetic Commun.* **2005**, *35*, 751.
- Kim, S. S.; Kim, D. W.; Rajgopal, G. *Synthesis* **2004**, *2*, 213.
- Kim, S. S.; Song, D. H. *Lett. Org. Chem.* **2004**, *1*, 264.
- Kim, S. S. *Pure and Applied Chem.* **2006**, *78*, 977.
- Kim, S. S.; George, S. C. *Bull. Korean Chem. Soc.* **2007**, *28*, 1167.
- Kim, S. S.; Kwak, J. M. *Tetrahedron* **2006**, *62*, 49.
- Kim, S. S.; George, S. C.; Kadam, S. T. *Appl. Organometallic Chem.* **2007**, *21*, 994.
- Kim, S. S.; Kwak, J. M.; George, S. C. *Appl. Organometallic Chem.* **2007**, *21*, 809.
- Kozhevnikov, I. V. *Russ. Chem. Rev.* **1987**, *56*, 811.
- Firouzabadi, H.; Iranpoor, N.; Amani, K. *Synthesis* **2003**, *408*.
- Kozhevnikova, E. F.; Derouane, E. G.; Kozhevnikov, I. V. *Chem. Commun.* **2002**, 1178.
- Kishore Kumar, G. D.; Baskaran, S. *Synlett* **2004**, *1719*.
- Yadav, J. S.; Raghavendra, S.; Satyanarayana, M.; Balanarasaiah, E. *Synlett* **2005**, *2461*.
- Kishore Kumar, G. D.; Baskaran, S. *J. Org. Chem.* **2005**, *70*, 4520.
- Kim, S. S.; Kadam, S. T. *Synthesis* **2008**, *2*, 267.
- Shen, Z. L.; Ji, S. J.; Loh, T. P. *Tetrahedron Lett.* **2005**, *46*, 3137.
- Lakshimikantm, M.; Seekanth, P.; Santhi, P. L. *Green Chem.* **2000**, *47*.
- Suzuki, Y.; Abu Bakar, M. D.; Sato, M. *Tetrahedron* **2005**, *62*, 4227.
- Khan, N-UL.; Agrawal, R. K.; Abdi, S. H. R.; Sing, S.; Jasra, R. *V. J. Organomet. Chem.* **2007**, *692*, 4361.
- Mei, L. *J. Mol. Catal. A* **2005**, *227*, 183.
- Fetterly, B. M.; Verkade, J. H. *Tetrahedron Lett.* **2005**, *46*, 8061.
- De, S. K.; Gibbs, R. A. *J. Mol. Catal. A* **2005**, *232*, 123.
- Saravanan, P.; Anand, R. V.; Singh, V. K. *Tetrahedron Lett.* **1998**, *39*, 3823.
- Kurono, N.; Yamaguchi, M.; Suzuki, K.; Ohkuma, T. *J. Org. Chem.* **2005**, *70*, 6530.
- Zhang, G.; He, T.; Chen, Y.; Yang, W.; Yao, J. *Phys. Chem. Phys.* **2003**, *5*, 2751.
- Amini, M. M.; Shaabani, A.; Bazgir, A. *Cata. Commun.* **2006**, *7*, 843.